

World Journal of *Stem Cells*

World J Stem Cells 2017 July 26; 9(7): 98-106





Editorial Board

2016-2019

The *World Journal of Stem Cells* Editorial Board consists of 700 members, representing a team of worldwide experts in infectious diseases. They are from 44 countries, including Argentina (2), Australia (9), Austria (6), Belgium (3), Brazil (9), Canada (16), China (73), Cyprus (2), Czech Republic (5), Denmark (6), Ecuador (1), Egypt (2), Finland (3), France (19), Germany (32), Greece (1), Hungary (3), India (10), Iran (9), Ireland (3), Israel (10), Italy (52), Japan (54), Jordan (1), Malaysia (1), Mexico (1), Morocco (1), Netherlands (6), Norway (2), Portugal (1), Romania (1), Russia (3), Singapore (19), Slovakia (1), South Korea (44), Spain (16), Sweden (3), Switzerland (5), Thailand (1), Tunisia (1), Turkey (5), United Arab Emirates (1), United Kingdom (28), and United States (229).

EDITORS-IN-CHIEF

Tong Cao, *Singapore*

Oscar Kuang-Sheng Lee, *Taipei*

ASSOCIATE EDITORS

Wei Cui, *London*

Paul Lu, *La Jolla*

Yuko Miyagoe-Suzuki, *Tokyo*

Seyed J Mowla, *Tehran*

Kai C Sonntag, *Massachusetts*

Bao-Hong Zhang, *Greenville*

GUEST EDITORIAL BOARD MEMBERS

Chia-Ning Chang, *Taichung*

Chuck Ching-Kuey Chao, *Taoyuan*

Chie-Pein Chen, *Taipei*

Fu-Chou Cheng, *Taichung*

Ing-Ming Chiu, *Jhunan*

Akon Higuchi, *Taoyuan*

Hossein Hosseinkhani, *Taipei*

Yu-Chen Hu, *Hsinchu*

Yen-Hua Huang, *Taipei*

Jyh-Cherng Ju, *Taichung*

Steven Shoei-Lung Li, *Kaohsiung*

Feng-Huei Lin, *Zhunan Town*

Shing-Hwa Liu, *Taipei*

Jui-Sheng Sun, *Taipei*

Tzu-Hao Wang, *Taoyuan*

Yau-Huei Wei, *New Taipei City*

Kuo-Liang Yang, *Hualien*

Chao-Ling Yao, *Chung-Li City*

MEMBERS OF THE EDITORIAL BOARD



Argentina

Federico J Benetti, *Santa Fe*

Luis E Politi, *Bahia Blanca*



Australia

Michael K Atkinson, *Brisbane*

Peter M Bartold, *South Australia*

Jeremy M Crook, *Victoria*

Simon A Koblar, *South Australia*

Kuldip S Sidhu, *Sydney*

Paul J Verma, *Clayton Vic*

Ernst J Wolvetang, *Brisbane*

Cory J Xian, *South Australia*

Xin-Fu Zhou, *Adelaide*



Austria

Ludwig Aigner, *Salzburg*

Ferdinand Frauscher, *Innsbruck*

Regina Grillari, *Vienna*

Mariann Gyongyosi, *Vienna*

Günter Lepperdinger, *Innsbruck*

Peter Valent, *Vienna*



Belgium

Yves Beguin, *Liege*

Mieke Geens, *Brussels*

Najimi Mustapha, *Brussels*



Brazil

Niels OS Camara, *Cidade Universitária*

Armando DM Carvalho, *Botucatu*

Katherine AT de Carvalho, *Curitiba*

Regina CDS Goldenberg, *Rio de Janeiro*

Irina Kerkis, *Sao Paulo*

Ana H da Rosa Paz, *Porto Alegre*

Luís C De Moraes Sobrinho Porto, *Rio de Janeiro RJ*

Rodrigo Resende, *Belo Horizonte*

Naiara Z Saraiva, *Jaboticabal*



Canada

Borhane Annabi, *Quebec*

Long-Jun Dai, *Vancouver*

Connie J Eaves, *Vancouver*

Santokh Gill, *Ottawa*

Jeffrey T Henderson, *Toronto*

Rosario Isasi, *Quebec*

Xiaoyan Jiang, *Vancouver*

Seung U Kim, *Vancouver*

William A King, *Guelph*

Ren-Ke Li, *Toronto*

Zubin Master, *Edmonton*

Christopher Naugler, *Calgary*

Dominique Shum-Tim, *Quebec*

Jean-Francois Tanguay, *Quebec*

Kursad Turksen, *Ottawa*

Lisheng Wang, *Ontario*



China

Xiu-Wu Bian, *Chongqing*

Andrew Burd, *Hong Kong*

Kai-Yong Cai, *Chongqing*

CHI-KAI Chen, *Shantou*

Ling-Yi Chen, *Tianjin*

Fu-Zhai Cui, *Beijing*

Yong Dai, *Shenzhen*

Yu-Cheng Dai, *Nanchang*

Li Deng, *Chengdu*

Jian Dong, *Shanghai*

Jian-Xin Gao, *Shanghai*
 Zhi-Liang Gao, *Guangzhou*
 Zi-Kuan Guo, *Beijing*
 Zhong-Chao Han, *Tianjin*
 Ling-Ling Hou, *Beijing*
 Yi-Ping Hu, *Shanghai*
 Jian-Guo Hu, *Bengbu*
 Jian-Hua Huang, *Yinchuan*
 Dong-Sheng Huang, *Guangzhou*
 Jin-Jun Li, *Shanghai*
 Jun Dou, *Nanjing*
 Jiu-Hong Kang, *Shanghai*
 Dong-Mei Lai, *Shanghai*
 Anskar Yu-Hung Leung, *Hong Kong*
 Gui-Rong Li, *Hong Kong*
 Xiang-Yun Li, *Baoding*
 Xiao-Rong Li, *Tianjin*
 Zong-Jin Li, *Tianjin*
 Gang Li, *Hong Kong*
 Qizhou Lian, *Hong Kong*
 Hong Liao, *Nanjing*
 Kai-Yan Liu, *Beijing*
 Lei Liu, *Chengdu*
 Pauline Po-Yee Lui, *Hong Kong*
 Cai-Ping Ren, *Changsha*
 Ren-Hua Wu, *Shantou*
 Chun-Meng Shi, *Chongqing*
 Shu-Ren Zhang, *Beijing*
 Guan-Bin Song, *Chongqing*
 Jing-He Tan, *Tanan*
 Jin-Fu Wang, *Hangzhou*
 Tie-Qiao Wen, *Shanghai*
 Ji Wu, *Shanghai*
 Ruian Xu, *Xiamen*
 Xue-Tao Pei, *Beijing*
 Chuan Ye, *Guiyang*
 Yi-Jia Lou, *Hangzhou*
 Xi-Yong Yu, *Guangzhou*
 Hao Zhang, *Beijing*
 Yun-Hai Zhang, *Hefei*
 Lei Zhao, *Wuhan*
 Xiao-Gang Zhong, *Nanning*
 Bo Zhu, *Chongqing*
 Zhong-Min Zou, *Chongqing*



Cyprus

Pantelis Georgiades, *Nicosia*
 Nedime Serakinci, *Nicosia*



Czech Republic

Eva Bártová, *Brno*
 Petr Dvorak, *Brno*
 Jaroslav Mokry, *Hradec Kralove*
 Jakub Suchánek, *Hradec Kralove*
 Holan Vladimír, *Videnska*



Denmark

Basem M Abdallah, *Odense*
 Soren P Sheikh, *Odense*
 Lin Lin, *Tjele*
 Poul Hyttel, *Frederiksberg C*
 Morten Meyer, *Blommenslyst*
 Vladimir Zachar, *Aalborg*



Ecuador

Pedro M Aponte, *Quito*



Egypt

Mohamed A Ghoneim, *Mansora*
 Alaa E Ismail, *Cairo*



Finland

Jukka Partanen, *Helsinki*
 Petri Salven, *Helsinki*
 Heli TK Skottman, *Tampere*



France

Ez-Zoubir Amri, *Nice Cedex*
 Bernard Binetruy, *Marseille*
 Philippe Bourin, *Toulouse*
 Alain Chapel, *Fontenay-Aux-Roses*
 Yong Chen, *Paris*
 Dario Coleti, *Paris*
 Christelle Coraux, *Reims*
 Anne C Fernandez, *Montpellier*
 loic Fouillard, *Paris*
 Norbert-Claude Gorin, *Paris*
 Enzo Lalli, *Valbonne*
 Gwendal Lazennec, *Montpellier*
 Nathalie Lefort, *Eury*
 Laurent Lescaudron, *Nantes*
 David Magne, *Villeurbanne Cedex*
 Muriel Perron, *Orsay*
 Xavier Thomas, *Lyon*
 Ali G Turhan, *Villejuif*
 Didier Wion, *Grenoble*



Germany

Nasreddin Abolmaali, *Dresden*
 James Adjaye, *Berlin*
 Halvard Bonig, *Frankfurt*
 Sven Brandau, *Essen*
 Christian Buske, *Munich*
 Denis Corbeil, *Dresden*
 Hassan Dihazi, *Goettingen*
 Thomas Dittmar, *Witten*
 Juergen Dittmer, *Halle*
 Frank Edenhofer, *Bonn*
 Ursula M Gehling, *Hamburg*
 Alexander Ghanem, *Bonn*
 Eric Gottwald, *Karlsruhe*
 Gerhard Gross, *Braunschweig*
 Kaomei Guan, *Goettingen*
 Christel Herold-Mende, *Heidelberg*
 Jorg Kleeff, *Munich*
 Gesine Kogler, *Dusseldorf*
 Steffen Koschmieder, *Munster*
 Nan Ma, *Rostock*
 Ulrich R Mahlke, *Homburg/Saar*
 Ulrich Martin, *Hannover*
 Kurt P Pfannkuche, *Cologne*
 Michael Platten, *Heidelberg*
 Arjang Ruhparwar, *Heidelberg*
 Heinrich Sauer, *Giessen*

Richard Schafer, *Tübingen*
 Nils O Schmidt, *Hamburg*
 Sonja Schrepfer, *Hamburg*
 Dimitry Spitkovsky, *Cologne*
 Sergey V Tokalov, *Dresden*
 Wolfgang Wagner, *Aachen*



Greece

Nicholas P Anagnostou, *Athens*



Hungary

Andras Dinnyes, *Godollo*
 Balazs Sarkadi, *Budapest*
 Ferenc Uher, *Budapest*



India

Anirban Basu, *Haryana*
 Chiranjib Chakraborty, *Vellore*
 Gurudutta U Gangenahalli, *Delhi*
 Minal Garg, *Lucknow*
 Devendra K Gupta, *New Delhi*
 Asok Mukhopadhyay, *New Delhi*
 Riaz A Shah, *Kashmir*
 Prathibha H Shetty, *Navi Mumbai*
 Anjali Shiras, *Maharashtra*
 Malancha Ta, *Bangalore*



Iran

Hossein Baharvand, *Tehran*
 Mohamadreza B Eslaminejad, *Tehran*
 Iraj R Kashani, *Tehran*
 Mansoureh Movahedin, *Tehran*
 Ghasem Hosseini Salekdeh, *Tehran*
 Masoud Soleimani, *Tehran*
 Mohammad M Yaghoobi, *Ostandari St.Kerman*
 Arash Zaminy, *Rasht*



Ireland

Frank P Barry, *Galway*
 Leo Quinlan, *Galway*
 Ralf M Zwacka, *Galway*



Israel

Nadir Askenasy, *Petah Tiqwa*
 Zeev Blumenfeld, *Haifa*
 Benayahu Dafna, *Tel Aviv*
 Benjamin Dekel, *Tel Hashomer*
 Dan Gazit, *Jerusalem*
 Gal Goldstein, *Tel-Hashomer*
 Eran Meshorer, *Jerusalem*
 Rachel Sarig, *Rehovot*
 Avichai Shimoni, *Tel-Hashomer*
 Shimon Slavin, *Tel Aviv*



Italy

Andrea Barbuti, *Milan*

Carlo A Beltrami, *Udine*
 Bruno Bonetti, *Verona*
 Paola Bruni, *Florence*
 Laura Calzà, *Bologna*
 Giovanni Camussi, *Turin*
 Domenico Capone, *Naples*
 Francesco Carinci, *Ferrara*
 Carmelo Carlo-Stella, *Milan*
 Clotilde Castaldo, *Naples*
 Angela Chambery, *Caserta*
 Francesco Dieli, *Palermo*
 Massimo Dominici, *Modena*
 Massimo De Felici, *Rome*
 Stefania Filosa, *Naples*
 Guido Frosina, *Genova*
 Umberto Galderisi, *Naples*
 Pompilio Giulio, *Milan*
 Antonio Graziano, *Napoli*
 Brunella Grigolo, *Bologna*
 Annalisa Grimaldi, *Varese*
 Angela Gritti, *Milan*
 Enzo Di Iorio, *Zelarino*
 Alessandro Isidori, *Pesaro*
 Giampiero Leanza, *Trieste*
 Enrico Lucarelli, *Bologna*
 Margherita Maioli, *Sassari*
 Ferdinando Mannello, *Urbino*
 Tullia Maraldi, *Modena*
 Gianvito Martino, *Milan*
 Monica Mattioli-Belmonte, *Ancona*
 Fabrizio Michetti, *Roma*
 Gabriella Minchiotti, *Naples*
 Roberta Morosetti, *Rome*
 Gianpaolo Papaccio, *Napoli*
 Felicita Pedata, *Florence*
 Maurizio Pesce, *Milan*
 Anna C Piscaglia, *Rome*
 Vito Pistoia, *Genova*
 Francesca Pistollato, *Ispra*
 Alessandro Poggi, *Genoa*
 Caterina AM La Porta, *Milan*
 Domenico Ribatti, *Bari*
 Giampiero La Rocca, *Palermo*
 Sergio Rutella, *Rome*
 Sonia Scarfi, *Genoa*
 Arianna Scuteri, *Monza*
 Luca Steardo, *Rome*
 Gianluca Vadalà, *Roma*
 Maria T Valenti, *Verona*
 Carlo Ventura, *Ravenna*
 Stefania Violini, *Lodi*



Japan

Manabu Akahane, *Nara*
 Yasuto Akiyama, *Shizuoka*
 Tomoki Aoyama, *Kyoto*
 Sachiko Ezoe, *Osaka*
 Yusuke Furukawa, *Tochigi*
 Masayuki Hara, *Osaka*
 Eiso Hiyama, *Hiroshima*
 Kanya Honoki, *Kashihara*
 Yuichi Hori, *Kobe*
 Susumu Ikehara, *Osaka*
 Masamichi Kamihira, *Fukuoka*
 Yonehiro Kanemura, *Osaka*
 Hiroshi Kanno, *Yokohama*
 Masaru Katoh, *Tokyo*
 Eihachiro Kawase, *Kyoto*
 Isobe, Ken-ichi, *Nagoya*

Toru Kondo, *Sapporo*
 Toshihiro Kushibiki, *Osaka*
 Tao-Sheng Li, *Nagasaki*
 Yasuhisa Matsui, *Sendai*
 Taro Matsumoto, *Tokyo*
 Hiroyuki Miyoshi, *Ibaraki*
 Hiroyuki Mizuguchi, *Osaka*
 Hiroshi Mizuno, *Tokyo*
 Takashi Nagasawa, *Kyoto*
 Kohzo Nakayama, *Nagano*
 Tetsuhiro Niidome, *Kyoto*
 Toshio Nikaido, *Toyama*
 Shoko Nishihara, *Tokyo*
 Hirofumi Noguchi, *Okinawa*
 Tsukasa Ohmori, *Tochigi*
 Katsutoshi Ozaki, *Tochigi*
 Kumiko Saeki, *Tokyo*
 Kazunobu Sawamoto, *Aichi*
 Goshi Shiota, *Yonago*
 Mikiko C Siomi, *Tokyo*
 Yoshiaki Sonoda, *Osaka*
 Takashi Tada, *Kyoto*
 Miyako Takaki, *Nara*
 Shihori Tanabe, *Tokyo*
 Kenzaburo Tani, *Fukuoka*
 Shuji Toda, *Saga*
 Atsunori Tsuchiya, *Niigata*
 Shingo Tsuji, *Osaka*
 Kohichiro Tsuji, *Tokyo*
 Akihiro Umezawa, *Tokyo*
 Hiroshi Wakao, *Sapporo*
 Yoichi Yamada, *Aichi*
 Takashi Yokota, *Kanazawa*
 Yukio Yoneda, *Kanazawa*
 Kotaro Yoshimura, *Tokyo*
 Katsutoshi Yoshizato, *Higashihiroshima*
 Louis Yuge, *Hiroshima*



Jordan

Khitam SO Alrefu, *Karak*



Malaysia

Rajesh Ramasamy, *Serdang*



Mexico

Marco A Velasco-Velazquez, *Mexico*



Morocco

Radouane Yafia, *Ouarzazate*



Netherlands

Robert P Coppes, *Groningen*
 Christine L Mummery, *Leiden*
 Vered Raz, *Leiden*
 Bernard AJ Roelen, *Utrecht*
 Marten P Smidt, *Utrecht*
 Frank JT Staal, *Leiden*



Norway

Zhenhe Suo, *Oslo*

Berit B Tysnes, *Bergen*



Portugal

Inês M Araújo, *Coimbra*



Romania

Mihaela C Economescu, *Bucharest*



Russia

Igor A Grivennikov, *Moscow*
 Sergey L Kiselev, *Moscow*
 Serov Oleg, *Novosibirsk*



Singapore

Yu Cai, *Singapore*
 Jerry Chan, *Singapore*
 Gavin S Dawe, *Singapore*
 Peter Droge, *Singapore*
 Seet L Fong, *Singapore*
 Boon C Heng, *Singapore*
 Yunhan Hong, *Singapore*
 Chan Woon Khiong, *Singapore*
 Chan Kwok-Keung, *Singapore*
 Yui-Han Loh, *Singapore*
 Koon G Neoh, *Singapore*
 Steve KW Oh, *Singapore*
 Kian K Poh, *Singapore*
 Seeram Ramakrishna, *Singapore*
 Herbert Schwarz, *Singapore*
 Winston Shim, *Singapore*
 Vivek M Tanavde, *Singapore*
 Shu Wang, *Singapore*



Slovakia

Lubos Danisovic, *Bratislava*



South Korea

Kwang-Hee Bae, *Daejeon*
 Hyuk-Jin Cha, *Seoul*
 Jong Wook Chang, *Seoul*
 Kyu-Tae Chang, *Chungcheongbuk-do*
 Chong-Su Cho, *Seoul*
 Ssang-Goo Cho, *Seoul*
 Myung Soo Cho, *Seoul*
 Kang-Yell Choi, *Seoul*
 HO Jae Han, *Gwangju*
 Myung-Kwan Han, *Jeonju*
 Chanyeong Heo, *Gyeonggi-do*
 Ki-Chul Hwang, *Seoul*
 Dong-Youn Hwang, *Seongnam*
 Sin-Soo Jeun, *Seoul*
 Youngjoon Jun, *Gyeonggi-do*
 Jin Sup Jung, *Yangsan Si*
 Ji-Won Jung, *Chungbuk*
 Kyung-Sun Kang, *Seoul*
 Gilson Khang, *Jeonju*
 Yoon Jun Kim, *Seoul*

Byung Soo Kim, *Seoul*
 Hyo-Soo Kim, *Seoul*
 Moon Suk Kim, *Suwon*
 Jong-Hoon Kim, *Seoul*
 Haekwon Kim, *Seoul*
 Hyeon Kim, *Daejeon*
 Sang Gyung Kim, *Daegu*
 Song Cheol Kim, *Seoul*
 Kwang-Bok Lee, *Chonbuk*
 Dong Ryul Lee, *Seoul*
 Soo-Hong Lee, *Gyunggi-do*
 Younghee Lee, *Chungbuk*
 Jong Eun Lee, *Seoul*
 Dae-Sik Lim, *Daejeon*
 Kyu Lim, *Daejeon*
 Do Sik Min, *Pusan*
 Jong-Beom Park, *Seoul*
 Byung Soon Park, *Seoul*
 Gyu-Jin Rho, *Jinju*
 Chun Jeih Ryu, *Seoul*
 Sun Uk Song, *Incheon*
 Jong-Hyuk Sung, *Seoul*
 Jong-Ho Won, *Seoul*
 Seung Kwon You, *Seoul*



Spain

Luis MA Aparicio, *A Coruna*
 Angel Ayuso-Sacido, *Valencia*
 Fernando Cobo, *Granada*
 Juan AM Corrales, *Granada*
 Sabrina C Desbordes, *Barcelona*
 Ramon Farre, *Barcelona*
 Damian Garcia-Olmo, *Madrid*
 Boulaiz Houria, *Granada*
 Juan M Hurle, *Santander*
 Antonia A Jiménez, *Granada*
 Marta M Llamosas, *Asturias*
 Pablo Menendez, *Granada*
 Maria D Minana, *Valencia*
 Eduardo Moreno, *Madrid*
 Felipe Prosper, *Navarra*
 Manuel Ramírez, *Madrid*



Sweden

M Quamrul Islam, *Linköping*
 Stefan Karlsson, *Lund*
 Rachael V Sugars, *Huddinge*



Switzerland

Thomas Daikeler, *Basel*
 Anis Feki, *Geneva*
 Sanga Gehmert, *Basel*
 Sabrina Mattoli, *Basel*
 Arnaud Scherberich, *Basel*



Thailand

Rangsun Parnpai, *Nakhon Ratchasima*



Tunisia

Faouzi Jenhani, *Monastir*



Turkey

Kamil C Akcali, *Ankara*
 Berna Arda, *Ankara*
 Alp Can, *Ankara*
 Y Murat Elcin, *Ankara*
 Erdal Karaoz, *Kocaeli*



United Arab Emirates

Sherif M Karam, *Al-Ain*



United Kingdom

Malcolm R Alison, *London*
 Charles Archer, *Cardiff*
 Dominique Bonnet, *London*
 Kristin M Braun, *London*
 Nicholas R Forsyth, *Hartshill*
 Rasmus Freter, *Oxford*
 Hassan T Hassan, *Scotland*
 David C Hay, *Edinburgh*
 Wael Kafienah, *Bristol*
 Francis L Martin, *Lancaster*
 Stuart McDonald, *London*
 Pankaj K Mishra, *Wolverhampton*
 Ali Mobasher, *Sutton Bonington*
 Michel Modo, *London*
 Donald Palmer, *London*
 Stefano Pluchino, *Milan*
 Julia M Polak, *London*
 Stefan A Przyborski, *Durham*
 James A Ross, *Edinburgh*
 Alastair J Sloan, *Cardiff*
 Virginie Sottile, *Nottingham*
 Petros V Vlastarakos, *Stevenage*
 Hong Wan, *London*
 Christopher M Ward, *Manchester*
 Heping Xu, *Aberdeen*
 Lingfang Zeng, *London*
 Rike Zietlow, *Cardiff*



United States

Gregor B Adams, *Los Angeles*
 Arshak R Alexanian, *Milwaukee*
 Ali S Arbab, *Detroit*
 Kinji Asahina, *Los Angeles*
 Atsushi Asakura, *Minneapolis*
 Prashanth Asuri, *Santa Clara*
 Craig S Atwood, *Madison*
 Debabrata Banerjee, *New Brunswick*
 David W Barnes, *Lawrenceville*
 Surinder K Batra, *Omaha*
 Aline M Betancourt, *New Orleans*
 John J Bright, *Indianapolis*
 Bruce A Bunnell, *Covington*
 Matthew E Burow, *New Orleans*
 Rebecca J Chan, *Indianapolis*
 Anthony WS Chan, *Atlanta*
 Joe Y Chang, *Houston*
 G Rasul Chaudhry, *Rochester*
 Caifu Chen, *Foster City*
 Ke Cheng, *Los Angeles*
 Herman S Cheung, *Coral Gables*
 Kent W Christopherson II, *Chicago*

David W Clapp, *Indianapolis*
 Claudius Conrad, *Boston*
 Charles S Cox, *Houston*
 Ronald G Crystal, *New York*
 Hiranmoy Das, *Columbus*
 Douglas Dean, *Louisville*
 Bridget M Deasy, *Pittsburgh*
 Weiwen Deng, *Grand Rapids*
 Goberdhan Dimri, *Evanston*
 David Dingli, *Rochester*
 Juan Dominguez-Bendala, *Miami*
 Sergey V Doronin, *Stony Brook*
 Fu-Liang Du, *Vernon*
 Gary L Dunbar, *Pleasant*
 Todd Evans, *New York*
 Toshihiko Ezashi, *Columbia*
 Vincent Falanga, *Providence*
 Zhongling Feng, *Carlsbad*
 Markus Frank, *Boston*
 Mohamed A Gaballa, *Sun City*
 G Ian Gallicano, *Washington*
 Yair Gazitt, *San Antonio*
 Yong-Jian Geng, *Houston*
 Jorge A Genovese, *Salt Lake City*
 Mehrnaz Gharaee-Kermani, *Ann Arbor*
 Ali Gholamrezaezhad, *Baltimore*
 Joseph C Glorioso, *Pittsburgh*
 W Scott Goebel, *Indianapolis*
 Brigitte N Gomperts, *Los Angeles*
 Kristbjorn O Gudmundsson, *Frederick*
 Preethi H Gunaratne, *Houston*
 Yan-Lin Guo, *Hattiesburg*
 Robert G Hawley, *Washington*
 Tong-Chuan He, *Chicago*
 Mary JC Hendrix, *Chicago*
 Charles C Hong, *Pierce Ave*
 Yiling Hong, *Dayton*
 Courtney W Houchen, *Oklahoma City*
 George TJ Huang, *Boston*
 Jing Huang, *Bethesda*
 Johnny Huard, *Pittsburgh*
 Jaclyn Y Hung, *San Antonio*
 Lorraine Iacovitti, *Philadelphia*
 Tony Ip, *Worcester*
 D Joseph Jerry, *Amherst*
 Kun-Lin Jin, *Novato*
 Lixin Kan, *Chicago*
 Winston W Kao, *Cincinnati*
 Partow Kebriaei, *Houston*
 Mary J Kelley, *Portland*
 Sophia K Khaldoyanidi, *San Diego*
 Mahesh Khatri, *Wooster*
 Jaspal S Khillan, *Pittsburgh*
 Katsuhiro Kita, *Galveston*
 Mikhail G Kolonin, *Houston*
 Prasanna Krishnamurthy, *Chicago*
 Marlene A Kristeva, *Van Nuys*
 John S Kuo, *Madison*
 Mark A LaBarge, *Berkeley*
 Uma Lakshmipathy, *Carlsbad*
 Hillard M Lazarus, *Shaker Heights*
 Techung Lee, *Buffalo*
 Xudong J Li, *Charlottesville*
 Shaoguang Li, *Worcester*
 Jianxue Li, *Boston*
 Xiao-Nan Li, *Houston*
 Shengwen C Li, *Orange*
 Marcos de Lima, *Houston*
 P Charles Lin, *Nashville*
 Ching-Shwun Lin, *San Francisco*
 Zhenguo Liu, *Columbus*

Su-Ling Liu, *Ann Arbor*
 Ning Liu, *Madison*
 Aurelio Loricó, *Las Vegas*
 Jean-Pierre Louboutin, *Philadelphia*
 Qing R Lu, *Dallas*
 Bing-Wei Lu, *Stanford*
 Nadya L Lumelsky, *Bethesda*
 Hong-Bo R Luo, *Boston*
 Hinh Ly, *Atlanta*
 Teng Ma, *Tallahassee*
 Kenneth Maiese, *Newark*
 Debra JH Mathews, *Baltimore*
 Robert L Mauck, *Philadelphia*
 Glenn E McGee, *New York*
 Jeffrey A Medin, *Milwaukee*
 Lucio Miele, *Jackson*
 Robert H Miller, *Cleveland*
 David K Mills, *Ruston*
 Murielle Mimeault, *Omaha*
 Prasun J Mishra, *Bethesda*
 Kalpana Mujoo, *Houston*
 Masato Nakafuku, *Cincinnati*
 Mary B Newman, *Chicago*
 Wenze Niu, *Dallas*
 Christopher Niyibizi, *Hershey*
 Jon M Oatley, *Pullman*
 Seh-Hoon Oh, *Gainesville*
 Shu-ichi Okamoto, *La Jolla*
 Nishit Pancholi, *Chicago*
 Deric M Park, *Charlottesville*
 Gregory Pastores, *New York*
 Ming Pei, *Morgantown*
 Derek A Persons, *Memphis*
 Donald G Phinney, *Jupiter*
 John S Pixley, *Reno*
 Dimitris G Placantonakis, *New York*
 George E Plopper, *Troy*
 Mark EP Prince, *Ann Arbor*
 April Pyle, *Los Angeles*
 Murugan Ramalingam, *Gaithersburg*
 Guangwen Ren, *New Brunswick*
 Brent A Reynolds, *Gainesville*
 Jeremy N Rich, *Cleveland*
 Shuo L Rios, *Los Angeles*
 Angie Rizzino, *Omaha*,

Fred J Roisen, *Louisville*
 Rouel S Roque, *Henderson*
 Carl B Rountree, *Hershey*
 Clinton T Rubin, *Madison*
 Donald Sakaguchi, *Ames*
 Paul R Sanberg, *Tampa*
 Masanori Sasaki, *West Haven*
 Stewart Sell, *Albany*
 Ivana de la Serna, *Toledo*
 Arun K Sharma, *Chicago*
 Susan G Shawcross, *Manchester*
 Jinsong Shen, *Dallas*
 Ashok K Shetty, *New Orleans*
 Yanhong Shi, *Duarte*
 Songtao Shi, *Los Angeles*
 Vassilios I Sikavitsas, *Norman*
 Igor I Slukvin, *Madison*
 Shay Soker, *Winston Salem*
 Hong-Jun Song, *Baltimore*
 Edward F Srour, *Indianapolis*
 Hua Su, *San Francisco*
 Jun Sun, *Rochester*
 Tao Sun, *New York*
 Kenichi Tamama, *Columbus*
 Masaaki Tamura, *Manhattan*
 Tetsuya S Tanaka, *Urbana*
 Dean G Tang, *Smithville*
 Hugh S Taylor, *New Haven*
 Jonathan L Tilly, *Boston*
 Jakub Tolar, *Minneapolis*
 Deryl Troyer, *Manhattan*
 Kent KS Tsang, *Memphis*
 Scheffer C Tseng, *Miami*
 Cho-Lea Tso, *Los Angeles*
 Lyuba Varticovski, *Bethesda*
 Tandis Vazin, *Berkeley*
 Qi Wan, *Reno*
 Shu-Zhen Wang, *Birmingham*
 Lianchun Wang, *Athens*
 Guo-Shun Wang, *New Orleans*
 Yigang Wang, *Cincinnati*
 Zack Z Wang, *Scarborough*
 Charles Wang, *Los Angeles*
 Limin Wang, *Ann Arbor*
 Zhiqiang Wang, *Duarte*

David Warburton, *Los Angeles*
 Li-Na Wei, *Minneapolis*
 Christof Westenfelder, *Salt Lake City*
 Andre J van Wijnen, *Worcester*
 Marc A Williams, *Rochester*
 J Mario Wolosin, *New York*
 Raymond C Wong, *Irvine*
 Joseph C Wu, *Stanford*
 Lizi Wu, *Gainesville*
 Wen-Shu Wu, *Scarborough*
 Sean M Wu, *Boston*
 Ping Wu, *Galveston*
 Xiaowei Xu, *Philadelphia*
 Yan Xu, *Pittsburgh*
 Meifeng Xu, *Cincinnati*
 Dean T Yamaguchi, *Los Angeles*
 Jun Yan, *Louisville*
 Phillip C Yang, *Stanford*
 Feng-Chun Yang, *Indianapolis*
 Xiao-Feng Yang, *Philadelphia*
 Xiaoming Yang, *Seattle*
 Shang-Tian Yang, *Columbus*
 Youxin Yang, *Boston*
 Jing Yang, *Orange*
 Kaiming Ye, *Fayetteville*
 Pampee P Young, *Nashville*
 John S Yu, *Los Angeles*
 Hong Yu, *Miami*
 Seong-Woon Yu, *East Lansing*
 Hui Yu, *Pittsburgh*
 Xian-Min Zeng, *Novato*
 Ming Zhan, *Baltimore*
 Chengcheng Zhang, *Texas*
 Ying Zhang, *Baltimore*
 Qunzhou Zhang, *Los Angeles*
 Yan Zhang, *Houston*
 X. Long Zheng, *Philadelphia*
 Pan Zheng, *Ann Arbor*
 Xue-Sheng Zheng, *Charlestown*
 John F Zhong, *Los Angeles*
 Xianzheng Zhou, *Minneapolis*
 Bin Zhou, *Boston*
 Feng C Zhou, *Indianapolis*



ORIGINAL ARTICLE

Basic Study

- 98 Modifying oxygen tension affects bone marrow stromal cell osteogenesis for regenerative medicine

Inagaki Y, Akahane M, Shimizu T, Inoue K, Egawa T, Kira T, Ogawa M, Kawate K, Tanaka Y

ABOUT COVER

Editorial Board Member of *World Journal of Stem Cells*, Ming Pei, MD, PhD, Associate Professor, Director, Stem Cell and Tissue Engineering Laboratory, Department of Orthopaedics, West Virginia University, Morgantown, WV 26506, United States

AIM AND SCOPE

World Journal of Stem Cells (*World J Stem Cells*, *WJSC*, online ISSN 1948-0210, DOI: 10.4252), is a peer-reviewed open access academic journal that aims to guide clinical practice and improve diagnostic and therapeutic skills of clinicians.

WJSC covers topics concerning all aspects of stem cells: embryonic, neural, hematopoietic, mesenchymal, tissue-specific, and cancer stem cells; the stem cell niche, stem cell genomics and proteomics, and stem cell techniques and their application in clinical trials.

We encourage authors to submit their manuscripts to *WJSC*. We will give priority to manuscripts that are supported by major national and international foundations and those that are of great basic and clinical significance.

INDEXING/ABSTRACTING

World Journal of Stem Cells is now indexed in PubMed, PubMed Central, Science Citation Index Expanded (also known as SciSearch®), Journal Citation Reports/Science Edition, Biological Abstracts, and BIOSIS Previews.

FLYLEAF

I-V

Editorial Board

EDITORS FOR THIS ISSUE

Responsible Assistant Editor: *Xiang Li*
Responsible Electronic Editor: *Ya-Jing Lu*
Proofing Editor-in-Chief: *Lian-Sheng Ma*

Responsible Science Editor: *Jin-Xin Kong*
Proofing Editorial Office Director: *Jin-Lai Wang*

NAME OF JOURNAL
World Journal of Stem Cells

ISSN
ISSN 1948-0210 (online)

LAUNCH DATE
December 31, 2009

FREQUENCY
Monthly

EDITORS-IN-CHIEF
Tong Cao, BM BCh, DDS, PhD, Associate Professor, Doctor, Department of Oral Sciences, National University of Singapore, Singapore 119083, Singapore

Oscar Kuang-Sheng Lee, MD, PhD, Professor, Medical Research and Education of Veterans General Hospital-Taipei, No. 322, Sec. 2, Shih-pai Road, Shih-pai, Taipei 11217, Taiwan

EDITORIAL BOARD MEMBERS
All editorial board members resources online at <http://www.wjnet.com/1948-0210/editorialboard.htm>

EDITORIAL OFFICE

Xiu-Xia Song, Director
World Journal of Stem Cells
Baishideng Publishing Group Inc
7901 Stoneridge Drive, Suite 501, Pleasanton, CA 94588, USA
Telephone: +1-925-2238242
Fax: +1-925-2238243
E-mail: editorialoffice@wjnet.com
Help Desk: <http://www.wjnet.com/helpdesk>
<http://www.wjnet.com>

PUBLISHER

Baishideng Publishing Group Inc
7901 Stoneridge Drive, Suite 501,
Pleasanton, CA 94588, USA
Telephone: +1-925-2238242
Fax: +1-925-2238243
E-mail: bpgoffice@wjnet.com
Help Desk: <http://www.wjnet.com/helpdesk>
<http://www.wjnet.com>

PUBLICATION DATE

July 26, 2017

COPYRIGHT

© 2017 Baishideng Publishing Group Inc. Articles published by this Open-Access journal are distributed under the terms of the Creative Commons Attribution Non-commercial License, which permits use, distribution, and reproduction in any medium, provided the original work is properly cited, the use is non-commercial and is otherwise in compliance with the license.

SPECIAL STATEMENT

All articles published in journals owned by the Baishideng Publishing Group (BPG) represent the views and opinions of their authors, and not the views, opinions or policies of the BPG, except where otherwise explicitly indicated.

INSTRUCTIONS TO AUTHORS

<http://www.wjnet.com/bpg/gerinfo/204>

ONLINE SUBMISSION

<http://www.wjnet.com>

Basic Study

Modifying oxygen tension affects bone marrow stromal cell osteogenesis for regenerative medicine

Yusuke Inagaki, Manabu Akahane, Takamasa Shimizu, Kazuya Inoue, Takuya Egawa, Tsutomu Kira, Munehiro Ogawa, Kenji Kawate, Yasuhito Tanaka

Yusuke Inagaki, Takamasa Shimizu, Kazuya Inoue, Takuya Egawa, Tsutomu Kira, Munehiro Ogawa, Yasuhito Tanaka, Department of Orthopedic Surgery, Nara Medical University, Kashihara, Nara 634-8522, Japan

Manabu Akahane, Department of Public Health, Health Management and Policy, Nara Medical University, Faculty of Medicine, Kashihara, Nara 634-8521, Japan

Kenji Kawate, Departments of Artificial Joint and Regenerative Medicine for Bone and Cartilage, Nara Medical University, Kashihara, Nara 634-8522, Japan

Author contributions: Inagaki Y and Akahane M designed the study; Inagaki Y, Akahane M, Shimizu T, Inoue K, Egawa T and Kira T performed the study; Inagaki Y and Akahane M drafted the manuscript; Ogawa M, Kawate K and Tanaka Y critically reviewed the draft; all authors read and approved the final manuscript.

Institutional review board statement: This study was approved by the Institutional Review Board of Nara Medical University before beginning experiments.

Institutional animal care and use committee statement: All experimental protocols using animals were approved by the Animal Experimental Review Board of Nara Medical University before beginning experiments.

Conflict-of-interest statement: There is no conflict of interest regarding to this study.

Data sharing statement: None.

Open-Access: This article is an open-access article which was selected by an in-house editor and fully peer-reviewed by external reviewers. It is distributed in accordance with the Creative Commons Attribution Non Commercial (CC BY-NC 4.0) license, which permits others to distribute, remix, adapt, build upon this work non-commercially, and license their derivative works on different terms, provided the original work is properly cited and the use is non-commercial. See: <http://creativecommons.org/licenses/by-nc/4.0/>

[licenses/by-nc/4.0/](http://creativecommons.org/licenses/by-nc/4.0/)

Manuscript source: Invited manuscript

Correspondence to: Yusuke Inagaki, MD, PhD, Assistant Professor, Department of Orthopedic Surgery, Nara Medical University, 840 Shijo-cho, Kashihara, Nara 634-8522, Japan. yinagaki@naramed-u.ac.jp
Telephone: +81-744-223051
Fax: +81-744-256449

Received: January 26, 2017

Peer-review started: February 2, 2017

First decision: March 31, 2017

Revised: April 27, 2017

Accepted: June 6, 2017

Article in press: June 8, 2017

Published online: July 26, 2017

Abstract

AIM

To establish a hypoxic environment for promoting osteogenesis in rat marrow stromal cells (MSCs) using osteogenic matrix cell sheets (OMCSs).

METHODS

Rat MSCs were cultured in osteogenic media under one of four varying oxygen conditions: Normoxia (21% O₂) for 14 d (NN), normoxia for 7 d followed by hypoxia (5% O₂) for 7 d (NH), hypoxia for 7 d followed by normoxia for 7 d (HN), or hypoxia for 14 d (HH). Osteogenesis was evaluated by observing changes in cell morphology and calcium deposition, and by measuring osteocalcin secretion (ELISA) and calcium content. *In vivo* syngeneic transplantation using OMCSs and β -tricalcium phosphate discs, preconditioned under NN or HN conditions, was also evaluated by histology, calcium content measurements,

and real-time quantitative PCR.

RESULTS

In the NN and HN groups, differentiated, cuboidal-shaped cells were readily observed, along with calcium deposits. In the HN group, the levels of secreted osteocalcin increased rapidly from day 10 as compared with the other groups, and plateaued at day 12 ($P < 0.05$). At day 14, the HN group showed the highest amount of calcium deposition. *In vivo*, the HN group showed histologically prominent new bone formation, increased calcium deposition, and higher collagen type I messenger RNA expression as compared with the NN group.

CONCLUSION

The results of this study indicate that modifying oxygen tension is an effective method to enhance the osteogenic ability of MSCs used for OMCSs.

Key words: Hypoxia; Osteogenesis; Tissue engineering; Marrow stromal cells; Regenerative medicine

© The Author(s) 2017. Published by Baishideng Publishing Group Inc. All rights reserved.

Core tip: Bone tissue engineering using marrow stromal cells (MSCs) is a promising method in regenerative medicine. Here, we have reported a scaffold-free transplantation technique using hypoxic-preconditioned osteogenic matrix cell sheets (OMCSs) derived from MSCs. We show that modifying the oxygen tension before implantation of OMCS composites led to an increased osteogenic capacity of rat bone MSCs.

Inagaki Y, Akahane M, Shimizu T, Inoue K, Egawa T, Kira T, Ogawa M, Kawate K, Tanaka Y. Modifying oxygen tension affects bone marrow stromal cell osteogenesis for regenerative medicine. *World J Stem Cells* 2017; 9(7): 98-106 Available from: URL: <http://www.wjgnet.com/1948-0210/full/v9/i7/98.htm> DOI: <http://dx.doi.org/10.4252/wjsc.v9.i7.98>

INTRODUCTION

Bone defects resulting from severe fracture, infection, or tumor resection are serious problems that impair patient quality of life. Bone tissue engineering is a novel way to produce sufficient bone to repair bony defects. Various methods^[1-5] have examined the use of marrow stromal cells (MSCs) as a cell source for bone tissue engineering, and several reports have incorporated natural or synthetic scaffolds to maintain MSCs^[6-8]. However, each method has its limitations, including possible immunological responses against natural materials, and reduced bioactivity or biocompatibility with synthetic materials^[9]. So, too, have several recombinant proteins, such as bone morphogenetic protein-2, been vigorously tested in conjunction with these scaffolding materials because of

their capacity to enhance osteogenesis. However, the use of recombinant proteins is limited, as it is difficult to control their dosage, with multiple applications or genetic manipulation, such as gene transfer, often required to accommodate their short half-life *in vivo*. Thus, more effective and simpler methods are needed to enhance osteogenesis for bone tissue reconstruction.

Oxygen tension affects the proliferation and differentiation of MSCs^[10,11], and cell culture conditions are generally set to approximately 21% O₂ and 5% CO₂ at 37 °C. However, several studies have reported that, in the bone marrow, physiological oxygen concentrations range from 6.6% to 8.6% (54.9 mmHg to 71.4 mmHg), as measured using a polarographic needle electrode^[12,13]. In a study focusing on the effect of hypoxia on MSC osteogenesis, Lennon *et al.*^[10] reported that 5% O₂ in primary and subcultures of rat MSCs could enhance osteogenesis. Conversely, D'Ippolito *et al.*^[11] have shown that 3% O₂ inhibits osteogenic differentiation of human MSCs. Thus, the ideal concentration, duration, and timing of hypoxic treatment to enhance osteogenesis remain unclear.

We previously reported several methods for musculoskeletal reconstruction using cell transplantation techniques using composites of artificial bone combined with MSCs, and the use of a scaffold-free cell sheets, referred to as osteogenic matrix cell sheets (OMCSs). As hypoxic treatment may enhance osteogenesis for such composites and cell sheets, in the present study, we evaluated whether hypoxia could enhance MSCs and the osteogenesis of OMCSs created from MSCs.

MATERIALS AND METHODS

Ethics statement

All experimental protocols using animals were approved by the Animal Experimental Review Board of the Nara Medical University before experimentation. Animals were housed in a temperature-controlled environment at approximately 21 °C under a 12-h light/12-h dark cycle with free access to food and water.

Bone marrow cell preparation

Seven-week-old male Fisher-344 rats (Japan SLC, Shizuoka, Japan) were purchased for bone marrow cell preparation. Bone marrow cells were obtained from the femoral shafts of rats as previously described^[1]. Briefly, both ends of the femurs were cut from the epiphysis, and the marrow was flushed with 10 mL of basal medium expelled from a syringe through a 21-gauge needle. Basal medium consisted of Eagle's Minimal Essential Medium (Nacalai Tesque, Kyoto, Japan), 15% fetal bovine serum (Gibco, Thermo Fisher Scientific, Waltham, MA, United States) and antibiotics (100 U/mL penicillin and 100 µg/mL streptomycin; Nacalai Tesque). The flushed cells were collected into two

T-75 flasks (Falcon, BD Biosciences, Franklin Lakes, NJ, United States) containing 15 mL of basal medium. Non-adherent cells were removed during media changes, which were performed three times per week. Cultures were maintained in a humidified atmosphere of 95% air and 5% CO₂ at 37 °C.

After reaching confluence, cells were released by trypsin/EDTA (Nacalai Tesque) and used for *in vitro* and *in vivo* experiments.

***In vitro* experiment**

Osteogenic cell culture and experimental design:

Cells were seeded at a density of 1×10^4 cells/cm² in 12-well cell culture plates (Falcon, BD Biosciences), and subcultured in osteogenic medium consisting of basal medium supplemented with 10 nmol/L dexamethasone (Sigma-Aldrich, St. Louis, MO, United States) and 0.28 mmol/L ascorbic acid phosphate (Wako Pure Chemical Industrials, Kyoto, Japan). These subcultured cells were exposed to one of four variable oxygen concentration conditions: Normoxia (21% O₂) for 14 d (NN), normoxia for the first 7 d followed by hypoxia (5% O₂) for the next 7 d (NH), hypoxia for the first 7 d followed by normoxia for the next 7 d (HN), and hypoxia for 14 d (HH). The entire experiment was repeated using cells from two different animals. The number of replicates within each assay.

Osteocalcin secretion measurement: Osteocalcin secretion was measured to evaluate the osteogenic potential of MSCs. Secreted osteocalcin is a reliable marker for predicting *in vivo* osteogenic potential for bone tissue engineering^[14]. Secreted osteocalcin levels were measured on days 7, 10, 12, and 14 using an enzyme-linked immunosorbent assay (ELISA) with anti-rat osteocalcin monoclonal antibody (DS Pharma Biomedical, Osaka, Japan). A media change performed 48 h before collection ($n = 5$ for each group).

Observations of cell morphology and calcium deposition: After 14 d of osteogenic culture, the media was replaced with phosphate-buffered saline (PBS; Gibco, Paisley, United Kingdom), and cell morphology and calcium deposition on the culture plates were observed using an inverted microscope (Eclipse Ti-S, Nikon, Tokyo, Japan). Images were taken using a digital camera (Digital Sight DS-Fi1, Nikon) ($n = 5$ for each group).

Measurement of calcium deposition: After observations of cell morphology and calcium deposition, total calcium was extracted from each well with 2.0 mL of 20% formic acid, and measured using a methylxlenol blue method (Calcium E-test Wako Kit, Wako Pure Chemical Industrials) ($n = 5$ for each group). Measurements were adjusted to the total amount of protein in each well, as determined using a spectrophotometric method with bovine serum albumin as a standard.

Alkaline phosphatase staining: For alkaline phosphatase (ALP) staining^[1], cells were cultured in osteogenic medium for 14 d in 6-well plates under variable oxygen conditions, rinsed twice with PBS, and then stained with naphthol-AS-MX phosphate sodium salt (Sigma-Aldrich) and fast red violet LB salt (Nacalai Tesque) at room temperature for 10 min. The stain was removed by rinsing with tap water, and air dried.

Cell proliferation assay: A colorimetric assay using tetrazolium salt was performed to assess the effect of hypoxic conditions on the proliferative capacity of MSCs. Cells were seeded at a density of 1×10^4 cells/cm² into the wells of a 96-well cell culture plate (Falcon, BD Biosciences) and subcultured in basal medium for 3 d under hypoxia or normoxia. Cell proliferation was then measured using a cell proliferation assay kit (Promega, Fitchburg, WI, United States), as per the manufacturer's recommendations ($n = 6$ for each group).

***In vivo* experiment**

Syngeneic OMCS transplantation: *In vivo* syngeneic transplantation experiments were performed using OMCSs prepared from second-passage bone marrow cells, as previously reported^[2,3]. OMCSs were exposed to one of two oxygen conditions: Normoxia (21% O₂) for 14 d (NN) or hypoxia (5% O₂) for the first 7 d followed by normoxia for the next 7 d (HN); these two conditions were chosen based on the results of the *in vitro* experiments. β -tricalcium phosphate (β -TCP) discs (Hoya, Tokyo, Japan; 75% porosity, 5-mm diameter, and 2-mm thickness) were wrapped with OMCSs and then implanted at subcutaneous sites on the backs of recipient rats.

In this experiment, OMCSs were wrapped around β -TCP discs so that the sheets could be easily identified and harvested for precise histological evaluation.

Histological evaluation: β -TCP discs with OMCSs were harvested after 4 wk. Samples were decalcified in K-CX solution (Falma, Tokyo, Japan), embedded in paraffin, cut at the middle of the specimen, and stained with hematoxylin and eosin (HE). Two authors (KI and TE), blinded to the grouping, evaluated the histological findings ($n = 5$ for each group).

Calcium content measurements: To quantify the amount of newly formed hydroxyapatite, harvested constructs were homogenized, and calcium content was measured as described earlier ($n = 5$ for each group).

Real-time quantitative PCR: Total RNA was extracted from harvested specimens using ISOGEN (Nippon Gene, Tokyo, Japan), and reverse transcribed into complementary DNA. Real-time quantitative PCR (Applied Biosystems Step One Plus Real Time PCR System, Thermo Fisher Scientific, MA, United

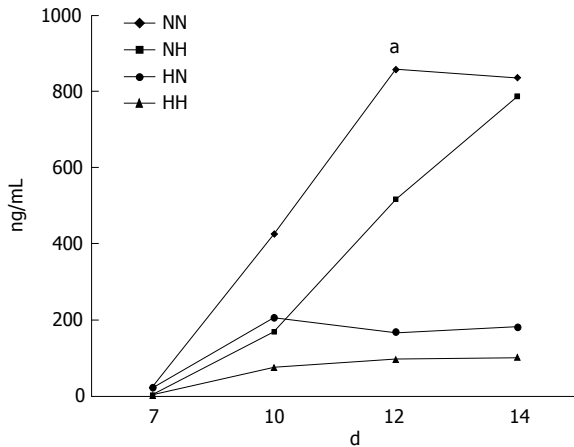


Figure 1 Osteocalcin secretion. In cells exposed to hypoxia (5% O₂) for 7 d followed by normoxia (21% O₂) for 7 d (HN), the level of osteocalcin increased rapidly from day 10, peaking at day 12, as compared with cells in the other groups. NN, normoxia for 14 d; NH, normoxia for 7 d followed by hypoxia for 7 d; and HH, hypoxia for 14 d. ^a $P < 0.05$.

States) was performed to measure the expression of collagen type I (Rn00801649 g1) and osteocalcin (Rn01455285 g1) ($n = 5$ for each group). Thermal cycling conditions were 20 s at 95 °C for activation (TaqMan Fast Universal PCR Master Mix, Thermo Fisher Scientific) followed by 40 cycles of 1 s at 95 °C for denaturation, and 20 s at 60 °C for annealing and extension. Expression levels were normalized to β -actin (Rn00667869 m1). All experiments were performed in duplicate.

Statistical analysis

Mann-Whitney *U*-test and one-way ANOVA with Bonferroni *post hoc* multiple comparisons were performed using SPSS Ver. 17.0 (IBM, Chicago, IL, United States). *P* values less than 0.05 were considered statistically significant for both tests.

RESULTS

In vitro experiment

Osteocalcin secretion measurement: At day 7, osteocalcin secretion levels were low in all four groups. In the HN group, levels started to increase rapidly at day 10, peaking and stabilizing from day 12 ($P < 0.05$). Levels also increased steadily for cells in the NN group, but remained low for cells in the NH and HH groups through day 14 (Figure 1).

Observations of cell morphology and calcium deposition: In the NN and HN groups, the differentiated cells appeared cuboidal, and cell nodules with calcium deposition were observed. In the NH and HH groups, however, few such nodules were seen. Instead, the cells in the NH and HH groups appeared spindle-shaped and undifferentiated, particularly in the HH group (Figure 2).

Calcium content measurements: At day 14, we compared the adjusted total calcium deposition in the culture wells among the four groups. The HN group showed the highest calcium deposition, followed by the NN group, as compared with HH and NH groups ($P < 0.05$) (Figure 3).

Alkaline phosphatase staining: The NH, HN, and HH groups showed broader positive staining areas as compared with the NN group. Among the three groups, the HN group showed the strongest and the broadest ALP staining. Staining intensity was weakest in the HH group (Figure 4).

Cell proliferation assay: Cell proliferation for cells grown under hypoxic conditions was significantly higher than that of cells grown under normoxic conditions ($P < 0.05$) (Figure 5).

In vivo experiment

Histological evaluation: HN constructs harvested from rats showed prominent new bone formation within the pores of the β -TCP discs. In contrast, there was less new bone formation observed in the NN constructs. This could be due to the reduced osteogenic ability of second-passage MSCs; although, the same cells were used for the HN group. The histological findings were consistent between the two blinded observers (KI and TE) (Figure 6).

Calcium contents measurement: HN constructs showed a significantly higher amount of calcium deposition as compared with the NN constructs (Figure 7).

Real-time quantitative PCR: We measured significantly higher expression of collagen type I mRNA in the HN constructs as compared with the NN constructs (Figure 8). Furthermore, there was a tendency for higher expression of osteocalcin mRNA, although this difference was not statistically significant.

DISCUSSION

Hypoxic environments affect all facets of cell function, including survival, proliferation, differentiation, migration, and endocrine and paracrine signaling. Hypoxia is mediated through the activity of transcription factors, most notably hypoxia inducible factor (HIF)^[15]. Because of the broad range of effects that hypoxia has on cell function, the effects of hypoxia on the osteogenic ability of MSCs has been controversial^[10,11]. In addition, differences in the experimental cell types and culture methods, and the timing of exposure to the hypoxic environment can lead to variation in findings among different studies. On the basis of our methods for regenerative medicine, we show that hypoxia (5% O₂) enhances cell proliferation when delivered for 7 d followed by normoxia for 7 d (HN group), with observed

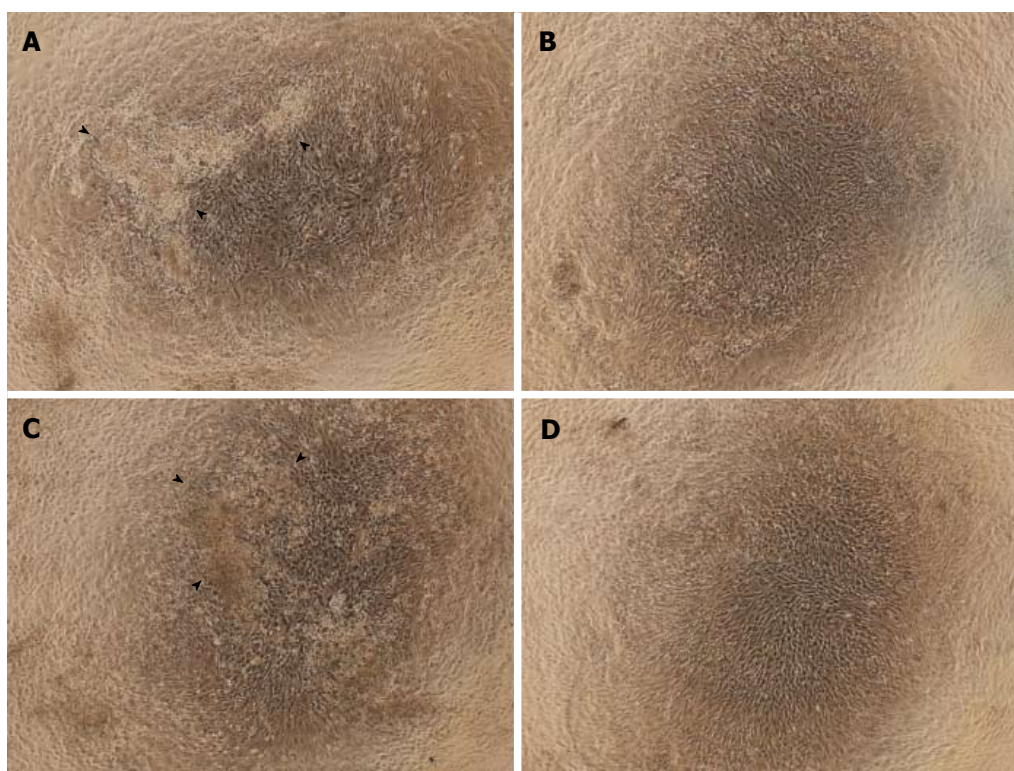


Figure 2 Observations of cell morphology and calcium deposition. Cells treated with normoxia (21% O₂) for 14 d (NN) (A) or hypoxia (5% O₂) for 7 d followed by normoxia for 7 d (HN) (C) were differentiated and cuboidal-shaped, and showed cell nodules with calcium deposits. These changes were not present in cells exposed to normoxia for 7 d followed by hypoxia for 7 d (NH) (B) or hypoxia for 14 d (HH) (D). Arrowheads indicate calcium deposition.

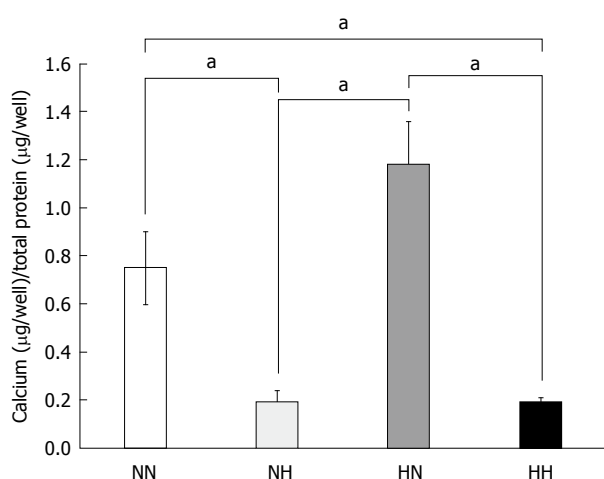


Figure 3 Calcium deposition. Cells were exposed to normoxia (21% O₂) for 14 d (NN), normoxia for 7 d followed by hypoxia (5% O₂) for 7 d (NH), hypoxia for 7 d followed by normoxia for 7 d (HN), or hypoxia for 14 d (HH). Calcium deposition was adjusted to total protein content. Cells in the HN group showed the highest amount of calcium deposition among the four groups. ^a*P* < 0.05.

increases in osteocalcin secretion, calcium deposition, and ALP staining, suggestive of enhanced osteogenesis in MSCs. The results of our *in vivo* experiments also show that hypoxic pretreatment can drive higher rates of osteogenesis as compared with normal oxygen levels.

With regards to cell survival, others^[16] have shown that hypoxic preconditioning (0.5% O₂ for 24 h) both

in vitro and *in vivo* can increase the expression of pro-survival factors, Bcl-2 and Bcl-xL, and reduce cell death and caspase-3 activation in stem cells as compared with stem cells grown under normal oxygen conditions. Despite some contradictory results^[17,18], many other studies also support the positive effects of hypoxia (1.5%-8% O₂) on MSC proliferation^[10,11,19-22]. Here, we also showed enhanced MSC proliferation with hypoxic preconditioning, and suggest that the elevated osteogenic ability of the cells in the HN group may have arisen from the enhanced cell proliferation during the first 7 d of hypoxic culture.

D'Ippolito *et al.*^[11] previously reported an inhibitory effect of hypoxia on osteogenic differentiation of human marrow-isolated adult multilineage-inducible cells. However, they also reported that hypoxia shortened population doubling time, resulting in an increase in the rate of cell proliferation, which agrees with our results. However, in their study, hypoxia was employed throughout the culture period. In our study, we found that cells treated continuously under hypoxic conditions (HH group; 5% hypoxia for 14 d) showed lower proliferation, less osteogenic ability, and retained an undifferentiated morphology. Collectively, these data suggest that the appropriate timing of hypoxia is important for stimulating osteogenesis. To the best of our knowledge, our study is the first to seek the best temporal combination of hypoxia and normoxia during osteogenic culture.

Environmental preconditioning, such as through

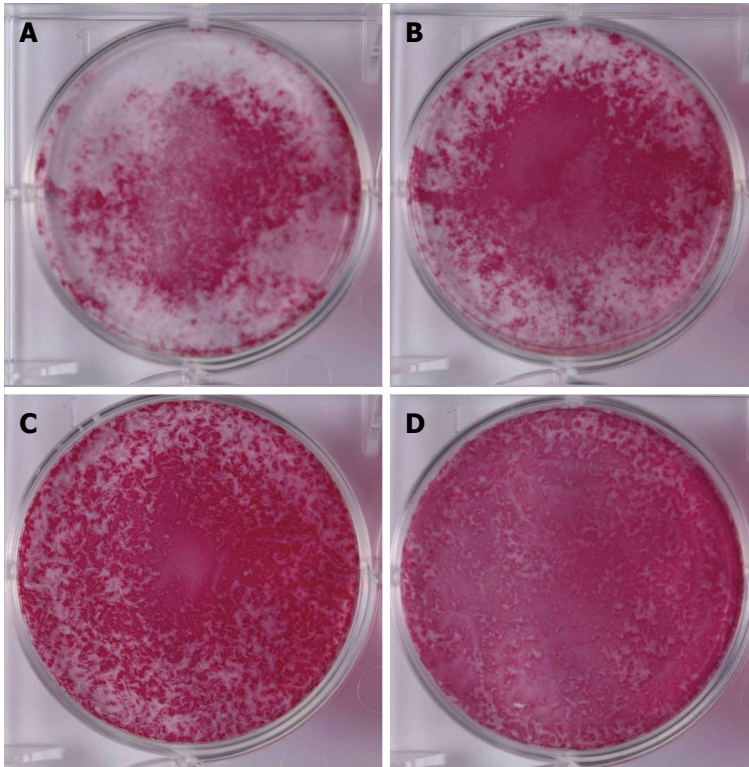


Figure 4 Alkaline phosphatase staining. Cells were exposed to normoxia (21% O₂) for 14 d (NN) (A), normoxia for 7 d followed by hypoxia (5% O₂) for 7 d (NH) (B), hypoxia for 7 d followed by normoxia for 7 d (HN) (C), or hypoxia for 14 d (HH) (D) and then stained with alkaline phosphatase staining. The HN group showed the strongest and the broadest alkaline phosphatase staining (C).

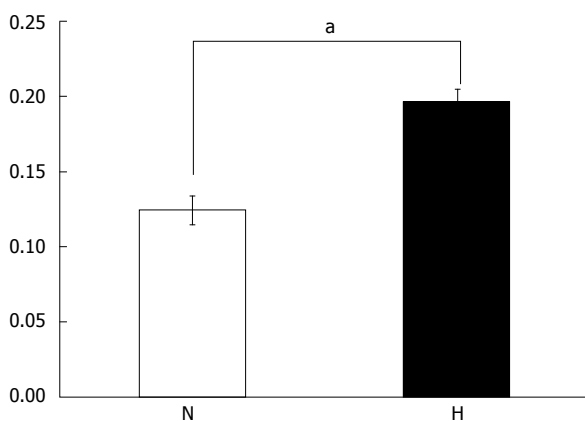


Figure 5 Cell proliferation assay. Cell proliferation under hypoxic conditions (H: 5% O₂) was significantly higher than that under normal oxygen conditions (N: 21% O₂). ^aP < 0.05.

the use of hypoxia or growth factor supplementation offers a potentially powerful approach to enhance the proliferative and differentiative ability of MSCs^[23]. Hagmann *et al.*^[24] added fibroblast growth factor-2 during human MSCs expansion, and found higher cell population growth indices and a downregulation of CD146, a marker of endothelial cells. Others have shown that decellularized extracellular matrix (dECM), deposited by stem cells, is another promising approach to create environmental preconditioning. He *et al.*^[25] construct a dECM by culturing porcine synovium-derived stem cells (SDSCs) on fibronectin-coated surfaces, and then lysed the cells using a nonionic surfactant. The authors then seeded SDSCs onto the dECM and found increased cell numbers and enhanced

chondrogenic capacity as compared with cells seeded on control substrates.

Numerous studies have reported the use of bio-engineered scaffolds for enhanced bone repair^[6-8]. However, considering the potential disadvantages of scaffolds, such as reduced biocompatibility^[9] or the possibility of causing an immunological response, we believe that scaffold- and recombinant protein-free techniques are better solutions. Recently, we reported the culture of MSCs as OMCSs, and demonstrated their osteogenic potential *in vitro* and bone formation *in vivo* in the absence of scaffolds^[2]. Furthermore, OMCSs can be used in non-union surgery and to accelerate bone-tendon healing in ligament reconstruction^[3]. Here, we showed that OMCSs preconditioned with hypoxic conditions offers a simple and inexpensive method to improve the osteogenic capacity of cells, and this may provide a better method for MSC-mediated bone tissue engineering.

Hypoxia as an environment preconditioning tool has been explored predominantly as a strategy to enhance the chondrogenic ability of MSCs^[23]. Human MSCs, preconditioned under hypoxic and normoxic environments, were encapsulated in alginate hydrogels and implanted subcutaneously onto the backs of nude mice. Whereas the hypoxia-preconditioned implants retained a chondral phenotype after implantation, the normoxia-preconditioned implants underwent calcification, vascular invasion, and subsequent endochondral ossification^[26]. Jukes *et al.*^[27] also utilized endochondral ossification to engineer bone tissue from mouse embryonic stem cells; however, the authors did not modulate the oxygen tension. We speculate that the

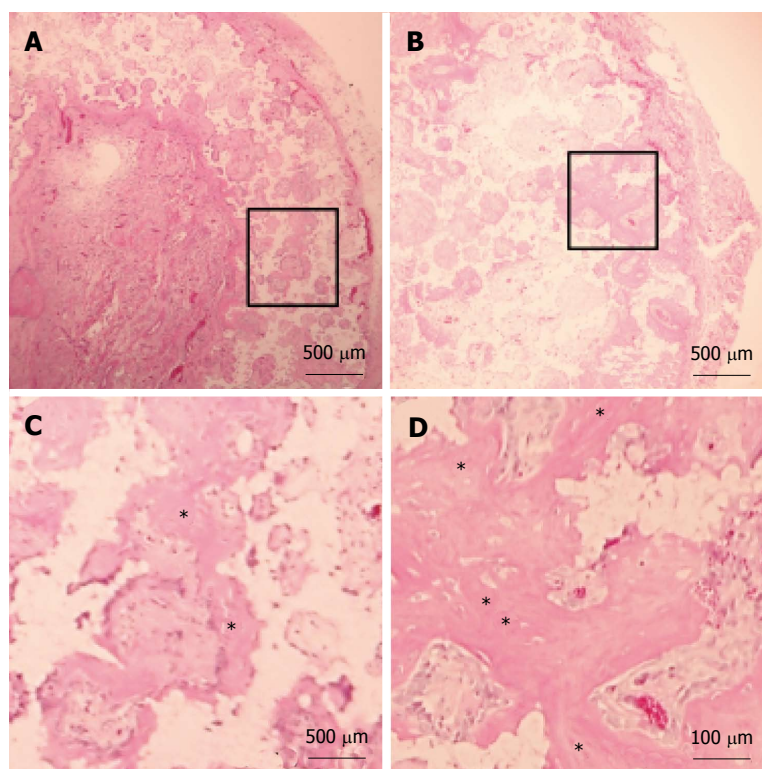


Figure 6 Histology of β -tricalcium phosphate discs wrapped with osteogenic matrix cell sheets. Cell sheets were exposed to hypoxia (5% O_2) for 7 d followed by normoxia (21% O_2) for 7 d (B) or normoxia for 14 d (A). Prominent newly formed bone (*) was observed in the HN group. (C) and (D) are higher magnifications of squared areas indicated in (A) and (B), respectively.

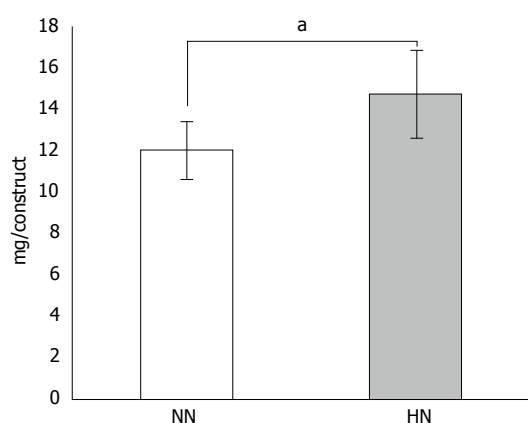


Figure 7 Calcium content in β -tricalcium phosphate discs wrapped with osteogenic matrix cell sheet. Cell sheets were exposed to hypoxia (5% O_2) for 7 d followed by normoxia (21% O_2) for 7 d (HN) or normoxia for 14 d (NN). The HN group showed a significantly higher amount of calcium content compared with the NN group. $^aP < 0.05$.

increased osteogenic ability of the cells in the HN group in our study also developed through endochondral ossification. However, the time course is relatively short and additional experiments will be needed to confirm this hypothesis.

There were a few limitations in this study. First, because we used only rat MSCs, evaluations using human MSCs should be performed in future experiments. Second, more detailed intracellular signaling changes caused by the hypoxic environment should be elucidated at the molecular level. Third, although the temporal combination of hypoxia and normoxia clearly boosted osteogenesis of rat MSCs, it is unclear whether this increased osteogenesis is solely caused

by the increase in cell number or whether hypoxic preconditioning also enhanced the differentiation and mineralization of these cells. Despite these limitations, our findings offer an important insight into the potential for hypoxic preconditioning in the field of bone regenerative medicine.

In conclusion, we show that modifying oxygen tension can improve the higher osteogenic ability of rat MSCs both under *in vitro* and *in vivo* conditions. Thus, hypoxic preconditioning appears to be an effective method for MSC-mediated bone tissue engineering.

ACKNOWLEDGMENTS

We would like to thank to Ms. F. Kunda and Ms. M. Matsumura (Nara Medical University) for their technical assistance.

COMMENTS

Background

Bone tissue engineering using marrow stromal cells (MSCs) as a cell source has been widely studied. Among several factors affecting MSC osteogenesis, oxygen tension is important; however, the specific tension and timing of hypoxic preconditioning remains controversial. Here, the authors investigated how hypoxia affects the osteogenic ability of rat MSCs *in vitro* and within cell sheets in a subcutaneous scaffold *in vivo*.

Research frontiers

Various methods have been reported to enhance the osteogenic ability of MSCs, including the use of scaffolds and growth factors. However, considering the potential disadvantages of these approaches, such as immunological responses to the scaffold, as well as the complicated procedure of producing suitable scaffolds for insertion, techniques that avoid these approaches would be better suited. In this context, the authors suggest that modulating oxygen

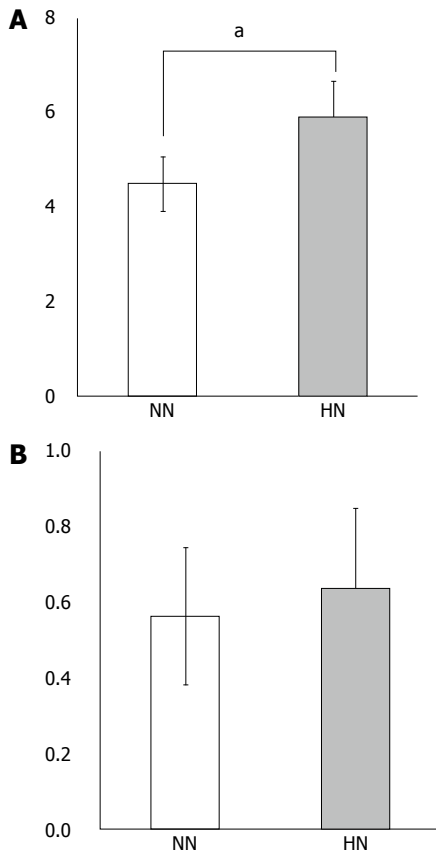


Figure 8 Real-time quantitative PCR of β -tricalcium phosphate discs wrapped with osteogenic matrix cell sheet. Increased collagen type I mRNA expression was observed in the HN group exposed to hypoxia (5% O_2) for 7 d followed by normoxia (21% O_2) for 7 d, compared with the NN group exposed to normoxia for 14 d (A). A tendency for higher expression of osteocalcin mRNA was also observed in the HN group (B). $^aP < 0.05$.

tension and the use of osteogenic matrix cell sheet (OMCS) could offer a promising method for bone repair.

Innovations and breakthroughs

Here, the authors show that modifying oxygen tension using hypoxia preconditioning can enhance the osteogenic ability of MSCs *in vitro*, and similarly advance bone formation in OMCS wrapped around scaffolds when implanted subcutaneously on the backs of rats.

Applications

Modulating oxygen tension to enhance osteogenesis is a simple and inexpensive preconditioning method. Combining OMCSs with appropriately timed hypoxia can enhance bone tissue engineering.

Terminology

MSCs: Marrow stromal cells, derived from the bone marrow. MSCs can be induced to differentiate into osteogenic, chondrogenic, adipogenic or other cell lineages with the appropriate media conditions. These cells are routinely used as a cell source for musculoskeletal tissue engineering purposes. OMCSs: Osteogenic matrix cell sheets are MSCs cultured with dexamethasone and ascorbic acid phosphate (originally with also β -glycerophosphate). The cells undergo differentiation and matrix production, producing a cell sheet structure that can be collected as a single cell sheet. These sheets offer *in vitro* osteogenic potential and *in vivo* bone formation without the need for scaffolds. OMCSs in the current study were implanted into the backs of rats using a β -TCP scaffold for positioning and to be able to identify the OMCS later for harvesting to measure bone formation changes. OMCSs can be used alone for non-union surgery and to accelerate bone-tendon healing in ligament reconstruction.

Peer-review

This study is new. This manuscript aims at investigating whether modifying oxygen tension affected MSC osteogenesis. The authors found that low oxygen pretreatment for 7-d following by 7-d treatment under normal oxygen could promote MSCs' osteogenic differentiation in both *in vitro* and *in vivo* models.

REFERENCES

- Ohgushi H, Dohi Y, Katuda T, Tamai S, Tabata S, Suwa Y. In vitro bone formation by rat marrow cell culture. *J Biomed Mater Res* 1996; **32**: 333-340 [PMID: 8897137 DOI: 10.1002/(SICI)1097-4636(199611)32:3<333::AID-JBM5>3.0.CO;2-T]
- Akahane M, Nakamura A, Ohgushi H, Shigematsu H, Dohi Y, Takakura Y. Osteogenic matrix sheet-cell transplantation using osteoblastic cell sheet resulted in bone formation without scaffold at an ectopic site. *J Tissue Eng Regen Med* 2008; **2**: 196-201 [PMID: 18493911 DOI: 10.1002/term.81]
- Inagaki Y, Uematsu K, Akahane M, Morita Y, Ogawa M, Ueha T, Shimizu T, Kura T, Kawate K, Tanaka Y. Osteogenic matrix cell sheet transplantation enhances early tendon graft to bone tunnel healing in rabbits. *Biomed Res Int* 2013; **2013**: 842192 [PMID: 24106718 DOI: 10.1155/2013/842192]
- Caplan AI. Mesenchymal stem cells. *J Orthop Res* 1991; **9**: 641-650 [PMID: 1870029 DOI: 10.1002/jor.1100090504]
- Ueha T, Akahane M, Shimizu T, Uchihara Y, Morita Y, Nitta N, Kido A, Inagaki Y, Kawate K, Tanaka Y. Utility of tricalcium phosphate and osteogenic matrix cell sheet constructs for bone defect reconstruction. *World J Stem Cells* 2015; **7**: 873-882 [PMID: 26131318 DOI: 10.4252/wjsc.v7.i5.873]
- Chiu LH, Lai WF, Chang SF, Wong CC, Fan CY, Fang CL, Tsai YH. The effect of type II collagen on MSC osteogenic differentiation and bone defect repair. *Biomaterials* 2014; **35**: 2680-2691 [PMID: 24411332 DOI: 10.1016/j.biomaterials.2013.12.005]
- He Y, Dong Y, Cui F, Chen X, Lin R. Ectopic osteogenesis and scaffold biodegradation of nano-hydroxyapatite-chitosan in a rat model. *PLoS One* 2015; **10**: e0135366 [PMID: 26258851 DOI: 10.1371/journal.pone.0135366]
- Qi Y, Niu L, Zhao T, Shi Z, Di T, Feng G, Li J, Huang Z. Combining mesenchymal stem cell sheets with platelet-rich plasma gel/calcium phosphate particles: a novel strategy to promote bone regeneration. *Stem Cell Res Ther* 2015; **6**: 256 [PMID: 26689714 DOI: 10.1186/s13287-015-0256-1]
- Eloumi-Hannachi I, Yamato M, Okano T. Cell sheet engineering: a unique nanotechnology for scaffold-free tissue reconstruction with clinical applications in regenerative medicine. *J Intern Med* 2010; **267**: 54-70 [PMID: 20059644 DOI: 10.1111/j.1365-2796.2009.02185.x]
- Lennon DP, Edmison JM, Caplan AI. Cultivation of rat marrow-derived mesenchymal stem cells in reduced oxygen tension: effects on *in vitro* and *in vivo* osteochondrogenesis. *J Cell Physiol* 2001; **187**: 345-355 [PMID: 11319758 DOI: 10.1002/jcp.1081]
- D'Ippolito G, Diabira S, Howard GA, Roos BA, Schiller PC. Low oxygen tension inhibits osteogenic differentiation and enhances stemness of human MIAMI cells. *Bone* 2006; **39**: 513-522 [PMID: 16616713 DOI: 10.1016/j.bone.2006.02.061]
- Harrison JS, Rameshwar P, Chang V, Bandari P. Oxygen saturation in the bone marrow of healthy volunteers. *Blood* 2002; **99**: 394 [PMID: 11783438 DOI: 10.1182/blood.V99.1.394]
- Maurer P, Meyer L, Eckert AW, Berginski M, Schubert J. Measurement of oxygen partial pressure in the mandibular bone using a polarographic fine needle probe. *Int J Oral Maxillofac Surg* 2006; **35**: 231-236 [PMID: 16185845 DOI: 10.1016/j.ijom.2005.07.016]
- Nakamura A, Dohi Y, Akahane M, Ohgushi H, Nakajima H, Funaoka H, Takakura Y. Osteocalcin secretion as an early marker of *in vitro* osteogenic differentiation of rat mesenchymal stem cells. *Tissue Eng Part C Methods* 2009; **15**: 169-180 [PMID: 19191495 DOI: 10.1089/ten.tec.2007.0334]
- Guillemin K, Krasnow MA. The hypoxic response: huffing and HIFing. *Cell* 1997; **89**: 9-12 [PMID: 9094708 DOI: 10.1016/S0092-8674(00)80176-2]

- 16 **Hu X**, Yu SP, Fraser JL, Lu Z, Ogle ME, Wang JA, Wei L. Transplantation of hypoxia-preconditioned mesenchymal stem cells improves infarcted heart function via enhanced survival of implanted cells and angiogenesis. *J Thorac Cardiovasc Surg* 2008; **135**: 799-808 [PMID: 18374759 DOI: 10.1016/j.jtcvs.2007.07.071]
- 17 **Wang DW**, Fermor B, Gimble JM, Awad HA, Guilak F. Influence of oxygen on the proliferation and metabolism of adipose derived adult stem cells. *J Cell Physiol* 2005; **204**: 184-191 [PMID: 15754341 DOI: 10.1002/jcp.20324]
- 18 **Hung SC**, Pochampally RR, Hsu SC, Sanchez C, Chen SC, Spees J, Prockop DJ. Short-term exposure of multipotent stromal cells to low oxygen increases their expression of CX3CR1 and CXCR4 and their engraftment in vivo. *PLoS One* 2007; **2**: e416 [PMID: 17476338 DOI: 10.1371/journal.pone.0000416]
- 19 **Grayson WL**, Zhao F, Izadpanah R, Bunnell B, Ma T. Effects of hypoxia on human mesenchymal stem cell expansion and plasticity in 3D constructs. *J Cell Physiol* 2006; **207**: 331-339 [PMID: 16331674 DOI: 10.1002/jcp.20571]
- 20 **Grayson WL**, Zhao F, Bunnell B, Ma T. Hypoxia enhances proliferation and tissue formation of human mesenchymal stem cells. *Biochem Biophys Res Commun* 2007; **358**: 948-953 [PMID: 17521616 DOI: 10.1016/j.bbrc.2007.05.054]
- 21 **Ren H**, Cao Y, Zhao Q, Li J, Zhou C, Liao L, Jia M, Zhao Q, Cai H, Han ZC, Yang R, Chen G, Zhao RC. Proliferation and differentiation of bone marrow stromal cells under hypoxic conditions. *Biochem Biophys Res Commun* 2006; **347**: 12-21 [PMID: 16814746 DOI: 10.1016/j.bbrc.2006.05.169]
- 22 **Carrancio S**, López-Holgado N, Sánchez-Guijo FM, Villarón E, Barbado V, Tabera S, Díez-Campelo M, Blanco J, San Miguel JF, Del Cañizo MC. Optimization of mesenchymal stem cell expansion procedures by cell separation and culture conditions modification. *Exp Hematol* 2008; **36**: 1014-1021 [PMID: 18468767 DOI: 10.1016/j.exphem.2008.03.012]
- 23 **Pei M**. Environmental preconditioning rejuvenates adult stem cells' proliferation and chondrogenic potential. *Biomaterials* 2017; **117**: 10-23 [PMID: 27923196 DOI: 10.1016/j.biomaterials.2016.11.049]
- 24 **Hagmann S**, Moradi B, Frank S, Dreher T, Kämmerer PW, Richter W, Gotterbarm T. FGF-2 addition during expansion of human bone marrow-derived stromal cells alters MSC surface marker distribution and chondrogenic differentiation potential. *Cell Prolif* 2013; **46**: 396-407 [PMID: 23869761 DOI: 10.1111/cpr.12046]
- 25 **He F**, Chen X, Pei M. Reconstruction of an in vitro tissue-specific microenvironment to rejuvenate synovium-derived stem cells for cartilage tissue engineering. *Tissue Eng Part A* 2009; **15**: 3809-3821 [PMID: 19545204 DOI: 10.1089/ten.TEA.2009.0188]
- 26 **Leijten J**, Georgi N, Moreira Teixeira L, van Blitterswijk CA, Post JN, Karperien M. Metabolic programming of mesenchymal stromal cells by oxygen tension directs chondrogenic cell fate. *Proc Natl Acad Sci USA* 2014; **111**: 13954-13959 [PMID: 25205812 DOI: 10.1073/pnas.1410977111]
- 27 **Jukes JM**, Both SK, Leusink A, Sterk LM, van Blitterswijk CA, de Boer J. Endochondral bone tissue engineering using embryonic stem cells. *Proc Natl Acad Sci USA* 2008; **105**: 6840-6845 [PMID: 18467492 DOI: 10.1073/pnas.0711662105]

P- Reviewer: Pei M **S- Editor:** Kong JX **L- Editor:** A
E- Editor: Lu YJ





Published by **Baishideng Publishing Group Inc**
7901 Stoneridge Drive, Suite 501, Pleasanton, CA 94588, USA
Telephone: +1-925-223-8242
Fax: +1-925-223-8243
E-mail: bpgoffice@wjgnet.com
Help Desk: <http://www.f6publishing.com/helpdesk>
<http://www.wjgnet.com>

