


World Journal of *Methodology*

World J Methodol 2012 February 26; 2(1): 1-17



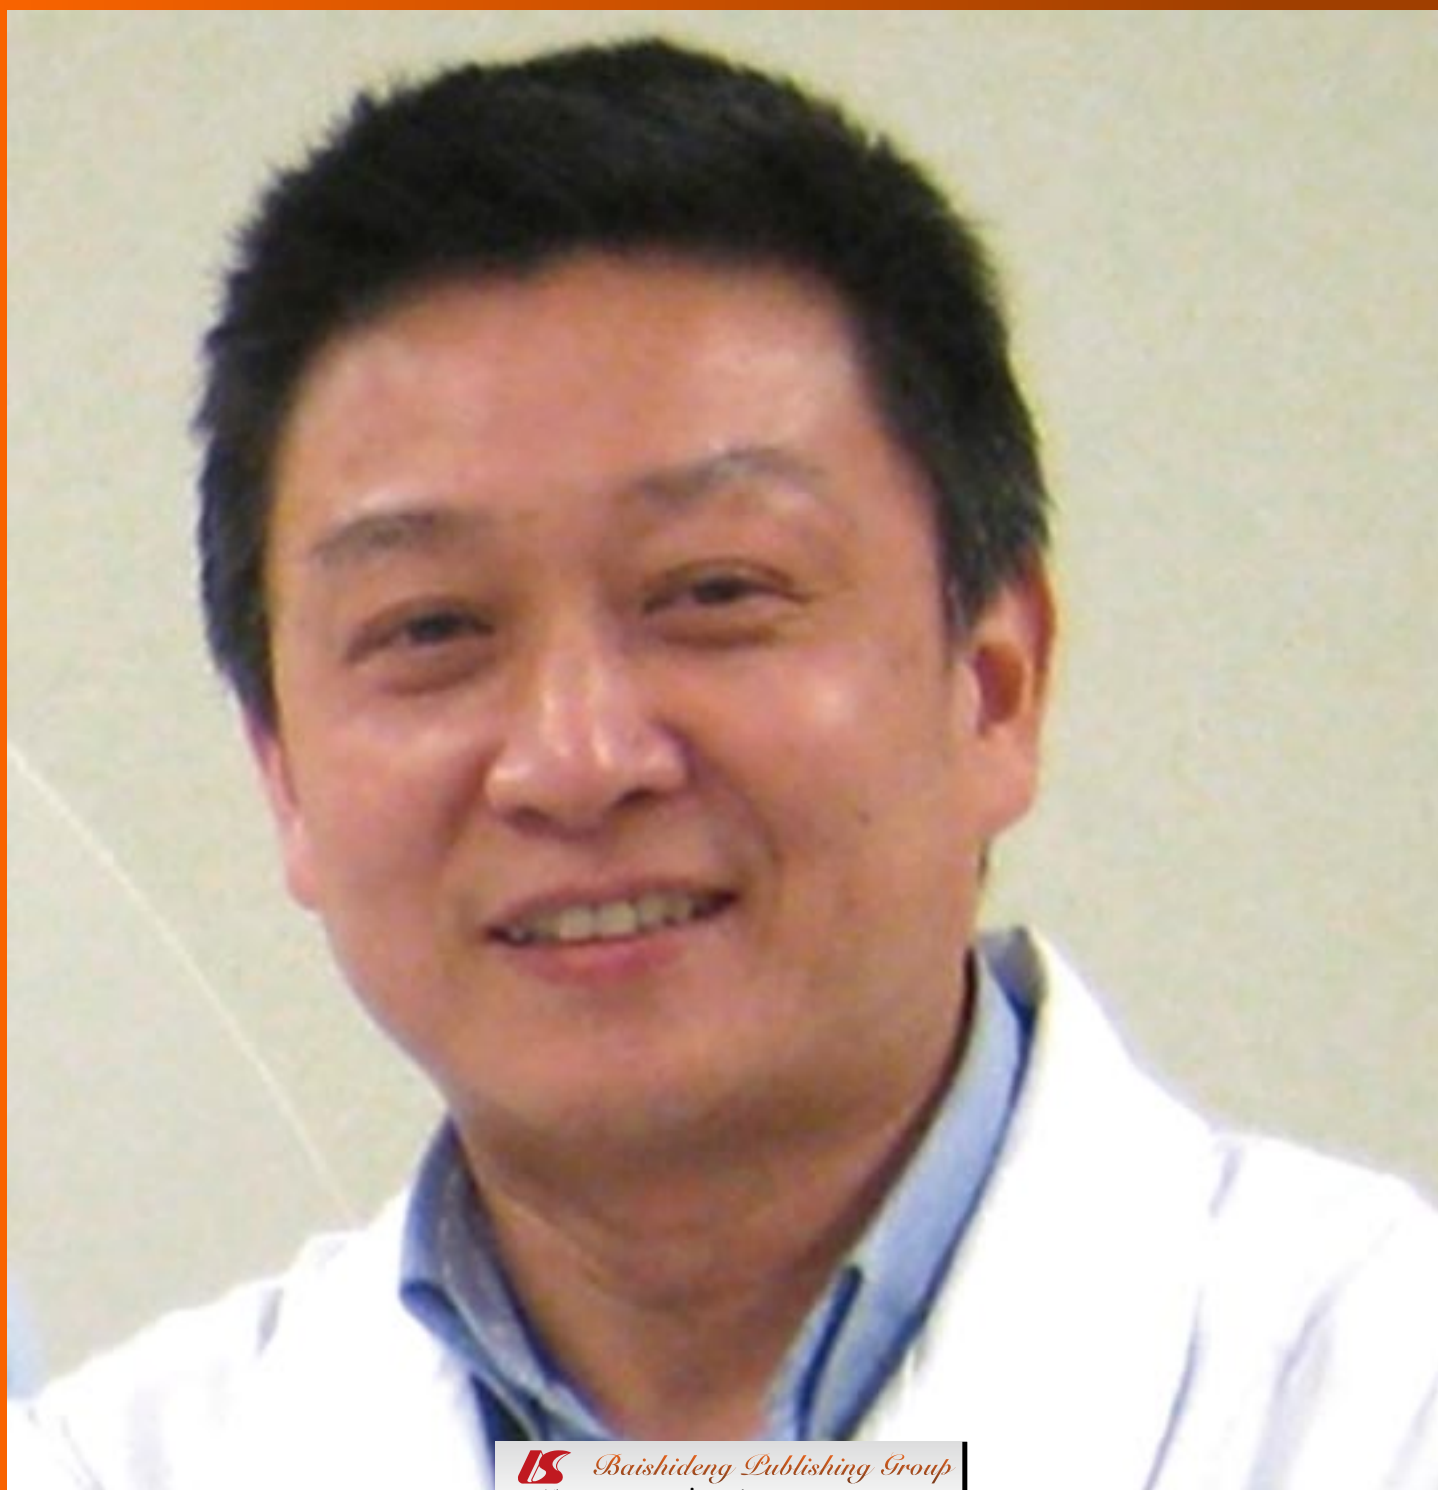

Editorial Board

2011-2015

The *World Journal of Methodology* Editorial Board consists of 238 members, representing a team of worldwide experts in methodology. They are from 41 countries, including Argentina (2), Australia (7), Austria (3), Belgium (4), Brazil (3), Canada (10), China (27), Croatia (1), Cuba (1), Czech (3), Denmark (2), Egypt (1), France (6), Germany (4), Greece (3), Hungary (2), India (8), Iran (3), Israel (1), Italy (18), Japan (12), Lithuania (1), Malaysia (1), Mexico (2), Netherlands (2), New Zealand (1), Norway (3), Pakistan (2), Poland (2), Portugal (3), Romania (4), Russia (2), South Korea (3), Spain (17), Sweden (1), Thailand (2), Turkey (2), United Arab Emirates (1), United Kingdom (10), United States (57), and Uruguay (1).

EDITOR-IN-CHIEF

Yicheng Ni, *Leuven*

STRATEGY ASSOCIATE

EDITORS-IN-CHIEF

Guido Gainotti, *Rome*

Val J GebSKI, *Sydney*

Bo Hang, *Berkeley*

George A Kelley, *Morgantown*

Sang-Soo Lee, *Chuncheon*

Gerhard Litscher, *Graz*

Laurentiu M Popescu, *Bucharest*

António Vaz Carneiro, *Lisboa*

GUEST EDITORIAL BOARD MEMBERS

Wen-Hsiung Chan, *Chung Li*

Long-Sen Chang, *Kaohsiung*

Hung-Jen Liu, *Taichung*

Ko-Huang Lue, *Taichung*

Chin-Tsan Wang, *I Lan*

Yau-Huei Wei, *Taipei*

Ching-Feng Weng, *Hualien*

MEMBERS OF THE EDITORIAL BOARD



Argentina

Paula Abate, *Córdoba*

Rodolfo G Wuilloud, *Mendoza*



Australia

Felix Acker, *Melbourne*

Seetal Dodd, *Geelong*

Guy D Eslick, *Sydney*

Adrian J Gibbs, *Canberra*

Phillipa Jane Hay, *Sydney*
Sanjay Patole, *Perth*



Austria

Gerwin A Bernhardt, *Graz*

Martin Voracek, *Vienna*



Belgium

Zeger Debyser, *Leuven*

Kristien Hens, *Leuven*

Piet K Vanhoenacker, *Aalst*



Brazil

Monica L Andersen, *Sao Paulo*

Mariana de Andrea Hacker, *Rio de Janeiro*

Moacyr A Rebello, *Rio de Janeiro*



Canada

Ahmed M Abou-Setta, *Edmonton*

Amir Azarpazhooh, *Toronto*

Elijah Dixon, *Calgary*

Martin A Katzman, *Toronto*

Alejandro Lazo-Langner, *London*

Richard WJ Neufeld, *London*

Prakesh S Shah, *Toronto*

Léon C van Kempen, *Montreal*

Yuzhuo Wang, *Vancouver*

Haishan Zeng, *Vancouver*



China

Deng-Feng Cao, *Beijing*

George G Chen, *Hong Kong*

William CS Cho, *Hong Kong*

Meng-Jie Dong, *Hangzhou*

Hani El-Nezami, *Hong Kong*

Rajiv Kumar Jha, *Xi'an*

Huang-Xian Ju, *Nanjing*

Yun-Feng Lin, *Chengdu*

Wing-Yee Lui, *Hong Kong*

Feng-Ming Luo, *Chengdu*

Jing-Yun Ma, *Beijing*

Hong-Xiang Sun, *Hangzhou*

Shi-Ying Xuan, *Qingdao*

Xilin Yang, *Hong Kong*

Bang-Ce Ye, *Shanghai*

Yue-Hong Zhang, *Hangzhou*

Zhongtying Zhao, *Hong Kong*

Chun-Fu Zheng, *Wuhan*

Ma Zheng, *Beijing*

Jun-Jie Zhu, *Nanjing*



Croatia

Marijeta Kralj, *Zagreb*



Cuba

Mariano R Ricard, *Habana*



Czech

Kamil Kuca, *Hradec Kralove*

Jiri Sedy, *Prague*

Miroslav Sip, *Ceske Budejovice*



Denmark

Morten Mørup, *Lyngby*

Hans Sanderson, *Roskilde*



Egypt

Nervana S Bayoumi, *Cairo*



France

Marc Y Bardou, *Dijon*
Mohammed M Bettahar, *Nancy*
Olivier David, *Grenoble*
Florian Lesage, *Sophia Antipolis*
Patrick Maison, *Creteil*
Sandrine Marquet, *Marseille*



Germany

Harald Hampel, *Frankfurt/ Main*
Frank Peinemann, *Cologne*
M Lienhard Schmitz, *Giessen*
Alfons Schnitzler, *Duesseldorf*



Greece

Konstantinos P Economopoulos, *Athens*
Demosthenes Panagiotakos, *Athens*
Issidora Papassideri, *Athens*



Hungary

Péter Halász, *Budapest*
András Komócsi, *Pécs*



India

Dipshikha Chakravorty, *Bangalore*
DK Dhawan, *Chandigarh*
R Jayakumar, *Cochin*
Abdul Viqar Khan, *Aligarh*
Geetha Manivasagam, *Vellore*
Jacob Peedicayil, *Vellore*
YS Prabhakar, *Lucknow*
Rakesh Kumar Sinha, *Ranchi*



Iran

Mehran Javanbakht, *Tehran*
Enayat Kalantar, *Sanandaj*
Shekoufeh Nikfar, *Tehran*



Israel

Dan Frenkel, *Tel Aviv*



Italy

Giuseppe Biondi-Zoccai, *Modena*
Carlo Bonanno, *Vicenza*
Paolo Borriero, *Turin*
Filippo Cademartiri, *Monastier di Treviso*

Alberto Chiesa, *Bologna*
Annamaria Cimini, *L'Aquila*
Giovanni Di Leo, *San Donato Milanese*
Giovanna Ferraioli, *Milan*
Irene Floriani, *Milan*
Landoni Giovanni, *Milano*
Stefano Girotti, *Bologna*
Paola Irato, *Padova*
Mario Mascalchi, *Florence*
Patrizia Mecocci, *Perugia*
Germano Orrù, *Cagliari*
Carlo Riccardi, *Perugia*
Mauro Valtieri, *Rome*



Japan

Kohei Akazawa, *Niigata*
Subash CB Gopinath, *Tsukuba*
Koichi Hattori, *Tokyo*
Satoshi Hirohata, *Okayama*
Masahiro Kohzuki, *Sendai*
Yoshinori Marunaka, *Kyoto*
Kenji Miura, *Tokorozawa*
Ryuichi Morishita, *Suita*
Mitsuhiro Noda, *Tokyo*
Yurai Okaji, *Tokyo*
Hirosato Seki, *Osaka*
Hisanori Umehara, *Kahoku-gun*



Lithuania

Giedrius Barauskas, *Kaunas*



Malaysia

Iis Sopyan, *Kuala Lumpur*



Mexico

Martha Rodríguez-Moran, *Durango*
Julio Sotelo, *Mexico*



Netherlands

Bart J Polder, *Emmeloord*
Frank Twisk, *Limmen*



New Zealand

Valery Feigin, *Auckland*



Norway

Cato Grønnerød, *Fredrikstad*
David F Mota, *Oslo*
Tore Syversen, *Trondheim*



Pakistan

Muhammad A Noor, *Islamabad*
Yasir Waheed, *Islamabad*



Poland

Piotr Dziegiel, *Wroclaw*
Tadeusz Robak, *Lodz*



Portugal

Nuno Lunet, *Porto*
Hugo Sousa, *Porto*



Romania

Elena Moldoveanu, *Bucharest*
Monica Neagu, *Bucharest*
Florin-Dan Popescu, *Bucharest*



Russia

Galina B Bolshakova, *Moscow*
Sergey V Dorozhkin, *Moscow*



South Korea

Sang Soo Hah, *Seoul*
Chang-Yong Lee, *Kongju*



Spain

Salvador F Aliño, *Valencia*
Mohamed Farouk Allam, *Cordoba*
Alejandro Cifuentes, *Madrid*
Miren Lopez de Alda, *Barcelona*
Joaquin de Haro, *Madrid*
Emma Garcia-Meca, *Cartagena*
Mónica H Giménez, *Zaragoza*
M de la Guardia, *Valencia*
Josep M Guerrero, *Barcelona*
Fernando Marin, *Madrid*
José A Orosa, *A Coruña*
Jesús Osada, *Zaragoza*
Soledad Rubio, *Córdoba*
Helmut Schröder, *Barcelona*
Jesus Simal-Gandara, *Ourense*
Gabriela Topa, *Madrid*
Miguel A Vallejo, *Madrid*



Sweden

Jenny Selander, *Stockholm*



Thailand

Amporn Jariyapongskul, *Bangkok*
Bungorn Sripanidkulchai, *Khon Kaen*



Turkey

Ferda E Percin, *Ankara*
Aysegul Yildiz, *Izmir*



United Arab Emirates

Hassib Narchi, *Al Ain*



United Kingdom

Richard H Barton, *London*

Paul Evans, *London*

Giuseppe Garcea, *Leicester*

Sinead Keeney, *Belfast*

Maurice J O'Kane, *Londonderry*

Abdullah Pandor, *Sheffield*

Susan Pang, *Teddington*

Pankaj Sharma, *London*

David E Whitworth, *Aberystwyth*

Shangming Zhou, *Swansea*



United States

Nasar U Ahmed, *Miami*

Mike Allen, *Milwaukee*

Srinivas Ayyadevara, *Little Rock*

Charles F Babbs, *West Lafayette*

Janet Barletta, *Baltimore*

Lawrence T Bish, *Philadelphia*

Richard W Bohannon, *Storrs*

Mark Bounthavong, *San Diego*

M Ahmad Chaudhry, *Burlington*

Pei Chen, *Beltsville*

Tao Chen, *Jefferson*

Yong Q Chen, *Winston-Salem*

Undurti N Das, *Shaker Heights*

Feng Ding, *Chapel Hill*

D Mark Estes, *Athens*

Bingliang Fang, *Houston*

Ronnie Fass, *Tucson*

Vesna D Garovic, *Rochester*

Alexandros Georgakilas, *Greenville*

Ronald Gillam, *Logan*

GAN Gowda, *West Lafayette*

James P Hardwick, *Rootstown*

Diane M Harper, *Kansas*

Odette A Harris, *Stanford*

Rod Havriluk, *Tallahassee*

Moonseong Heo, *Bronx*

Guoyuan Huang, *Evansville*

Reinhold J Hutz, *Milwaukee*

Bankole A Johnson, *Charlottesville*

Jennifer Kisamore, *Tulsa*

Georgios D Kitsios, *Boston*

Heidemarie Kremer, *Miami*

Dawei Li, *New Haven*

JL Mehta, *Little Rock*

Ray M Merrill, *Provo*

M Mimeault, *Nebraska*

Ron B Mitchell, *St Louis*

Yan Peng, *Dallas*

George Perry, *San Antonio*

Ilona Petrikovics, *Huntsville*

Shengping Qin, *Davis*

Peter J Quesenberry, *Providence*

P Hemachandra Reddy, *Beaverton*

Paul R Sanberg, *Tampa*

Dong-Chul Seo, *Bloomington*

Weihong Tan, *Gainesville*

Guangwen Tang, *Boston*

Catherine E Ulbricht, *Somerville*

Thomas TH Wan, *Orlando*

Xiao-Jing Wang, *Aurora*

Jang-Yen Wu, *Boca Raton*

Qing Wu, *Scottsdale*

Eleftherios S Xenos, *Lexington*

Xinan Yang, *Chicago*

Henry Zeringue, *Pittsburgh*



Uruguay

Matias Victoria, *Salto*



REVIEW

1

Dissolution mechanism of calcium apatites in acids: A review of literature

Dorozhkin SV

Contents

World Journal of Methodology
Volume 2 Number 1 February 26, 2012

ACKNOWLEDGMENTS I Acknowledgments to reviewers of *World Journal of Methodology*

APPENDIX I Meetings

I-V Instructions to authors

ABOUT COVER Yicheng Ni, MD, PhD, Professor, Editor-in-Chief of *World Journal of Methodology*, Department of Radiology, University Hospitals, KU, Leuven, Herestraat 49, B-3000, Leuven, Belgium

AIM AND SCOPE

World Journal of Methodology (*World J Methodol*, *WJM*, online ISSN 2222-0682, DOI: 10.5662) is a bimonthly peer-reviewed, online, open-access (OA), journal supported by an editorial board consisting of 23 experts in methodology from 41 countries.

WJM aims to rapidly report the most recent results in medical diagnostics, therapeutic techniques and equipment, clinical medical research, clinical and experimental techniques and methodology. It provides a platform to facilitate the integration of clinical medicine and experimental techniques and methodology to help clinicians improve diagnostic accuracy and therapeutic efficacy. The journal publishes original articles and reviews on the following topics: (1) Clinical medical techniques, including but not limited to those for pharmaceutical medicine, laboratory medicine, radioactive medicine, medical imaging, nuclear medicine, physical therapy, pathology, surgery, disinfection, nutritional therapy, transfusion and medical equipment; (2) Clinical medical research on etiology, epidemiology, pathogenesis, morphology and function, signs and symptoms, clinical trials, and evidence-based medicine; and (3) Laboratory methodology, including but not limited to techniques in DNA/RNA sequencing, preparation and transformation of competent cells, PCR, protein biochemistry, cell biology, genetics and epigenetics, immunology, microbiology, animal models of human pathologies, bioinformatics, and laboratory equipment manipulation and control.

FLYLEAF

I-III Editorial Board

EDITORS FOR THIS ISSUE

Responsible Assistant Editor: Yuan Zhou
Responsible Electronic Editor: Jin-Lei Wang
Proofing Editor-in-Chief: Lian-Sheng Ma

Responsible Science Editor: Jin-Lei Wang
Proofing Editorial Office Director: Jin-Lei Wang

NAME OF JOURNAL
World Journal of Methodology

ISSN
ISSN 2222-0682 (online)

LAUNCH DATE
September 26, 2011

FREQUENCY
Bimonthly

EDITING
Editorial Board of *World Journal of Methodology*
Room 903, Building D, Ocean International Center,
No. 62 Dongsihuan Zhonglu, Chaoyang District,
Beijing 100025, China
Telephone: +86-10-85381891
Fax: +86-10-85381893
E-mail: wjm@wjgnet.com
<http://www.wjgnet.com>

EDITOR-IN-CHIEF
Yicheng Ni, MD, PhD, Professor, Department of

Radiology, University Hospitals, KU, Leuven, Herestraat 49, B-3000, Leuven, Belgium

EDITORIAL OFFICE
Jin-Lei Wang, Director
World Journal of Methodology
Room 903, Building D, Ocean International Center,
No. 62 Dongsihuan Zhonglu, Chaoyang District,
Beijing 100025, China
Telephone: +86-10-85381891
Fax: +86-10-85381893
E-mail: wjm@wjgnet.com
<http://www.wjgnet.com>

PUBLISHER
Baishideng Publishing Group Co., Limited
Room 1701, 17/F, Henan Building,
No.90 Jaffe Road, Wanchai,
Hong Kong, China
Fax: +852-31158812
Telephone: +852-58042046
E-mail: bpg@baishideng.com
<http://www.wjgnet.com>

PUBLICATION DATE
February 26, 2012

COPYRIGHT
© 2012 Baishideng. Articles published by this Open-Access journal are distributed under the terms of the Creative Commons Attribution Non-commercial License, which permits use, distribution, and reproduction in any medium, provided the original work is properly cited, the use is non commercial and is otherwise in compliance with the license.

SPECIAL STATEMENT
All articles published in this journal represent the viewpoints of the authors except where indicated otherwise.

INSTRUCTIONS TO AUTHORS
Full instructions are available online at http://www.wjgnet.com/2222-0682/g_info_20100722180909.htm

ONLINE SUBMISSION
<http://www.wjgnet.com/2222-0682office/>

Dissolution mechanism of calcium apatites in acids: A review of literature

Sergey V Dorozhkin

Sergey V Dorozhkin, Kudrinskaja sq. 1-155, Moscow 123242, Russia

Author contributions: Dorozhkin SV solely contributed to this paper.

Correspondence to: Sergey V Dorozhkin, PhD, Kudrinskaja sq. 1-155, Moscow 123242, Russia. sedorozhkin@yandex.ru

Telephone: +7-499-255-4460

Received: September 23, 2011 Revised: February 17, 2012

Accepted: February 21, 2012

Published online: February 26, 2012

Biostatistics, College of Medicine, Mayo Clinic, 13400 E Shea Blvd, Scottsdale, AZ 85259, United States

Dorozhkin SV. Dissolution mechanism of calcium apatites in acids: A review of literature. *World J Methodol* 2012; 2(1): 1-17
 Available from: URL: <http://www.wjgnet.com/2222-0682/full/v2/i1/1.htm> DOI: <http://dx.doi.org/10.5662/wjm.v2.i1.1>

Abstract

Eight dissolution models of calcium apatites (both fluorapatite and hydroxyapatite) in acids were drawn from the published literature, analyzed and discussed. Major limitations and drawbacks of the models were conversed in details. The models were shown to deal with different aspects of apatite dissolution phenomenon and none of them was able to describe the dissolution process in general. Therefore, an attempt to combine the findings obtained by different researchers was performed which resulted in creation of the general description of apatite dissolution in acids. For this purpose, eight dissolution models were assumed to complement each other and provide the correct description of the specific aspects of apatite dissolution. The general description considers all possible dissolution stages involved and points out to some missing and unclear phenomena to be experimentally studied and verified in future. This creates a new methodological approach to investigate reaction mechanisms based on sets of affine data, obtained by various research groups under dissimilar experimental conditions.

© 2012 Baishideng. All rights reserved.

Key words: Calcium orthophosphates; Fluorapatite; Hydroxyapatite; Dissolution; Model; Mechanism

Peer reviewer: Qing Wu, MD, ScD, Assistant Professor of

INTRODUCTION

Calcium apatites [hydroxyapatite (HA): $\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$ and fluorapatite (FA): $\text{Ca}_{10}(\text{PO}_4)_6\text{F}_2$] appear to be of a special interest to the mankind, because natural apatites are the main source of inorganic phosphorus in nature^[1], while calcified tissues (bones and teeth) of mammals consist of ion-substituted calcium apatites of biological origin^[2-4]. Therefore, HA and FA are widely used in various aspects of human being, starting from the major source of phosphorus-containing fertilizer production and ending with various biomedical applications, for example, using as artificial bone grafts. The latter resulted in a great number of research papers published on calcium apatites and related calcium orthophosphates^[5-7]. Since the chemical nature of natural phosphate ores and the inorganic phase of bones and teeth is almost the same, such different processes as fertilizer production, dental caries, osteoporosis, as well as both *in vitro* and *in vivo* biodegradation of artificial bone grafts might be simulated by dissolution of chemically pure calcium apatites (HA and FA) in acids. Therefore, establishing of the true dissolution mechanism of calcium apatites in acids appears to be of the paramount importance for our species.

In chemistry, a reaction mechanism is the step by step sequence of elementary reactions by which the overall chemical change occurs^[8]. Regarding the dissolution process of calcium apatites in acids, eight models have been already proposed to explain the processes

involved. These models already provided the important information about the factors associated with solution (pH, composition, saturation and hydrodynamics), bulk solid (chemical composition, solubility, particle sizes) and surface (defects, adsorbed ions, “history”, phase transformation) of the apatite crystals. These findings cannot be underestimated because they have already made a significant impact on understanding of the medical aspects of both dental caries and osteoporosis, as well as they created the necessary fundamentals for fertilizer production industry. Nevertheless, there are still a lot of elements missing in the overall explanation for the processes involved.

To clarify possible directions of further investigations on apatite dissolution, a critical analysis of currently available models has been made in this review followed by an attempt to combine the data available into a general dissolution mechanism. This creates a new methodological approach to investigate reaction mechanisms based on sets of affine data, obtained by various research groups under dissimilar experimental conditions.

CRITICAL ANALYSIS OF THE DISSOLUTION MODELS OF CALCIUM APATITES

Diffusion (or transport) and kinetically (or surface) controlled models

A diffusion (or transport) and a kinetically (or surface) controlled^[9-30] dissolution models, as well as the two-site model^[15,31-33], are devoted to comparison of transport rates of chemical reagents (H^+ and anions of acid) from bulk solution to the surface of apatite crystals and those of products (Ca^{2+} , F^- and orthophosphate anions) obtained backwards with the kinetics of chemical interactions on the crystal surface. According to the diffusion-controlled and two-site models, a transport of either the chemical reagents and/or the products of chemical reactions mainly determine the overall dissolution rate, whereas the kinetically controlled model emphasizes chemical transformations on the surface as the limiting factor (Figure 1)^[34]. An important consequence of the two types of rate-controlling mechanism is that the solution immediately next to the crystal surface is undersaturated with respect to apatite in the surface controlled process and this solution is saturated in the diffusion-controlled process^[35]. Both models usually operate with a so-called “driving force” which means either a concentration gradient within the Nernst diffusion layer (the diffusion controlled model) or a gradient of ionic chemical potentials between the apatite crystal surface and bulk solution (the kinetically controlled model).

To investigate whether a dissolution process follows either of these models, one should study the influence of hydrodynamics, concentration of reagents, ionic strength, solution undersaturation, pH, temperature, crystal dimensions and the presence of chemical modifiers on the dissolution kinetics. A rotary disk^[10,13,14], constant composition^[9,16,18,19,20,36-38] or dual constant composition^[22,38,39]

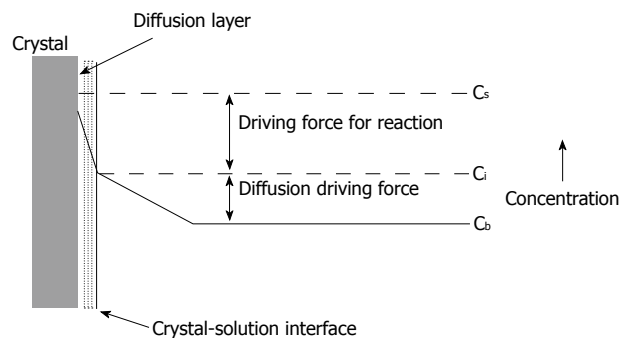


Figure 1 A dissolution process according to the diffusion and kinetically controlled models. C_s : Solute concentration on the surface; C_i : Solute concentration on the interface; C_b : Solute concentration in bulk. Reprinted from Ref.[34] with permission.

techniques are used for experimental investigations. The results obtained are usually plotted as an uptake of H^+ ions (e.g., as a titrant volume added) and/or a release of calcium, orthophosphate and fluoride ions versus the dissolution time. Afterwards, calculations of the numeric values for activation energy, rate constants, effective reaction order, diffusion layer thickness, characteristic adsorption impedance, diffusive jump distance, *etc.*, are performed^[9-33,36-40]. The conclusion on whether a dissolution process is kinetically or diffusion controlled is made based on the numeric values calculated. For example, when analysis of the rate data gave a numeric value of the effective reaction order $n = 6$, a surface controlled dissolution mechanism was suggested^[22].

Basic thermodynamic principles predict that dissolution rates should increase with increasing driving force or chemical potential; however, the experimental studies show that this dependence is complex. Namely, dissolution of apatite in some cases was found to be diffusion controlled^[19,20,23,25], in some other cases - kinetically controlled^[21,22] and even intermediate (i.e., both kinetically and diffusion controlled) in still other cases^[14]. Furthermore, the dissolution process might be composed of two stages: the first one was found to be both surface and diffusion controlled, while the second one was an exactly diffusion-controlled dissolution^[24]. Therefore, the results obtained for these models are valid within the experimental conditions studied only; no extrapolation can be made outside the ranges studied. For example, after, say, an agitation decreasing or temperature increasing, an initially kinetically controlled dissolution might be controlled by diffusion^[30].

Furthermore, in some cases, dissolution curves (a titrant volume against time) reach plateaus prior to complete dissolution of HA, thus indicating a creation of metastable states in which the reaction is effectively terminated even though apatite crystals remain in contact with the undersaturated solutions^[41-53]. There is an opinion^[54] that this effect resulted from a false solubility product value for HA. Thus, a high sensitivity to the experimental conditions appears to be the main drawback of these models.

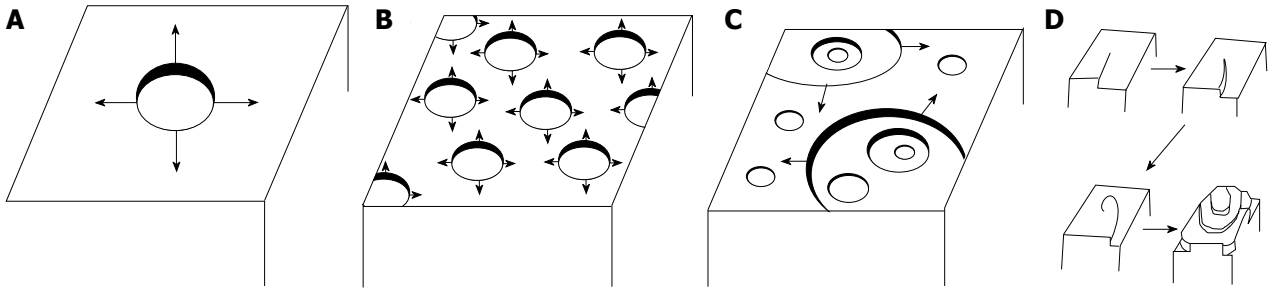


Figure 2 A dissolution process according to the mono- and polynuclear models. A: Mononuclear model; B: Polynuclear model in one crystal step; C: Polynuclear model in multiple steps: birth and spread; D: Spiral model. Reprinted from Ref.[34] with permission.

Mono- and polynuclear models

The surface dissolution may be described by three different models shown schematically in Figure 2. As may be seen in Figure 2A it is possible to start dissolution from one center from which originates the units detachment leading to step disintegration. This is a mononuclear dissolution. It is also possible that detachment takes place simultaneously from multiple centers (Figure 2B and C) which may be developed in one or more steps on the crystal surface. This is a polynuclear dissolution. Alternatively, it has been suggested that the crystal units' detachment takes place along spirals originating from an active site on the crystal surface following an Archimedean spiral (Figure 2D). The unit detachment along the spirals takes place at constant velocity^[34].

A polynuclear model^[55-64] was created from the study on apatite dissolution and growth kinetics under the constant composition conditions. Polydispersed samples of apatite were put into a stirred undersaturated (for dissolution experiments) or supersaturated (for those on crystal growth) solutions and the solution pH and amount of chemicals added (an acid for the dissolution experiments and a base for those on crystal growth) were permanently recorded as functions of time. The results obtained were plotted versus either undersaturation or supersaturation values: straight lines were obtained in the specific logarithmic coordinates typical for this model^[63]. According to this model, dissolution nuclei, i.e., collections of vacant sites for Ca^{2+} , PO_4^{3-} and OH^- ions, are formed on the crystal surface of apatite and spread over the surface with a definite lateral rate^[56].

In polynuclear model, the nucleation rate is assumed as a function of the mean ion activity. A lateral growth rate of the nuclei is assumed proportional to the difference between the total concentration of calcium ions in the saturated solution and in a solution, while the rate constant is related to the frequency for calcium ions to make a diffusion jump into a kink and, simultaneously, partly dehydrate^[62,63]. Investigations on apatite dissolution and crystal growth using atomic force microscopy revealed that the rate-determining step was not the diffusion but two-dimensional surface nucleation^[66,67]. These observations provided a valuable support for the polynuclear model.

The experimental data on dissolution and growth

rates versus undersaturation ($S < 1$) and supersaturation ($S > 1$) values, respectively, were obtained. Numeric values of surface tension (40 mJ/m^2 for apatite dissolution and 100 mJ/m^2 for apatite growth^[62,63]), ionic frequencies to enter or leave a kink ($1.6 \times 10^5/\text{s}$ ^[61]), the mean distance between kinks in a surface nucleus (approximately 3.07 \AA ^[60]) and the critical nuclei for both HA ^[55-59,62,63] and FA ^[60,61] were calculated. Furthermore, within $5.0 < \text{pH} < 7.2$ the dissolution kinetics was found to follow the polynuclear model, while that of growth appeared to follow the polynuclear model within $5.5 < \text{pH} < 6.5$ and the combined mono-polynuclear model at $\text{pH} = 5.0$ ^[60,61].

A new idea about hydroxide ions formation at the hydroxide sites of HA from water molecules trapped under the crystal surface appeared in the most recent papers of this series^[62,63]. Probably, this might be a reason for the above changing in the growth model found for HA at $\text{pH} = 5.0$. To conclude, the polynuclear model seems to be better elaborated among others because it is valid for apatite dissolution within solution pH of 5.0-7.2, saturation degrees of $0.1 < S < 7$, and Ca/P molar ratios of 0.1-20^[63]. However, nothing has been published on a validity of this model in more acidic solutions.

Self-inhibition (calcium-rich layer formation) model

A model with a self-inhibition layer formation describes a formation of a calcium-rich layer on the surface of apatite during dissolution^[19,49-53]. This model was created from the results on dissolution kinetics of apatite powders in acidic buffers at solution pH within 3.7-6.9 (the constant composition technique was used). Following concentration of calcium and solution pH, the authors found that during the initial period (2-5 min) of dissolution release of calcium into the bulk solution was always less when compared with consumption of H^+ . When dissolution progressed, rates of calcium release permanently increased and hydrogen uptake decreased until the equivalence (consumption of two hydrogen resulted in release of one calcium) was reached, while the over-all rate of apatite dissolution permanently decreased^[19,49-53]. Similar decreasing of apatite dissolution rates were obtained by other research groups^[41-48,68].

According to this model, apatite is dissolved by ionic detachment of calcium and orthophosphate ions from the surface to a solution. When an initial portion of apa-

tite has been dissolved, some amount of calcium cations (presumably, in connection with anionic counter ions) is returned from the solution and adsorbed back onto the surface of apatite. The latter results in formation of a semi-permeable ionic membrane consisting of a positively charged layer containing strongly adsorbed calcium ions, i.e., a calcium-rich layer is formed^[19,49-53]. An indirect confirmation of the presence of a calcium-rich layer was obtained in the most recent paper of this series: for initial strong calcium undersaturation in solutions, attainment of a pseudo-steady state was very long^[53]. The areas per adsorbed single PO_4^{3-} and Ca^{2+} ions on HA surface at the point of zero charge (pH = 8.5) were estimated to be 33.1 ± 2.7 and $23.0 \pm 2.1 \text{ \AA}^2$, respectively^[69].

The authors of calcium-rich layer formation model suggested that the rate control of apatite dissolution was diffusion of calcium and/or orthophosphate ions through an interfacial surface layer formed during the initial portion of the dissolution process. This interface would be composed of the Nernst layer that would be adjacent to the calcium-rich layer. This last one would present low permeability making the dissolution process slower^[19,49-53]. It is important to notice that these conclusions were made from the experiments on following calcium concentration and solution pH only; no measurements of the surface composition of apatites were performed.

As said by this model, ionic diffusion in solution results in a situation when ionic concentration near the surface layer of apatite is always higher than that in the bulk solution. Calcium concentration in the solution is also inhomogeneous: it decreases when the distance from the liquid/solid interfaces increases^[19,49-53]. Therefore, the calcium-rich layer appears to be undoubtedly rich in calcium when compared with the bulk solution only. However, when compared with the bulk of solid apatite (Ca/P = 1.67) this layer appears to be calcium-rich (Ca/P > 1.67) when the counter anions A^{n-} (it is assumed, that apatite is dissolved in acid H_nA , where A^{n-} is an anion) adsorbed from the solution are not taken into account. If the counter anions are calculated, a numeric value for Ca/(P+A) molar ratio on the surface will be around 1.67 in the case of zero charge on the surface.

On the other hand, ions of calcium might be adsorbed without the counter anions. This results in an electrical double layer formation on the solid/liquid interface with positive charge on apatite. Indeed, apatite is charged positively in acidic solutions. This effect was explained by adsorption of either protons only^[70] or protons and calcium cations from the solution^[71,72]. Certainly, the presence of a positive charge on apatite surface is in favor for the calcium-rich layer model but one should not forget that this charge might be caused by adsorption of protons only^[70]. The dissolution rate reduction found by the authors and explained by the state of the interface (adsorption of calcium^[53]) might also be explained by adsorption of some impurities those always present in the solution. Other explanations are also

available^[41-48]. Thus, unless the direct measurements of the calcium content on the surface are made, this model cannot be considered as experimentally proven.

A contradiction between the calcium-rich layer formation and polynuclear models can be outlined: sorption of calcium is likely to happen on the dissolution nuclei. In this case, some amount of the nuclei should disappear, as a result. No suggestions how to overcome this contradiction were found in the references.

To conclude this model, one should notice that due to the formation of a calcium-rich layer, a non-stoichiometric (incongruent) dissolution (see the next model) is suggested by default.

Stoichiometric/non-stoichiometric (congruent/incongruent) dissolution

A congruent/incongruent (or stoichiometric/non-stoichiometric) dissolution^[11,17,19,21,40,50,68,73-90] is based on the direct measurements of either the ionic concentrations in a solution^[19,21,40,68,74-76,80,83,84,87,88,90] or the surface composition of apatites during dissolution^[17,77,81]. According to the definitions, ions of a solid might be dissolved either simultaneously with the dissolution rates proportional to their molar concentrations (a congruent dissolution) or non-simultaneously with different values of the dissolution rates for each ion (an incongruent dissolution). The latter case always results in a situation when a surface layer with a chemical composition different from that of the bulk of solid is formed.

For acidic dissolution of FA, ions of F^- were found to dissolve faster (or in a greater ionic proportion) when compared to ions of calcium and orthophosphate^[17,68,77,83,88,89]. A similar phenomenon of faster (or in a greater ionic proportion) dissolution of calcium when compared to that of orthophosphate was also found^[40,75,76,79-82,90]. In the latter case, a surface layer of acidic calcium orthophosphates, presence of HPO_4^{2-} ions and/or Ca-depleting of the surface were either suggested^[52,61,85] or found^[81,86,88,89]. Thus, if incongruent dissolution occurs from a stoichiometric HA surface, the surface Ca/P ratio will become lower than for the bulk and a Ca-deficient HA (CDHA) must then be present, even if there is no phase change^[54]. However, there are contradictory results. For example, when FA was dissolved, the solution concentrations of calcium and fluoride ions were non-stoichiometrically lower with respect to that of orthophosphate ions due to a possibility that some amount of sparingly soluble calcium fluoride was precipitated^[40,86,88-94]. Furthermore, one should mention on a study, in which release of calcium into the bulk solution was always less, when compared with release of orthophosphate^[68]. On the other hand, having followed the release kinetics of calcium and orthophosphate ions into solution, apatites were found to dissolve stoichiometrically (congruently)^[21,73,95].

Interestingly, but apatites might be dissolved stoichiometrically or non-stoichiometrically depending on the experimental conditions. For example, CDHA was found to dissolve congruently at the solution pH < 4.5,

while an incongruent dissolution with Ca/P ratio in solution attaining values as high as about 25 was detected in solutions within $4.5 < \text{pH} < 8.2$. Furthermore, almost negligible dissolution with another type of a non-stoichiometry with Ca/P ratio close to zero in solutions was found at solution $\text{pH} > 8.2$ ^[87]. For $4.5 < \text{pH} < 8.2$ conditions, the authors explained the incongruent dissolution by re-adsorption of already dissolved orthophosphate anions from the solution onto the positively charged CDHA surface. While in more basic solutions, the surface of CDHA was charged negatively and, thus, the authors suggested a possibility of both re-adsorption of already dissolved calcium cations onto CDHA surface and desorption of orthophosphate ions from the CDHA surface. However, it has to be realized that at solution $\text{pH} > 8.2$ the uncertainties in the chemical analysis of Ca (in particular) and P were relatively high, making any quantitative interpretation of this re-adsorption/desorption difficult^[87]. The same effect was discovered in another study^[89]. Furthermore, dissolution of both FA and natural sedimentary carbonated FA was found to be incongruent in the early stages but tended toward congruency as the dissolution reaction proceeded to steady state^[40,68,96]. According to the authors, this initial incongruency was likely a result of the exchange of solution H^+ ion for mineral bound Ca^{40} . Besides, a presence of simple inorganic salts (Na_2SO_4 , CH_3COONa or NaCl) in solution appeared to have an influence on the equilibrium concentrations of orthophosphate and calcium ions released from apatite: the order of salts increasing orthophosphate in solution was $\text{Na}_2\text{SO}_4 > \text{CH}_3\text{COONa} > \text{NaCl}$, while that increasing calcium was opposite^[84]. This effect was explained by a specific affinity of some ions (e.g., sulfate) for apatite and might be a reason for transition of congruent to incongruent dissolution in some cases^[92-94,97]. Similarly, presence of other compounds might influence the dissolution congruence^[98]. Other reasonable explanations might be due to either experimental difficulties in precise following of Ca/P ratio both in the solution and on the crystal surface or differences in chemical and structural compositions of apatites studied by different researchers (both FA and HA are known to be often non-stoichiometric and calcium-deficient, especially on the surface^[2-4,87-89,99]).

The idea on a great influence of a surface layer is supported by the data on dissolution of stoichiometric HA ($\text{Ca/P} = 1.67$) in aqueous solutions within $\text{pH} 4.90-9.94$ ^[76]. The authors found that after removal of an irreversible surface, which generated excessive calcium and orthophosphate solution concentrations, further behavior of HA became reproducible. A surface of one atom-layer thickness or less was believed to have formed during the preparation of the solid^[76]. On the other hand, dissolution of HA in aqueous medium appeared to be always non-stoichiometric at the beginning, but when the solid was successively equilibrated at any given pH , the solution Ca/P ratio approached a limiting value of 1.67. Once this value was reached, the solid only



maintained this solution ratio by dissolving stoichiometrically^[76]. The authors explained these phenomena by a previous history of the samples studied. A similar conclusion was also made in another paper^[74]. Thus, the experimental techniques of apatite preparation might have a great influence to stoichiometry/non-stoichiometry of dissolution. This is a serious drawback.

Finally, the results on theoretical analysis of surface layer formation on HA should be reported^[85]. The main point of that paper is an idea that both the stoichiometric HA ($\text{Ca/P} = 1.67$) and any non-stoichiometric CDHA (Ca/P ratio within 1.5-1.67) might be described as the same substance. More precisely, there is a continuous amount of intermediate compounds within $1.5 \leq \text{Ca/P} \leq 1.67$ having the same crystal structure which is drawn as a line on the solubility diagram $\text{CaO} - \text{P}_2\text{O}_5 - \text{H}_2\text{O}$ ^[85]. Furthermore, according to the authors, at the steady state, both HA and CDHA are dissolved congruently only when both the solution and solid have the same Ca/P ratio. Therefore, any sample of HA and CDHA is dissolved incongruently except the only one solution composition having the similar Ca/P ratio with that particular sample. In all other cases, a surface layer having a Ca/P ratio less than 1.67, which is often used as the indication of incongruent dissolution of apatite, will form as a result (this, however, depends on the accuracy with which the analyses can be made)^[85]. Thus, whether apatites are dissolved congruently or incongruently might also depend on both their initial chemical composition and the solution properties.

To conclude, one should notice that all the aforementioned cases of incongruent dissolution of both FA and HA describe the formation of a surface layer of a CDHA and/or acidic calcium orthophosphates, which is calcium-depleted when compared to the bulk apatite. Thus, there is a disagreement between the incongruent dissolution and calcium-rich layer formation model. Perhaps, this might be due to the differences in experimental conditions.


Chemical model

A chemical dissolution model was proposed as well^[100-102]. This model was developed from a self-evident supposition that it would be highly unlikely if apatite were dissolved by detachment of "single molecules" equal to the unit cells and consisting of 18 ions. Moreover, in the crystal lattice all ions are shared with neighboring unit cells and often cannot be attributed to the given "single molecule". Therefore, based on the experimental results obtained on the one hand and an analysis of the data found in references on the other hand, a sequence of four successive chemical reactions:




was proposed to describe the chemical processes of apatite dissolution^[100-102]. According to this model, equations

(1)-(4) should be used instead of the well-known net-reactions (5) and (6):



Chemical model (1)-(4) was initially created for description of apatite dissolution in strong acidic media^[101] and appeared to be a further development of some ideas proposed earlier. For example, already in 1960s reactions (5) and (6) had been suggested “not to give the mechanism but merely express net-reactions only”^[103]. Later, Pearce^[104] and Chow^[135] discussed which of net-reactions (5) or (6) described the dissolution process better. For acidic dissolution of apatites, net-reaction (5) represents the direct chemical interaction between the surface of solid apatite and an acidic solution. However, Pearce suggested that, in principle, the dissolution process might also happen according to net-reaction (6) followed by a chemical interaction in the solution among the ions of apatite and acid *near* the crystal surface^[104]:



In spite of a lack of the experimental techniques, able to follow the detachment of single ions, a reasonable ionic description of apatite dissolution as a system of chemical equations (1)-(4) was created from the indirect measurements^[100-102]. According to this model, chemical dissolution of apatite occurs step by step on the surface *via* intermediate formation of a mono-atomic layer of some virtual compounds, like $\text{Ca}_3(\text{PO}_4)_2$ and CaHPO_4 ^[100-102]. Both latter substances are known as precursors of apatite formation during chemical crystallization^[3,105]. Moreover, based on the sequence of ionic detachment (first fluorine for FA or hydroxide for HA, followed by calcium and afterwards by orthophosphate) it is suggested that dissolution of apatites is always incongruent (non-stoichiometric) at the atomic (ionic) level. However, a lack of the precise experimental verification transforms the chemical model into a reasonable hypothesis only.

To conclude this model, one may assume that some new relations between the kinetically controlled and chemical models might be established in future. Before the chemical model was created, chemistry of apatite dissolution had been always described by equations (5) or (6) + (7). For this reason, the kinetically controlled model was also adapted for these equations. For example, the overall rate constants for net-reactions (5), (6) and (7) are still used for calculations, whereas they are probably equal to either the lowest of the rate constants of (1)-(4) (the rate determining step) or some combination.

Etch pit formation

A process of etch pit formation describes acidic dissolution of apatite crystals containing structural defects (dislocations and inclusions)^[41-48,96,106-115]. A radius of dislocations outlets (hollow cores) on apatite was calculated to be within 8.3-20 Å for screw dislocations and 18-43 Å for edge ones^[109]. The presence of dislocations accelerates dissolution, because dislocations give rise to con-

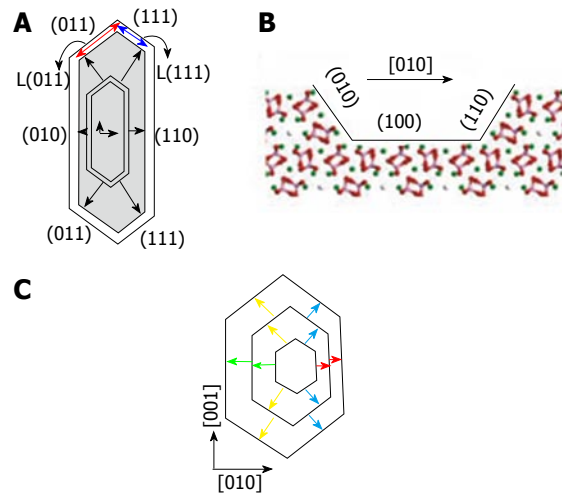


Figure 3 A typical etch pit on the surface of calcium apatites. A: Top view and a model of its evolution during dissolution. Arrows represent relative step velocities displaying different facets; B: View through the [001] direction in the (100) surface. The exposed step faces can be seen to be un-equivalent owing to the opposite orientations of the orthophosphate groups. Reprinted from Ref. [118] with permission; C: Schematic of the evolution of hexagonal etch pits. Four differently colored arrows represent relative step velocities. Reprinted from Ref. [120] with permission.

tinuous steps on the surface (Figure 2D) and the strain energy they cause in crystals favors etch pit formation. Thus, the dissolution process of solids is induced by formation of pits (Figure 3) and continues with spreading of their stepwaves^[116,117]. As a result, the surface of apatite becomes rough and the total edge length and edge free energy increases^[41-48]. These pits provide dissolution sites and the entire reaction proceeds *via* nucleation and growth of the pits accompanying step flow. The pits appear at the dislocation outlets, usually they are 0.1-10 μm in size (their dimensions depend on dissolution kinetics and dissolution time: they increase when the dissolution progresses; furthermore, the crystals must be sufficiently big to provide enough room for large pits to form). The walls and bottom of etch pits consist of crystal faces possessing the highest dissolution rates, which allow them to grow. However, the growth kinetics of etch pits (therefore, the dissolution process of apatites in general) might be suppressed by addition of very simple chemicals, such as NaCl. This phenomenon might be attributed to a competition for surface protonation sites between Na^+ and H^+ ions.

For dissolution of apatites, the pits usually have a hexagonal shape (Figure 3) according to the crystal symmetry $\text{P6}_3/\text{m}$ of pure HA and FA^[106-111,118-123]. However, their shape might be different (e.g., triangular) when specific ions (e.g., fluoride) are present in a solution^[121]. It is important to mention that the growing process of etch pits might be inhomogeneous: movement of the dissolution steps on one side of any single pit might be faster or slower their counterparts on the other side, suggesting the formation of asymmetric pits, as schematically shown in Figures 3A and D. Concerning height of the steps, it appears to depend on both crystal faces and dissolution

conditions. For example, for an HA (100) surface exposed to deionized water, the average height of each step was found to be 0.84 ± 0.1 nm, which is close to the interlayer distance of the (100) surface [$d(100) \approx 0.82$ nm]. Furthermore, it remained constant during dissolution^[120].

The formation of etch pits on the crystal faces is the driving force for dissolution. However, in the case of nearly physiological conditions and sufficiently low solution undersaturation, a free energy barrier becomes too high for vacancy nucleation to occur on a time scale that is competitive with other processes. Thus, the dissolution process of apatites becomes spontaneous only when etch pits of critical sizes (determined by the Gibbs-Thomson effect, a well-known thermodynamic principle) are reached^[41-48]. At this critical size, the free energy change goes through a maximum that defines an energy barrier to a pit formation. Therefore, only relatively large pits (of sizes greater than a critical value) appear to be active, with stepwaves contributing to dissolution, while the spreading velocities are also dependent on the pit sizes, decreasing with pit size decreasing. Moreover, during dissolution, the crystals become smaller and the average lengths of dissolution steps decrease (which leads to a decrease in dissolution rates) and approach the critical value. When dimensions of dissolving crystals is sufficiently reduced, in some cases dissolution is thought to be dynamically stabilized (dissolution suppression) due to a lack of space for active pits/defects formation on the very small crystallite surfaces^[41-48]. This phenomenon involves particle-size-dependent critical conditions of energetic control at the molecular level. Although, the authors claim this effect as “a new dissolution model incorporating particle size considerations”^[41-48], in fact, they just have introduced some boundary conditions (the minimal pit sizes and crystal dimensions) to the etch pit formation process. One should remind, that a similar effect of the dissolution self-inhibition was detected by the authors of the calcium-rich layer formation model^[19,49-53], although the interpretation of this effect was quite different (see above).

Different acids were used in experimental investigations but, unless the conditions of surface coating creation^[124], no specific influence of the acids to etch pit formation and growth was found^[106-115]. A theoretical basis for the pit formation and growth at the surface outlets of dislocations includes detachment of single ions from the kink sites. The bulk rate associated with dissolution stepwaves arises quite naturally from the equations describing the spreading of step trains from structure defects and densities^[43]. However, until recently, the experimental investigations on pits formation and growth on apatites were made when their dimensions became at least 0.3-0.5 μm and even larger. Smaller dimensions of pits were out of the range of old microscopes. That is why, the initial stages of etch pits formation are not quite clear yet.

The investigations on apatite dissolution using atomic force microscopy provided new data on this point^[41-48,66,67].

^[118-122]. For example, the growth process of a single pit on apatite was followed since its dimensions were 50 nm^[66,67]. Therefore, one may expect new results on even smaller dimensions of pits to appear soon.

Ion exchange model

An ion exchange dissolution model is based on a supposition about adsorption of protons^[40] and anions of acid (e.g., citrate anions^[125-127]) from a solution onto the surface of apatite and removing ions of calcium and orthophosphate into the solution instead. An uptake of citric acid^[125] and citrate ions^[126] from dilute (4-12.5 mmol/L for citric acid^[125] and 0.05-1 mmol/L for sodium citrate^[126]) aqueous solutions by a synthetic HA was found to be time independent and follow *Langmuir* isotherms rather good. However, it was not the case when solutions of higher concentrations were used. In more concentrated solutions (13-100 mmol/L of citrate), this interaction was “reactive” and not “adsorptive”^[125].

Adsorption was found to take place by ionic exchange of orthophosphate by citrate ions at the solid-solution interface, caused by a higher affinity of citrate than orthophosphate species for the Ca-sites on the surface. Citrate ions were proposed to interact in two ways: $\text{C}_6\text{H}_8\text{O}_7^{3-}$ interacted weakly in a bi-dentate manner (1 citrate per 2 calcium sites), whereas $\text{C}_6\text{H}_9\text{O}_7^{2-}$ interacted strongly in a mono-dentate manner (1 citrate per 1 calcium site)^[126]. Recent computer simulations revealed that this process is followed by hydrogen-bonded interactions of citric acid to surface oxygen ions of apatites^[128]. Furthermore, the adsorbed citrate molecules can use their free carboxylate and hydroxyl groups to self-assemble on the HA surface *via* intermolecular hydrogen bonding^[129].

Later this model was updated by investigation of apatite dissolution in other acids and an adhesion-decalcification concept was introduced^[130,131]. According to this concept, the mechanism of acidic interaction with HA was found to involve two phases. In the first phase, an acid bonds to surface calcium of HA with formation of calcium-acid complexes. Depending on both a solubility and a diffusion rate of the calcium-acid complexes from the HA surface to a solution, the acid will in the second phase either remain attached to the HA surface with only limited decalcification involved or the calcium-acid complexes will detach, resulting in a substantial decalcification effect. Rather similar data, in which carboxylic groups of polyalkenoic acid were adsorbed on the surface of an HA substrate, replaced orthophosphate ions and made ionic bonds with calcium ions of HA, were obtained in another study^[132].

Recently, *ab initio* total energy methods were used to study the atomic structure and surface chemistry of HA^[133]. All surfaces of HA were found to react strongly with water and a loss of Ca from the surface in exchange for two H appeared to be very favorable. Since these calculations were performed for the case of water adsorption on HA, it remained unclear whether they can be applied to the acidic solutions. Nevertheless, other

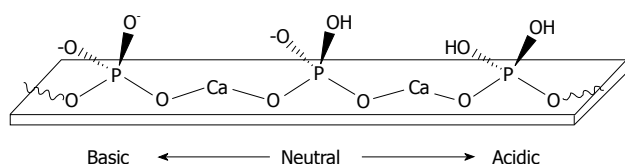


Figure 4 A schematic representation of surface protonation of apatites at different solution pH. Reprinted from Ref. [119] with permission.

researchers found this effect experimentally^[86,88]. Furthermore, another type of the exchange was proposed for HA, in which one calcium and one hydroxyl were replaced by one proton^[87].

To conclude this model, the time independent ionic exchange of orthophosphate by citrate was detected in dilute solutions only. In more concentrated solutions it transferred into chemical reaction (5) followed by time dependent precipitation of calcium citrate when its solubility was exceeded^[125,127]. Application of this model to HA dissolution in other acids revealed its dependency on both the solubility and the diffusion rate of the calcium-acid complexes^[130,131]. Thus, new experimental data are necessary, to elaborate the ion exchange model further.

Hydrogen catalytic model

A hydrogen catalytic model is based on a reasonable suggestion about adsorption of protons onto negatively charged oxygen ions of the surface orthophosphate groups of apatites^[134]. Sorption of protons results in partial transformation of surface PO_4^{3-} groups into HPO_4^{2-} and catalyses the dissolution process^[9,10,15,18,20,53-61,89]. A schematic representation of this process at different solution pH is shown in Figure 4^[119]. Besides, recent computer simulations revealed that both OH^- (for HA) and F^- (for FA) located on the surface are protonated as well and, of them, fluoride ions exhibited much lower proton affinities ($\text{pK}_\text{B} = 10.8$, a weak base) compared to hydroxide ($\text{pK}_\text{B} = 0$, a strong base)^[135]. Furthermore, the surface protonation of apatites is intimately related to hydrogen bonding. The details on the latter process are available in literature^[136].

One can notice, that the authors of different dissolution models (the diffusion and kinetically controlled^[9,10,15,18,20] and polynuclear^[56-61] models) have suggested a similar possibility of a catalytic effect of the adsorbed protons. At present, indirect data only are available to support this hypothesis. Namely, at neutral pH, dissociation of ions is penalized by more than 150 kJ/mol giving rise to very stable apatite-water interfaces^[135]. This picture changes drastically with decreasing pH, as the protonation of orthophosphate and hydroxide ions lowers the free energy of calcium ions dissociation. An obvious trend in apatite dissolution is that the dissolution rate is increased as the solution pH decreases, which is a general phenomenon observed in dissolution of other minerals. This indicates that dissolution proceeds by surface protonation, which promotes breaking of Ca-O bonds.

In the course of proton uptake, the charge of the surface anions is reduced and the Coulomb attraction to the crystal surface is lowered considerably, which might be considered as “catalysis”. Currently, no precise information about a catalytic activity of adsorbed protons on the dissolution of apatites is available. However, it does not mean that this effect does not exist. Up to now, nobody has ever succeeded to reveal a catalytic effect unambiguously due to a lack of an experimental technique able to provide the experimental data necessary. Obviously, the general idea on a catalytic activity of the adsorbed protons seems reasonable and, perhaps, this effect will be better elucidated in future.

SUMMARY ON THE DISSOLUTION MODELS

There is an old tale on six blind men, who wanted to determine what an elephant looked like. An elephant was delivered and the men were allowed to feel different parts of its body. The blind man who felt a leg said the elephant was like a pillar; the one who felt the tail said the elephant was like a rope; the one who felt the trunk said the elephant was like a tree branch; the one who felt an ear said the elephant was like a hand fan; the one who felt the belly said the elephant was like a wall; and the one who felt the tusk said the elephant was like a solid pipe. Thus, six blind men appeared to be in complete disagreement. Then, a wise man explained to them: “All of you are right. The reason every one of you is telling it differently is because each one of you touched the different part of the elephant. So, actually the elephant has all the features you mentioned.” The story is widely used to indicate that the reality may be viewed differently depending upon one’s perspective, suggesting that what seems the absolute truth may be relative due to a deceptive nature of half-truths.

As the complete physical picture that explains widely observed variations in dissolution behavior is still lacking, a similar approach must be adapted to the aforementioned dissolution models of calcium apatites. Undoubtedly, each from the aforementioned models appears to have limitations and drawbacks of its own and none of them is able to describe the apatite dissolution in general. Moreover, most of the models were elaborated for apatite dissolution in either slightly acidic or nearly neutral ($4 < \text{pH} < 8$) aqueous solutions, relatively small values of solution undersaturation and temperatures of 25 °C and 37 °C only. Nothing is known about the validity of these models for apatite dissolution in strong inorganic acids (HCl , HNO_3 , H_2SO_4 , H_3PO_4) for solution $\text{pH} < 2$ and temperatures above 70 °C. Moreover, in such “tough” experimental conditions, the numerical value of solution undersaturation by HA and FA becomes uncertain due to impossibility to determine their solubility^[1-4]. The latter cases serious problems for application of current versions of calcium-rich layer formation and polynuclear models to apatite dissolution in strong acids, because both models operate with the solution supersatura-

tion/undersaturation phenomena. The abovementioned “tough” dissolution conditions are common in industry of fertilizer production^[137] and have to be taken into account by the final version of any dissolution model.

However, there are no doubts that each of the models discussed is correct for the specific experimental conditions studied. The different models are just devoted to diverse aspects of the same process of apatite dissolution and are likely complement each other. Undoubtedly, the dissolution process of calcium apatites has all the features elaborated within eight dissolution models. Unfortunately, it is still impossible to obtain the complete understanding for all the processes involved because experimental techniques able to provide direct following after diffusion, sorption, detachment and transformation of the single atoms, ions and molecules currently are lacking. Therefore, researchers are still forced to make conclusions about the events happening at the atomic (ionic) level based on indirect measurements and/or calculations only. That is why, combining the experimental and theoretical findings, obtained by different investigators (often under hardly comparable experimental conditions), currently, seems to be the only way to create a general depiction of the dissolution mechanism of calcium apatites in acids.

A REASONABLE CLASSIFICATION OF THE DISSOLUTION MODELS

At the fundamental level reactions between solids and liquids involve a coupled sequence of mass transport, adsorption/desorption phenomena, heterogeneous reaction, chemical transformations of intermediates, *etc.*, whose identification, separation and kinetic quantification are all necessary if the mechanism of the process is to be fully understood and described^[138]. It is also generally agreed that during dissolution lattice ions undergo the following processes: (1) detachment from a kink site, (2) surface diffusion away from the crystal steps, (3) desorption from the surface and (4) diffusion into the bulk solution^[139]. Therefore, the steady-state conditions of apatite dissolution in aqueous acidic media include the following simultaneous processes or steps: (1) diffusion of chemical reagents (H^+ and anions of acid A^n) from bulk solution to the solid/liquid interface; (2) adsorption of the chemicals onto the surface of apatite; (3) chemical transformations on the surface; (4) desorption of products (ions of fluoride, calcium and orthophosphate) from the crystal surface; and (5) their diffusion into the bulk solution.

All the steps mentioned above are likely to be much more complicated. For example, processes 1 and 5 include chemical transformations happen with the ions during diffusion, because solution pH is known to depend on the distance from the solid/liquid interface (in acidic solutions it is higher near the surface of apatite and decreases when the distance increases)^[140,141]. Processes 2 and 4 include ionic diffusion along the surface

both to (step 2a) and away from (step 4a) the crystal steps, respectively, as well as a diffusive jump (steps 2b and 4b)^[139]. Finally, process 3 consists of several successive chemical transformations [step 3a - chemical equations (1)-(4)]^[100-102] and includes ionic detachment from the kink sites (step 3b)^[139]. Moreover, for adsorption (step 2) to take place, the following intermediate steps are necessary: (1) dehydration of a surface site; (2) partial dehydration of ions; and (3) a diffusive jump toward the surface^[139]. One can also expect three similar intermediate steps (diffusion jump from the surface, hydration both the ions and the surface site) for desorption (step 4).

As shown above, different models describe just diverse aspects of the same phenomenon of apatite dissolution. Commonly, the main distinction is made between the transport control and surface-reaction control. For example, in the diffusion controlled, two-site and polynuclear models steps 1 and 5 limit a reaction rate. On the contrary, in the kinetically controlled, chemical and hydrogen catalytic models a reaction rate is limited by step 3. In the cases of the ion exchange and self-inhibition (or calcium-rich layer formation) models, a reaction rate is likely to be controlled by both ionic diffusion (steps 1 and 5) and kinetics of the adsorption/desorption phenomena (steps 2 and 4). Processes of etch pit formation and dissolution stoichiometry - are the experimental facts, not models. Thus, they may be controlled by factors pertaining to any step from 1-5 and even all of them.

BRIEF INFORMATION ON APATITE STRUCTURE

Briefly, crystals of HA and FA consist of individual orthophosphate tetrahedra linked by calcium cations. The orthophosphate groups forms the skeleton having two types of calcium sites. The first [Ca(1) site] is occupied by four calcium atoms that have a nine-fold coordination, while the second [Ca(2) site] is occupied by six calcium atoms having a seven-fold coordination. Fluoride (for FA) or hydroxide (for HA) anions are located within the same channels as the Ca(2) sites and have a high mobility^[1-4,142,143]. Thus, the apatite structure contains Ca-F (for FA), O-H (for HA), Ca-O and P-O bonds; consideration of the relative electrostatic strength of these bonds suggests that their relative destruction rate is consistent with: $Ca-F \approx Ca-OH > Ca(1)-O > Ca(2)-O > P-O$. Considering its structure, once all Ca-F and Ca-O bonds are broken, apatite is destroyed; while breaking of P-O bonds is unnecessary for apatite dissolution^[96].

NECESSARY ASSUMPTIONS AND LIMITATIONS

When apatite comes into a contact with an acidic aqueous solution, dissolution steps 1-5 (see section 4) begin. Before giving the detailed description of the processes involved, the following assumptions and limitations must

be made: (1) the stoichiometric apatite ($\text{Ca}/\text{P} = 1.67$) is dissolved and neither non-stoichiometric layers nor other ions except of calcium, orthophosphate, hydroxide (for HA) or fluoride (for FA) are initially present in the crystal lattice, whereas volume and surface defects (dislocations and dislocation outlets respectively) might be present and, if present, they are distributed randomly; (2) except of the presence of dislocation outlets, the initial surface of apatite is perfect (molecularly smooth). Otherwise, each imperfection might act as a possible dissolution nucleus; (3) in spite of the limitations and drawbacks discussed above, all the afore-discussed dissolution models are correct and complementary to each other; (4) in some cases, anions of acid might have an influence on apatite dissolution due to a specific affinity (e.g., citrate) or by means of formation of insoluble compounds (e.g., sulfate, fluoride). That is why, anions are specified neither here nor below. It is just assumed that dissolution of apatite occurs in acid H_nA , where A^{n-} is an anion; (5) only soluble compounds are formed during the apatite dissolution in acids. No precipitates are obtained; (6) hydration effects for all the ions and molecules involved as well as those for crystal surface of apatite^[99,144-148] are omitted for simplicity; (7) all crystal faces of a solid apatite are equal and have a similar ionic arrangement. Although, it was found that HA (001) facets could be more resistant against acidic dissolution than (100) ones^[149], no specific influence of different crystal faces on the dissolution process is considered; and (8) since the afore-described dissolution models have been elaborated for micron-sized apatite crystals, while the nanodimensional calcium orthophosphates possess the special properties^[150,151], to eliminate the size effects, dissolution of large crystals is described. No specific influence of crystal dimensions on the dissolution mechanism is considered.

Based on these assumptions and limitations, an attempt to create the general description of the apatite dissolution mechanism at the atomic (ionic) level is given below.

CREATION OF THE GENERAL DISSOLUTION MECHANISM

Atomic (ionic) description for the perfect crystals

Immediately after being placed to acidic aqueous solutions, the surface of apatite crystals becomes in contact with water molecules and ions of the acid, which results in sorption of all these chemicals with simultaneous formation of a solid/liquid interface and various adjacent strata, such as a Nernst diffusion layer, an electrical double layer, *etc.* Transport of the chemicals (H^+ and A^{n-}) to the solid/liquid interface always happens by ionic diffusion through the Nernst diffusion layer (Figure 1). A thickness of this layer depends on both solution hydrodynamics and dimensions of the crystals dissolving: it decreases when agitation intensity increases and crystal sizes decrease. However, in no cases the thickness becomes equal to the zero^[152]. Thus, a concentration gradi-

ent is always present near the solid/liquid interface, the diffusion laws always remain valid and all findings of the diffusion-controlled model (e.g., an adsorption resistance and a diffusion jump) remain applicable for any case of apatite dissolution. A similar approach is correct for the surface phenomena: when dissolution occurs, adsorption and desorption of ions, as well as chemical transformations (1)-(4) always take place on the surface regardless the experimental conditions chosen.

After being delivered by diffusion to the solid/liquid interface, ions of H^+ and A^{n-} are adsorbed onto the surface of apatite. A great number of various surface complexes might be formed as a result^[86-89,153-155]. According to the diffusion-controlled model, there is an adsorption resistance for ions to be adsorbed onto the surface and in order to overcome the resistance the ions make a diffusive jump toward the surface to a distance corresponding to their size^[139,156]. Being charged positively, protons are adsorbed onto oxygen ions of orthophosphate groups^[58] as well as onto ions of fluoride (in the case of FA) and hydroxide (in the case of HA). After the model by Wu *et al.*^[153], the surface protonation of apatites proceeds *via* formation of $\equiv\text{POH}$ surface groups (" \equiv " stands for the surface) at $5 < \text{pH} < 7$, while apatite surfaces become fully protonated at $\text{pH} < 5$. One may expect to find some differences in the adsorption kinetics of protons onto fluoride, hydroxide and orthophosphate ions. Namely, due to a higher electro negativity of fluoride (when compared to oxygen ions of orthophosphate groups) and a higher basicity of hydroxide (when compared to orthophosphate), adsorption of protons might happen faster (or previously) onto these ions when compared with orthophosphate. However, recent results of computer simulations indicated a possibility of OH^- protonation by the nearest HPO_4^{2-} ion^[135], indicating to the fact, that orthophosphate ions might be protonated faster (or previously) if compared to that for hydroxide ions. Obviously, this topic needs to be clarified in future.

Anyway, negatively charged anions A^{n-} may be adsorbed onto calcium cations only. According to the ion exchange model, the exchange process shows an adsorption of about one anion per unit-cell of apatite^[125-127]. On the other hand, the surface of apatites is charged positively in aqueous acidic media and negatively in basic solutions (the point of zero charge is at solution pH within 6.8-8.5) with an electric double layer formation at the solid/liquid interface^[70-72,78,86-88,153-155,157,158]. The latter points out to a non-equivalent ionic adsorption of H^+ and A^{n-} onto apatite: in acidic solutions, adsorption of protons always exceeds that of A^{n-} , while in basic solutions the situation is opposite. Therefore, in acidic solutions there is at least one extra-adsorbed proton per several neighboring unit-cells of apatite when compared to the number of adsorbed anions. The fact of a non-equivalent ionic adsorption might be explained by differences in sizes and mobility between H^+ and A^{n-} ^[159]. Great difference in the surface sites available is another reason for the non-equivalent ionic adsorption. Namely,

the concentration of the lattice ions being on the surface of HA were found to be equal to 2.57, 3.02 and 4.50 ions/nm² for OH⁻, PO₄³⁻ and Ca²⁺, respectively^[69]. Furthermore, according to drawings of the apatite structure, the most part of its surface (up to 80%-90%) is covered by oxygen ions of orthophosphate groups^[160].

Ions of the crystal lattice of apatites are known to have different crystallographic positions: so-called X-ions (F⁻, OH⁻, Cl⁻ and substitutes for them) are located in Ca(2) channels parallel to *c*-axis^[1-4,142,143]. This position results in a relatively high mobility of X-ions: for example, they might be mutually substituted rather easily^[88,89,161-163] with formation of intermediate compounds, like fluorhydroxyapatites or hydroxyfluorapatites^[17,83,164]. Based on these findings, dissolution of apatite in acids was suggested to start with detachment of X-ions (more likely, as HX) from the surface^[100-102] followed by their diffusion away from the crystal steps and further into the bulk solution^[139,156]. Recent computer simulations revealed some differences in the dissolution kinetics between F⁻ and OH⁻ anions in apatites: surface fluoride is dissolved not as readily as hydroxide is^[143]. Initial leaving of X-ions was also detected in the incongruent dissolution model^[17,68,77,83,88,89]. Moreover, numerical values for the surface tension found for dissolution of HA appeared to be clearly lower than those found for HA growth (the polynuclear model). The latter data were explained by partial protonation of orthophosphate groups and missing of some hydroxide ions on the crystal surface^[60].

After detachment of X-ions from the surface, there are calcium, orthophosphate, H⁺ (as HPO₄ and/or H₂PO₄ groups) and Aⁿ⁻ ions left on it (hydration effect is omitted for simplicity). From now on, any differences between FA and HA disappear. In any cases, adsorption of protons onto calcium is impossible due to charge repulsion. Therefore, an electrical double layer with a positive charge on apatite cannot be continuous at the atomic (ionic) scale. There should be local uncharged places in it, say, at the positions of calcium cations. According to the chemical model, an interaction between calcium cations and anions of acid adsorbed from a solution is believed to happen in such places^[100-102]. This interaction results in breaking of surface ≡O-Ca bonds ("≡" stands for the surface) and detachment of some calcium from the kink sites followed by their diffusion away from crystal steps and further into the bulk solution (the diffusion-controlled model^[139,156]). Detachment of calcium might occur as calcium-acid complexes (the ion exchange model). Recent computer simulations revealed that a local excess charge of +3 and +4 must be created to cause exothermic Ca²⁺ displacement from Ca(1) and Ca(2) sites, respectively^[135]. If so, under otherwise equal conditions, detachment of Ca²⁺ ions from Ca(1) sites of the apatite surface should happen faster and/or easily than that from Ca(2) sites.

Detachment of calcium ions results in formation of dissolution nuclei. These nuclei are defined as collections of vacant sites for Ca²⁺, PO₄³⁻ and X⁻ ions on the crys-

tal surface of apatite^[56]. According to the polynuclear model, removal even of one ion might result in further dissolution because critical nuclei (x^*) were calculated to consist of 1-26 ions for dissolution of HA and 0.3-34 ions for dissolution of FA. (According to the authors, $x^* < 1$ means that there is no nucleation barrier to be overcome^[61]. Since one unit cell of apatite contains 18 ions, $x^* > 18$ means that more than one unit cell should be dissolved for a nucleus to form). The numeric values for x^* were found to depend on solution pH and solution undersaturation^[60,61]. Furthermore, due to charge repulsion, adsorbed protons (as HPO₄ and/or H₂PO₄ groups) might catalyze detachment of calcium ions from the kink sites (the hydrogen catalytic model).

After being detached, calcium cations [possibly, as calcium-acid complexes (the ion exchange model)] diffuse along the surface away from the dissolution steps before entering the solution^[139]. For dissolution of octacalcium phosphate (OCP): [Ca₈(HPO₄)₂(PO₄)₄·5H₂O] in slightly acidic (pH = 5.66) solutions numeric values for the mean surface diffusion distance of the lattice ions detached from steps were calculated. These values were found to depend on the edge free energy and be within $(17 \pm 4)\alpha - (41 \pm 10)\alpha$, where $\alpha \approx 3.7 \text{ \AA}$ is the size of a growth unit (or mean ionic diameter)^[156]. Numeric values of mean ionic diameter for apatites were also calculated. They appeared to be less than that for OCP: 3.09 Å for HA and 3.07 Å for FA^[62]. Taking into the consideration great similarities found between the chemical composition and crystal structures of OCP and HA^[165], one might assume that the numerical values of surface diffusion distance for HA should be close to the values for OCP.

Ionic detachment of some calcium results in removing of a local positive charge from apatite, which is immediately compensated by adsorption of other protons from the acidic solution. This conclusion is based on the surface charge measurements: no information on influence of dissolution time to values of the surface charge on apatite has been found in literature^[70-72,78,86-88,153-157]. So, one may assume, that if a chemical composition of the solution is kept constant the surface charge on apatite will also remain constant during dissolution. Replacement of calcium by protons results in formation of mono-atomic layer acidic calcium orthophosphates on the crystal surface. Chemical phenomena of these transformations are described by the chemical model^[100-102] and the kinetics (it strongly depends on the experimental conditions chosen) - by the surface controlled model.

After being desorbed from the surface, calcium cations (presumably, coupled with anions Aⁿ⁻) diffuse through the Nernst layer into the bulk solution (the diffusion controlled model)^[139,156]. However, according to the calcium-rich layer formation model, a part of the already dissolved calcium ions might be adsorbed back onto apatite. Adsorption of calcium was suggested to happen at the very beginning of dissolution only and resulted in formation of a perm-selective layer of calcium cations with or without counter ions (Aⁿ⁻ and/or

acidic orthophosphate)^[19,49-53,68]. In this case, there should be a competition between protons and calcium cations for the exposed ions of oxygen on the surface to be adsorbed onto. Experimental data on a shift of the point of surface zero charge into more basic solution pH in presence of calcium in a solution^[157] are in favor of such competition.

An idea on formation of some layer on the surface of apatite was raised in several dissolution models. For example, there is either a supposition (the polynuclear, diffusion and kinetically controlled models) or a description (the ion exchange, hydrogen catalytic and chemical models) of a very thin virtual layer of acidic calcium orthophosphates (more exactly presence of HPO_4^{2-} ions) on the surface of apatite. Besides, according to the calcium-rich layer formation model, dissolution of apatite happens by ionic diffusion through a layer containing calcium with or without counter ions^[19,49-53,68]. In part, this idea can be found within the ion exchange model where a monolayer of calcium citrate^[125-127] and/or calcium-acid complexes^[130,131] are assumed to form onto apatite during dissolution. However, no other model requires such suggestion. According to the rest of them, formation of any calcium containing compounds (different from acidic orthophosphates) on apatite is not discussed at all.

According to the chemical model, the initial stages of apatite dissolution consist of calcium detachment from the surface and incorporation of protons instead. Orthophosphate groups are assumed to keep their positions without any relocation^[100-102]. Due to the fact, that calcium occupies definite lattice positions, whereas protons are bound to oxygen ions of orthophosphate groups, removing of each calcium results in decreasing of attraction forces between the nearest (to this calcium) orthophosphate group and rest part of the crystals. When all (or almost all) neighboring cations of calcium have been removed, orthophosphate groups (as H_2PO_4^- , $\text{CaH}_2\text{PO}_4^+$ or H_3PO_4 - it is not clear yet) also detach from the surface. Then they diffuse along the surface away from the dissolution steps before entering the solution as described above for calcium^[139,156].

In the case of crystal faces with perfectly smooth surface (dissolution steps are absent), detachment of one or several ions results in formation of dissolution nuclei, which the polynuclear model is based on^[55-63]. According to this model, all sites in nuclei edges are the kink positions^[62] and, after appearance, the nuclei grow and spread over the surface with a definite lateral rate^[56], giving rise to formation of dissolution steps. If dissolution steps already existed on the crystal faces of apatite, detachment of one calcium or one orthophosphate would result in dissolution step movement jump-wise over a distance equal to the sizes of these ions (approximately for 1 and 3 Å, respectively).

The latter is also valid for dissolution of crystal edges and corners. Since the classical paper by Kaischew^[166], it is generally considered, that ions are less strongly bound

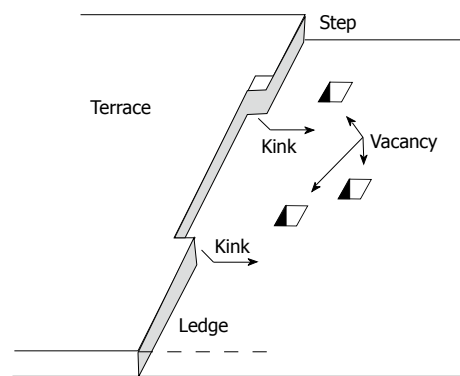


Figure 5 Surface of a crystal according to Kossel^[168]. The various types of imperfections are shown. Reprinted from Ref. [34] with permission.

along edges of a crystal than in the middle of faces and still less strongly at the corners^[167]. No information about the ionic arrangements on edges and corners of apatite crystals has been found in literature. Therefore, two boundary conditions are possible: the edges and corners mainly consist of ions of either calcium or orthophosphate. However, the edges parallel to the c -axis, in principle, may consist of X-ions (F^- , OH^- , Cl^-). The last case is the simplest one. According to the chemical model^[100-102], dissolution of apatite starts with protonation and detachment of X-ions, followed by removing of calcium (one should remind here that “walls” of the channels where X-ions are located consist of $\text{Ca}(2)$ ions^[96]) and afterwards by protonation and removing of orthophosphate. In the case, when the edges and corners of apatite mainly consist of calcium, again, according to the chemical model, detachment of weakly bounded calcium precedes protonation and removing of orthophosphate. Finally, if the edges and corners mainly consist of orthophosphate, the dissolution will start by chemical interaction of protons with these weakly bounded orthophosphate groups. The latter decreases electrostatic attraction forces between orthophosphate anions and neighboring calcium cations (attraction forces between Ca^{2+} and PO_4^{3-} are evidently stronger when compared with those between Ca^{2+} and HPO_4^{2-}). These forces become still weaker after adsorption of the second proton onto the given orthophosphate anion, causing its transformation to H_2PO_4^- followed by detachment.

Influence of dislocations and surface defects

Before now, no data on crystal defects have been used. For this reason, the above description is valid for dissolution of the perfect single crystals without defects and with the molecularly smooth surface. However, like other solids, crystals of apatite always contain both surface irregularities (e.g., steps, missing ions and dislocation outlets) and structural defects inside the bulk of crystals (e.g., dislocations and inclusions). The schematic depiction of a crystal surface is shown in Figure 5. This model is known as the “Kossel model”^[168]. In principle, any surface irregularities may act as dissolution nuclei

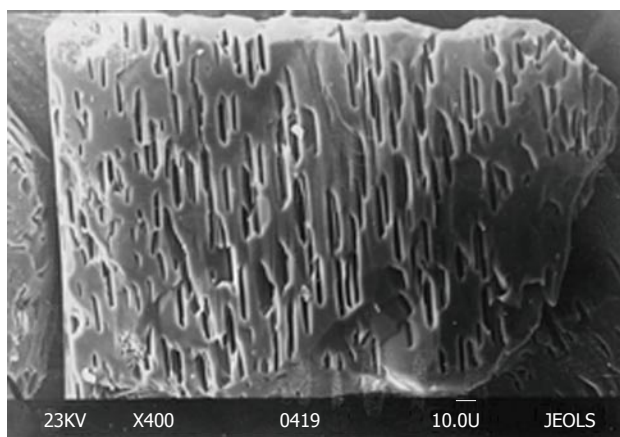


Figure 6 An example of etched crystal surface of natural fluorapatite with typical hexagonal etch pits. Bar 10 μm .

because sometimes even one missing ion might become the critical nuclei (the polynuclear model)^[60,61].

Each dislocation outlet on apatite was found to be a hollow core with radius within 8.3–20 Å for the screw dislocations and even 18–43 Å for the edge ones^[109]. Dimensions of the hexagonal unit-cell of apatite are: $a \approx 9.43$ Å, $c \approx 6.88$ Å. If the numeric values for the dislocation outlets were calculated correctly, their dimensions (diameter of the hollow cores) would be 1.8–4.2 times a or 2.4–5.8 times c (for the screw dislocations) and even 3.8–9.1 times a or 5.2–12.5 times c (for the edge dislocations). Thus, each dislocation outlet on the crystal surface looks like a large dissolution nucleus equal to detachment of 3–19 unit cells, (if this is taken to be the product ac) for the screw dislocations and even of 15–90 unit cells for the edge ones.

The process of etch pits formation and growth on apatites was described in details elsewhere^[41–48,66,67,106–122]. In the case of single crystals of pure HA, an acid attack was found to start formation of one etch pit in the basal plane which was the preferred dissolution spot or active site. Immediately afterwards the acid formed a longitudinal hole parallel to the c -axis^[110]. On the contrary, dissolution of natural FA was found to happen with formation of a great number of etch pits (about $5 \times 10^5 \text{ cm}^{-2}$) on the surface (Figure 6)^[113–115]. The latter just points out to the great differences in amount of crystal defects and impurities between the chemically pure^[41–48,66,67,106–112,118–122] and natural^[113–115] apatites.

In any case, after being formed, the pits were found to grow in all directions (length, width and depth - see Figure 3) with definite rates until they either covered all crystal faces of apatite (dissolution of natural crystals^[113–115]) or made longitudinal holes parallel to the c -axis (dissolution of the single crystals of pure HA^[106–111]). However, according to “a new dissolution model incorporating particle size considerations”, the dissolution process becomes spontaneous only when the pits are reached the critical sizes^[41–48]. The unit-step movement of etch pit growth was suggested to consist of removing of a single ion, followed by surface diffusion away from the

place of ionic detachment, desorption from the surface and diffusion into the bulk solution. All these processes evidently occur according to the basic findings of the ion exchange, chemical, calcium-rich layer formation, hydrogen catalytic and diffusion controlled dissolution models.

To conclude this part, except the dissolution rates increasing and surface etching, no other influences of dislocations on the dissolution mechanism were found.

CONCLUSION

Thus, based on eight dissolution models drawn from the previously published papers, an attempt to create the general description of apatite dissolution process at the atomic (ionic) level has been made. This dissolution mechanism is based on current level of knowledge and will be updated, corrected and modified simultaneously with appearance of new experimental data. Now some missing and unclear points to be investigated in future can be outlined: (1) chemical transformations happening with all ions during diffusion through the Nernst layer; (2) chemical composition of the apatite surface during dissolution; (3) processes of ionic sorption and detachment; (4) processes of dissolution nuclei formation and growth; (5) initial stages of etch pits formation at the dislocation outlets; and (6) specific influence of anions to the ionic sorption, surface diffusion and detachment. The above topics should be investigated in order to have better understanding of all the processes involved. For example, atomic force microscopy and phase shift interferometry might be useful tools in investigations on dissolution nuclei and etch pits formation^[66,67]. Micron-sized (better nano-sized) electrodes might be helpful in studying ionic transformations during diffusion through the Nernst layer^[140]. Modern techniques of the surface state analysis might be helpful in understanding the surface structure and its chemical composition.

REFERENCES

- 1 **McConnell D.** Apatite: its crystal chemistry, mineralogy, utilization, and geologic and biologic occurrences. Applied Mineralogy, Vol 5. Vienna and New York, USA: Springer-Verlag, 1973: 111 pp
- 2 **Aoki H.** Science and medical applications of hydroxyapatite. Tokyo, Japan: JAAS, 1991: 245 pp
- 3 **Elliott JC.** Structure and chemistry of the apatites and other calcium orthophosphates. Studies in inorganic chemistry, Vol. 18. Amsterdam, Netherlands: Elsevier, 1994: 389 pp
- 4 **LeGeros RZ.** Calcium phosphates in oral biology and medicine. Monographs in Oral Science. Vol. 15. Basel: Karger, 1991: 201 pp
- 5 **Dorozhkin SV.** Medical application of calcium orthophosphate bioceramics. *BIO* 2011; **1**: 1–51
- 6 **Dorozhkin SV.** Calcium orthophosphates: occurrence, properties, biomineralization, pathological calcification and biomimetic applications. *Biomatter* 2011; **1**: 121–164
- 7 **Dorozhkin SV.** Biocomposites and hybrid biomaterials based on calcium orthophosphates. *Biomatter* 2011; **1**: 3–56
- 8 **March J.** March's advanced organic chemistry: reactions, mechanisms, and structure. 5th Ed. New York: Wiley, 2001: 2083 pp

- 9 **Nancollas GH.** Physicochemistry of demineralization and remineralization. *J Dent Res* 1974; **53**: 297-302
- 10 **Wu MS, Higuchi WI, Fox JL, Friedman M.** Kinetics and mechanism of hydroxyapatite crystal dissolution in weak acid buffers using the rotating disk method. *J Dent Res* 1976; **55**: 496-505
- 11 **Smith AN, Posner AM, Quirk JP.** A model describing the kinetics of dissolution of hydroxyapatite. *J Coll Interf Sci* 1977; **62**: 475-494
- 12 **Okazaki M, Moriwaki Y, Aoba T, Doi Y, Takahashi J.** Dissolution rate behavior of fluoridated apatite pellets. *J Dent Res* 1981; **60**: 1907-1911
- 13 **Crommelin DJ, Higuchi WI, Fox JL, Spooner PJ, Katdare AV.** Dissolution rate behavior of hydroxyapatite-fluorapatite mixtures. *Caries Res* 1983; **17**: 289-296
- 14 **Nelson DG, Featherstone JD, Duncan JF, Cutress TW.** Effect of carbonate and fluoride on the dissolution behaviour of synthetic apatites. *Caries Res* 1983; **17**: 200-211
- 15 **Higuchi WI, Cesar EY, Cho PW, Fox JL.** Powder suspension method for critically re-examining the two-site model for hydroxyapatite dissolution kinetics. *J Pharm Sci* 1984; **73**: 146-153
- 16 **Budz JA, LoRe M, Nancollas GH.** Hydroxyapatite and carbonated apatite as models for the dissolution behavior of human dental enamel. *Adv Dent Res* 1987; **1**: 314-321
- 17 **Wong L, Cutress TW, Duncan JF.** The influence of incorporated and adsorbed fluoride on the dissolution of powdered and pelletized hydroxyapatite in fluoridated and non-fluoridated acid buffers. *J Dent Res* 1987; **66**: 1735-1741
- 18 **Budz JA, Nancollas GH.** The mechanism of dissolution of hydroxyapatite and carbonated apatite in acidic solutions. *J Cryst Growth* 1988; **91**: 490-496
- 19 **Thomann JM, Voegel JC, Gramain P.** Kinetics of dissolution of calcium hydroxyapatite powder. III: pH and sample conditioning effects. *Calcif Tissue Int* 1990; **46**: 121-129
- 20 **Chin KOA, Nancollas GH.** Dissolution of fluorapatite. A constant-composition kinetics study. *Langmuir* 1991; **7**: 2175-2179
- 21 **Margolis HC, Moreno EC.** Kinetics of hydroxyapatite dissolution in acetic, lactic, and phosphoric acid solutions. *Calcif Tissue Int* 1992; **50**: 137-143
- 22 **Paschalis EP, Wikiel K, Nancollas GH.** Dual constant composition kinetics characterization of apatitic surfaces. *J Biomed Mater Res* 1994; **28**: 1411-1418
- 23 **Calmanovici CE, Gilot B, Laguerie C.** Mechanism and kinetics for the dissolution of apatitic materials in acid solutions. *Brazilian J Chem Eng* 1997; **14**: 95-102
- 24 **Mohammadi Z, Ziaei-Moayyed AA, Sheikh-Mehdi Mesgar A.** In vitro dissolution of plasma-sprayed hydroxyapatite coatings with different characteristics: experimental study and modeling. *Biomed Mater* 2008; **3**: 015006
- 25 **van der Sluis S, Meszaros Y, Marchee WGJ, Wesselingh HA, van Rosmalen GM.** The digestion of phosphate ore in phosphoric acid. *Ind Eng Chem Res* 1987; **26**: 2501-2505
- 26 **Dobrydnev SV, Pochitalkina SA, Bogach VV, Beskov VS.** Ionometric study of the kinetics of acid decomposition of fluorapatite. *Russ J Appl Chem* 2001; **74**: 1627-1630
- 27 **Dobrydnev SV, Beskov VS, Bogach VV, Pochitalkina IA.** Ionometric study of the acid decomposition of phosphate minerals. *Theoret Found Chem Eng* 2001; **35**: 292-297
- 28 **Dobrydnev SV, Bogach VV, Beskov VS.** Analysis of the mass transfer in acid decomposition of phosphorus-containing raw material. *Theoret Found Chem Eng* 2003; **37**: 601-605
- 29 **Dobrydnev SV, Bogach VV, Kol'tsova EM, Beskov VS.** Effect of the charge of solid particles on the activation energy of acid decomposition of phosphorus-containing raw material. *Theoret Found Chem Eng* 2005; **39**: 415-418
- 30 **Brahim K, Antar K, Khattech I, Jemal M.** Effect of temperature on the attack of fluorapatite by a phosphoric acid solution. *Scientific Research and Essays* 2008; **3**: 035-039
- 31 **Fawzi MB, Fox JL, Dedhiya MG, Higuchi WI, Hefferren JJ.** A possible second site for hydroxyapatite dissolution in acidic media. *J Coll Interf Sci* 1978; **67**: 304-311
- 32 **Fox JL, Higuchi WI, Fawzi MB, Wu MS.** A new two-site model for hydroxyapatite dissolution in acidic media. *J Coll Interf Sci* 1978; **67**: 312-330
- 33 **Griffith EN, Katdare A, Fox JL, Higuchi WI.** Transmission electron microscopic confirmation of the morphological predictions of the two-site model for hydroxyapatite dissolution. *J Coll Interf Sci* 1978; **67**: 331-335
- 34 **Ehrlich H, Koutsoukos PG, Demadis KD, Pokrovsky OS.** Principles of demineralization: modern strategies for the isolation of organic frameworks. Part II. Decalcification. *Micron* 2009; **40**: 169-193
- 35 **Chow LC.** Response to Dr. E.I.F. Pearce's letter to the Editor. *J Dent Res* 1988; **67**: 1058-1059
- 36 **Tomson MB, Nancollas GH.** Mineralization kinetics: a constant composition approach. *Science* 1978; **200**: 1059-1060
- 37 **Tang R, Henneman ZJ, Nancollas GH.** Constant composition kinetics study of carbonated apatite dissolution. *J Cryst Growth* 2003; **249**: 614-624
- 38 **Tang R, Hass M, Wu W, Gulde S, Nancollas GH.** Constant composition dissolution of mixed phases. II. Selective dissolution of calcium phosphates. *J Coll Interf Sci* 2003; **260**: 379-384
- 39 **Ebrahimpour A, Zhang J, Nancollas GH.** Dual constant composition method and its application to studies of phase transformation and crystallization of mixed phases. *J Cryst Growth* 1991; **113**: 83-91
- 40 **Guidry MW, Mackenzie FT.** Experimental study of igneous and sedimentary apatite dissolution: control of pH, distance from equilibrium, and temperature on dissolution rates. *Geochim Cosmochim Acta* 2003; **67**: 2949-2963
- 41 **Tang R, Nancollas GH, Orme CA.** Mechanism of dissolution of sparingly soluble electrolytes. *J Am Chem Soc* 2001; **123**: 5437-5443
- 42 **Tang R, Wang L, Orme CA, Bonstein T, Bush PJ, Nancollas GH.** Dissolution at the nanoscale: self-preservation of biominerals. *Angew Chem Int Ed* 2004; **43**: 2697-2701
- 43 **Tang R, Wang L, Nancollas GH.** Size-effects in the dissolution of hydroxyapatite: an understanding of biological demineralization. *J Mater Chem* 2004; **14**: 2341-2346
- 44 **Tang R, Orme CA, Nancollas GH.** Dissolution of crystallites: surface energetic control and size effects. *Chemphyschem* 2004; **5**: 688-696
- 45 **Wang LJ, Tang R, Bonstein T, Bush P, Nancollas GH.** Enamel demineralization in primary and permanent teeth. *J Dent Res* 2006; **85**: 359-363
- 46 **Wang L, Nancollas GH.** Calcium orthophosphates: crystallization and dissolution. *Chem Rev* 2008; **108**: 4628-4669
- 47 **Wang L, Nancollas GH.** Pathways to biomineralization and biodegradation of calcium phosphates: the thermodynamic and kinetic controls. *Dalton Trans* 2009; 2665-2672
- 48 **Wang L, Nancollas GH.** Dynamics of Biomineralization and Biodegradation. *Met Ions Life Sci* 2010; **4**: 413-456
- 49 **Mafe S, Manzanares JA, Reiss H, Thomann JM, Gramain P.** Model for the dissolution of calcium hydroxyapatite powder. *J Phys Chem* 1992; **96**: 861-866
- 50 **Gasser P, Voegel JC, Gramain P.** Surface reactions on hydroxyapatite in the presence of fluoride ions. 1. Saturated and congruent conditions. *Colloids Surf A* 1993; **74**: 275-286
- 51 **Thomann JM, Voegel JC, Gramain P.** Quantitative model for the dissolution of calcium hydroxyapatite with a permselective ionic interface. *J Coll Interf Sci* 1993; **157**: 369-374
- 52 **Gasser P, Haikel Y, Voegel JC, Gramain P.** Surface reactions of hydroxyapatite in the presence of fluoride ions. 2. Effects of calcium and phosphate in saturated solutions. *Colloids Surf A* 1994; **88**: 157-168
- 53 **Schaad P, Poumier F, Voegel JC, Gramain P.** Analysis of calcium hydroxyapatite dissolution in non-stoichiometric

- solutions. *Colloids Surf A* 1997; **121**: 217-228
- 54 **Pan HB**, Darvell BW. Calcium phosphate solubility: the need for re-evaluation. *Cryst Growth Des* 2009; **9**: 639-645
 - 55 **Christoffersen J**, Christoffersen MR, Kjaergaard N. The kinetics of dissolution of calcium hydroxyapatite in water at constant pH. *J Cryst Growth* 1978; **43**: 501-511
 - 56 **Christoffersen J**. Kinetics of dissolution of calcium hydroxyapatite. III. Nucleation-controlled dissolution of a poly-disperse sample of crystals. *J Cryst Growth* 1980; **49**: 29-44
 - 57 **Christoffersen J**. Dissolution of calcium hydroxyapatite. *Calcif Tissue Int* 1981; **33**: 557-560
 - 58 **Christoffersen J**, Christoffersen MR. Kinetics of dissolution of calcium hydroxyapatite. V. The acidity constant for the hydrogen phosphate surface complex. *J Cryst Growth* 1982; **57**: 21-26
 - 59 **Christoffersen MR**, Christoffersen J. Possible mechanisms for the growth of the biomaterial, calcium hydroxyapatite microcrystals. *J Cryst Growth* 1992; **121**: 617-630
 - 60 **Christoffersen J**, Christoffersen MR, Johansen T. Kinetics of growth and dissolution of fluorapatite. *J Cryst Growth* 1996; **163**: 295-303
 - 61 **Christoffersen J**, Christoffersen MR, Johansen T. Some new aspects of surface nucleation applied to the growth and dissolution of fluorapatite and hydroxyapatite. *J Cryst Growth* 1996; **163**: 304-310
 - 62 **Christoffersen J**, Dohrup J, Christoffersen MR. The importance of formation of hydroxyl ions by dissociation of trapped water molecules for growth of calcium hydroxyapatite crystals. *J Cryst Growth* 1998; **186**: 275-282
 - 63 **Christoffersen MR**, Dohrup J, Christoffersen J. Kinetics of growth and dissolution of calcium hydroxyapatite in suspensions with variable calcium to phosphate ratio. *J Cryst Growth* 1998; **186**: 283-290
 - 64 **Zhang H**, Li S, Yan Y. Dissolution behavior of hydroxyapatite powder in hydrothermal solution. *Ceram Int* 2001; **27**: 451-454
 - 65 **Gilmer GH**, Bennema P. Simulation of crystal growth with surface diffusion. *J Appl Physics* 1972; **43**: 1347-1360
 - 66 **Onuma K**, Ito A, Tateishi T, Kameyama T. Growth kinetics of hydroxyapatite crystal revealed by atomic force microscopy. *J Cryst Growth* 1995; **154**: 118-125
 - 67 **Onuma K**, Ito A, Tateishi T. Investigation of a growth unit of hydroxyapatite crystal from the measurements of step kinetics. *J Cryst Growth* 1996; **167**: 773-776
 - 68 **Zhu Y**, Zhang X, Chen Y, Xie Q, Lan J, Qian M, He N. A comparative study on the dissolution and solubility of hydroxylapatite and fluorapatite at 25°C and 45°C. *Chemical Geology* 2009; **268**: 89-96
 - 69 **Kukura M**, Bell LC, Posner AM, Quirk JP. Radioisotope determination of the surface concentrations of calcium and phosphorus on hydroxyapatite in aqueous solution. *J Phys Chem* 1972; **76**: 900-904
 - 70 **Somasundaran P**. Zeta potential of apatite in aqueous solutions and its change during equilibration. *J Coll Interf Sci* 1968; **27**: 659-666
 - 71 **Bell LC**, Posner AM, Quirk JP. Surface charge characteristics of hydroxyapatite and fluorapatite. *Nature* 1972; **239**: 515-517
 - 72 **Bell LC**, Posner AM, Quirk JP. The point of zero charge of hydroxyapatite and fluorapatite in aqueous solutions. *J Coll Interf Sci* 1973; **42**: 250-261
 - 73 **Moreno EC**, Gregory TM, Brown WE. Preparation and solubility of hydroxyapatite. *J Res Natl Bur Stand* 1968; **72A**: 773-782
 - 74 **Chuong R**. Experimental study of surface and lattice effects on the solubility of hydroxyapatite. *J Dent Res* 1973; **52**: 911-914
 - 75 **Smith AN**, Posner AM, Quirk JP. Incongruent dissolution and surface complexes of hydroxyapatite. *J Coll Interf Sci* 1974; **48**: 442-449
 - 76 **Mika H**, Bell LC, Kruger BJ. The role of surface reactions in the dissolution of stoichiometric hydroxyapatite. *Arch Oral Biol* 1976; **21**: 697-701
 - 77 **Moreno EC**, Kresak M, Zahradnik RT. Physicochemical aspects of fluoride-apatite systems relevant to the study of dental caries. *Caries Res* 1977; **11** Suppl 1: 142-171
 - 78 **Bell LC**, Mika H, Kruger BJ. Synthetic hydroxyapatite-solubility product and stoichiometry of dissolution. *Arch Oral Biol* 1978; **23**: 329-336
 - 79 **Larsen MJ**. Chemical events during tooth dissolution. *J Dent Res* 1990; **69** Spec No: 575-580; discussion 634-636
 - 80 **Kaufman HW**, Kleinberg I. Studies on the incongruent solubility of hydroxyapatite. *Calcif Tissue Int* 1979; **27**: 143-151
 - 81 **Amrah-Bouali S**, Rey C, Lebugle A, Bernache D. Surface modifications of hydroxyapatite ceramics in aqueous media. *Biomaterials* 1994; **15**: 269-272
 - 82 **Nordström EG**, Hara T, Herø H. Solubility of hydroxyapatite/mica composites. *Biomed Mater Eng* 1996; **6**: 73-78
 - 83 **Pearce EI**, Guha-Chowdhury N, Iwami Y, Cutress TW. Stoichiometry of fluoride release from fluorhydroxyapatite during acid dissolution. *Caries Res* 1995; **29**: 130-136
 - 84 **Shimabayashi S**, Matsumoto M. Non-stoichiometric dissolution of hydroxyapatite in the presence of simple salts. *Nippon Kagaku Kaishi* 1993; **10**: 1118-1122
 - 85 **Brown PW**, Martin RI. An analysis of hydroxyapatite surface layer formation. *J Phys Chem B* 1999; **103**: 1671-1675
 - 86 **Chäirat C**, Oelkers EH, Schott J, Lartigue JE. Fluorapatite surface composition in aqueous solution deduced from potentiometric, electrokinetic, and solubility measurements, and spectroscopic observations. *Geochim Cosmochim Acta* 2007; **71**: 5888-5900
 - 87 **Bengtsson Å**, Shchukarev A, Persson P, Sjöberg S. A solubility and surface complexation study of a non-stoichiometric hydroxyapatite. *Geochim Cosmochim Acta* 2009; **73**: 257-267
 - 88 **Bengtsson Å**, Shchukarev A, Persson P, Sjöberg S. Phase transformations, ion-exchange, adsorption, and dissolution processes in aquatic fluorapatite systems. *Langmuir* 2009; **25**: 2355-2362
 - 89 **Bengtsson Å**, Sjöberg S. Surface complexation and proton-promoted dissolution in aqueous apatite systems. *Pure Appl Chem* 2009; **81**: 1569-1584
 - 90 **Feng MH**, Ngwenya BT, Wang L, Li W, Olive V, Ellam RM. Bacterial dissolution of fluorapatite as a possible source of elevated dissolved phosphate in the environment. *Geochim Cosmochim Acta* 2011; **75**: 5785-5796
 - 91 **Misra DN**. Interaction of citric or hydrochloric acid with calcium fluorapatite: precipitation of calcium fluoride. *J Coll Interf Sci* 1999; **220**: 387-391
 - 92 **Dobrydnev SV**, Bogach VV, Beskov VS. Thermodynamic grounds of sulfuric acid dissolution of fluorapatite. *Russ J Inorg Chem* 2002; **47**: 1063-1066
 - 93 **Dobrydnev SV**, Bogach VV, Beskov VS. Thermodynamics of fluoroapatite dissolution in phosphoric acid. *Russ J Inorg Chem* 2002; **47**: 1214-1216
 - 94 **Dobrydnev SV**, Bogach VV, Beskov VS. Thermodynamics of fluoroapatite dissolution in nitric acid. *Russ J Inorg Chem* 2002; **47**: 1217-1220
 - 95 **Harouiya N**, Chäirat C, Köhler SJ, Gout R, Oelkers EH. The dissolution kinetics and apparent solubility of natural apatite in closed reactors at temperatures from 5 to 50°C and pH from 1 to 6. *Chemical Geology* 2007; **244**: 554-568
 - 96 **Chäirat C**, Schott J, Oelkers EH, Lartigue JE, Harouiya N. Kinetics and mechanism of natural fluorapatite dissolution at 25°C and pH from 3 to 12. *Geochim Cosmochim Acta* 2007; **71**: 5901-5912
 - 97 **Melikhov IV**, Dorozhkin SV, Nikolaev AL, Voronina NY. Transition from congruent to incongruent dissolution. *Russ J Phys Chem* 1992; **66**: 1108-1111
 - 98 **Tanaka H**, Miyajima K, Nakagaki M, Shimabayashi S. Incongruent dissolution of hydroxyapatite in the presence of

- phosphoserine. *Coll Polymer Sci* 1991; **269**: 161-165
- 99 **Park C**, Fenter P, Zhang Z, Cheng L, Sturchio NC. Structure of the fluorapatite (100)-water interface by high-resolution X-ray reflectivity. *Am Mineral* 2004; **89**: 1647-1654
- 100 **Dorozhkin SV**. Surface Reactions of Apatite Dissolution. *J Colloid Interface Sci* 1997; **191**: 489-497
- 101 **Dorozhkin SV**. Acidic dissolution mechanism of natural fluorapatite. II. Nanolevel of investigations. *J Cryst Growth* 1997; **182**: 133-140
- 102 **Dorozhkin SV**. Inorganic chemistry of the dissolution phenomenon: the dissolution mechanism of calcium apatites at the atomic (ionic) level. *Comments Inorg Chem* 1999; **20**: 285-299
- 103 **Higuchi WI**, Gray JA, Hefferren JJ, Patel PR. Mechanisms of enamel dissolution in acid buffers. *J Dent Res* 1965; **44**: 330-341
- 104 **Pearce EI**. On the dissolution of hydroxyapatite in acid solutions. *J Dent Res* 1988; **67**: 1056-1059
- 105 **Eanes ED**, Meyer JL. The maturation of crystalline calcium phosphates in aqueous suspensions at physiologic pH. *Calcif Tissue Res* 1977; **23**: 259-269
- 106 **Lowell LC**. Dislocation etch pits in apatite. *Acta Metall* 1958; **6**: 775-778
- 107 **Jongebloed WL**, Molenaar I, Arends J. Orientation-dependent etchpit penetration and dissolution of fluoroapatite. *Caries Res* 1973; **7**: 154-165
- 108 **Jongebloed WL**, van den Berg PJ, Arends J. The dissolution of single crystals of hydroxyapatite in citric and lactic acids. *Calcif Tissue Res* 1974; **15**: 1-9
- 109 **Arends J**, Jongebloed WL. Dislocations and dissolution in apatites: theoretical considerations. *Caries Res* 1977; **11**: 186-188
- 110 **Arends J**, Jongebloed WL. Ultrastructural studies of synthetic apatite crystals. *J Dent Res* 1979; **58**: 837-843
- 111 **Daculsi G**, Kerebel B, Kerebel LM. Mechanisms of acid dissolution of biological and synthetic apatite crystals at the lattice pattern level. *Caries Res* 1979; **13**: 277-289
- 112 **Daculsi G**, LeGeros RZ, Mitre D. Crystal dissolution of biological and ceramic apatites. *Calcif Tissue Int* 1989; **45**: 95-103
- 113 **Melikhov IV**, Dorozhkin SV, Nikolaev AL, Kozlovskaya ED, Rudin VN. Dislocations and the rate of dissolution of solids. *Russ J Phys Chem* 1990; **64**: 1746-1750
- 114 **Dorozhkin SV**. Chemical etching of natural fluorapatite crystals in acid solutions studied with the scanning electron microscope. *Scanning* 1995; **17**: 355-360
- 115 **Dorozhkin SV**. Acidic dissolution mechanism of natural fluorapatite. I. Milli- and microlevels of investigations. *J Cryst Growth* 1997; **182**: 125-132
- 116 **Lasaga AC**, Lutge A. Variation of crystal dissolution rate based on a dissolution stepwise model. *Science* 2001; **291**: 2400-2404
- 117 **Dove PM**, Han N, De Yoreo JJ. Mechanisms of classical crystal growth theory explain quartz and silicate dissolution behavior. *Proc Natl Acad Sci USA* 2005; **102**: 15357-15362
- 118 **Kwon KY**, Wang E, Chung A, Chang N, Saiz E, Choe UJ, Koobatian M, Lee SW. Defect induced asymmetric pit formation on hydroxyapatite. *Langmuir* 2008; **24**: 11063-11066
- 119 **Kwon KY**, Wang E, Chung A, Chang N, Lee SW. Effect of salinity on hydroxyapatite dissolution studied by atomic force microscopy. *J Phys Chem C* 2009; **113**: 3369-3372
- 120 **Kwon KY**, Wang E, Chang N, Lee SW. Characterization of the dominant molecular step orientations on hydroxyapatite (100) surfaces. *Langmuir* 2009; **25**: 7205-7208
- 121 **Kwon KY**, Wang E, Nofal M, Lee SW. Microscopic study of hydroxyapatite dissolution as affected by fluoride ions. *Langmuir* 2011; **27**: 5335-5339
- 122 **Dong SS**, Hwan K, Jong KL. AFM study on the surface dissolution of hydroxyapatite. *Key Eng Mater* 2007; **336-338**: 1553-1555
- 123 **Wang LJ**, Lu JW, Xu FS, Zhang FS. Dynamics of crystallization and dissolution of calcium orthophosphates at the near-molecular level. *Chinese Sci Bull* 2011; **56**: 713-721
- 124 **Dorozhkin SV**. Process of epitaxial crystal growth for $\text{CaSO}_4 \cdot 0.5\text{H}_2\text{O}$ on a surface of dissolving fluorapatite crystals studied by scanning electron microscopy. *Scanning* 1996; **18**: 119-124
- 125 **Misra DN**. Interaction of citric acid with hydroxyapatite: surface exchange of ions and precipitation of calcium citrate. *J Dent Res* 1996; **75**: 1418-1425
- 126 **Lopez-Macipe A**, Gomez-Morales J, Rodriguez-Clemente R. The role of pH in the adsorption of citrate ions on hydroxyapatite. *J Coll Interf Sci* 1998; **200**: 114-120
- 127 **Misra DN**. Adsorption from solutions on synthetic hydroxyapatite: nonaqueous vs. aqueous solvents. *J Biomed Mater Res* 1999; **48**: 848-855
- 128 **Filgueiras MRT**, Mkhonto D, de Leeuw NH. Computer simulations of the adsorption of citric acid at hydroxyapatite surfaces. *J Cryst Growth* 2006; **294**: 60-68
- 129 **Jiang W**, Pan H, Cai Y, Tao J, Liu P, Xu X, Tang R. Atomic force microscopy reveals hydroxyapatite-citrate interfacial structure at the atomic level. *Langmuir* 2008; **24**: 12446-12451
- 130 **Yoshida Y**, Van Meerbeek B, Nakayama Y, Yoshioka M, Snauwaert J, Abe Y, Lambrechts P, Vanherle G, Okazaki M. Adhesion to and decalcification of hydroxyapatite by carboxylic acids. *J Dent Res* 2001; **80**: 1565-1569
- 131 **Yoshioka M**, Yoshida Y, Inoue S, Lambrechts P, Vanherle G, Nomura Y, Okazaki M, Shintani H, Van Meerbeek B. Adhesion/decalcification mechanisms of acid interactions with human hard tissues. *J Biomed Mater Res* 2002; **59**: 56-62
- 132 **Yoshida Y**, Van Meerbeek B, Nakayama Y, Snauwaert J, Hellemans L, Lambrechts P, Vanherle G, Wakasa K. Evidence of chemical bonding at biomaterial-hard tissue interfaces. *J Dent Res* 2000; **79**: 709-714
- 133 **Astala R**, Stott MJ. First-principles study of hydroxyapatite surfaces and water adsorption. *Phys Rev B* 2008; **78**: 075427 (11 pages)
- 134 **Posner AS**. The structure of bone apatite surfaces. *J Biomed Mater Res* 1985; **19**: 241-250
- 135 **Hochrein O**, Zahn D. On the molecular mechanisms of the acid-induced dissociation of hydroxy-apatite in water. *J Mol Model* 2011; **17**: 1525-1528
- 136 **Jarlborg M**, Gunneriusson L, Forsling W. Characterisation of the protolytic properties of synthetic carbonate free fluorapatite. *J Colloid Interface Sci* 2005; **285**: 206-211
- 137 **Becker P**. Phosphates and phosphoric acid: raw materials technology and economics of the wet process. 2nd Ed. Fertilizer science and technology series. New York, USA: Marcel Dekker, 1989: 760 pp
- 138 **Compton RG**, Harding MS, Pluck MR, Atherton JH, Brennan CM. Mechanism of solid/liquid interfacial reactions. The dissolution of benzoic acid in aqueous solution. *J Phys Chem* 1993; **97**: 10416-10420
- 139 **Zhang J**, Nancollas GH. Unexpected pH dependence of dissolution kinetics of dicalcium phosphate dihydrate. *J Phys Chem* 1994; **98**: 1689-1694
- 140 **de Aza PN**, Guitian F, Merlos A, Lora-Tamayo E, de Aza S. Bioceramics - simulated body fluid interfaces: pH and its influence of hydroxyapatite formation. *J Mater Sci Mater Med* 1996; **7**: 399-402
- 141 **Bohner M**, Lemaître J, Ring TA. Kinetics of Dissolution of beta-Tricalcium Phosphate *J Colloid Interface Sci* 1997; **190**: 37-48
- 142 **Young RA**. Implications of atomic substitutions and other structural details in apatites. *J Dent Res* 1974; **53**: 193-203
- 143 **de Leeuw NH**. Computer simulations of structures and properties of the biomaterial hydroxyapatite. *J Mater Chem* 2010; **20**: 5376-5389
- 144 **Pareek A**, Torrelles X, Angermund K, Rius J, Magdams U, Gies H. Structure of interfacial water on fluorapatite (100) surface. *Langmuir* 2008; **24**: 2459-2464

- 145 **Pan H**, Tao J, Wu T, Tang R. Molecular simulation of water behaviors on crystal faces of hydroxyapatite. *Zhongguo Huaxue Qianyan* 2007; **2**: 156-163
- 146 **Zahn D**, Hochrein O. Computational study of interfaces between hydroxyapatite and water. *Phys Chem Chem Phys* 2003; **5**: 4004-4007
- 147 **Corno M**, Busco C, Bolis V, Tosoni S, Ugliengo P. Water adsorption on the stoichiometric (001) and (010) surfaces of hydroxyapatite: a periodic B3LYP study. *Langmuir* 2009; **25**: 2188-2198
- 148 **Pareek A**, Torrelles X, Rius J, Magdans U, Gies H. Role of water in the surface relaxation of the fluorapatite (100) surface by grazing incidence X-ray diffraction. *Phys Rev B* 2007; **75**: 035418 (6 pages)
- 149 **Pan H**, Tao J, Yu X, Fu L, Zhang J, Zeng X, Xu G, Tang R. Anisotropic demineralization and oriented assembly of hydroxyapatite crystals in enamel: smart structures of biomaterials. *J Phys Chem B* 2008; **112**: 7162-7165
- 150 **Dorozhkin SV**. Nanodimensional and nanocrystalline apatites and other calcium orthophosphates in biomedical engineering, biology and medicine. *Materials* 2009; **2**: 1975-2045
- 151 **Dorozhkin SV**. Nanosized and nanocrystalline calcium orthophosphates. *Acta Biomater* 2010; **6**: 715-734
- 152 **Probstein RF**. Physicochemical hydrodynamics: an introduction. 2nd ed. Hoboken, NJ, USA: Wiley, 2003: 416 pp
- 153 **Wu L**, Forsling W, Schindler PW. Surface complexation of calcium minerals in aqueous solution. 1. Surface protonation at fluorapatite-water interfaces. *J Coll Interf Sci* 1991; **147**: 178-185
- 154 **Skartsila K**, Spanos N. Surface characterization of hydroxyapatite: potentiometric titrations coupled with solubility measurements. *J Colloid Interface Sci* 2007; **308**: 405-412
- 155 **Vucinić DR**, Radulović DS, Deusić SD. Electrokinetic properties of hydroxyapatite under flotation conditions. *J Colloid Interface Sci* 2010; **343**: 239-245
- 156 **Zhang J**, Nancollas GH. Kinetics and mechanisms of octacalcium phosphate dissolution at 37°C. *J Phys Chem* 1992; **96**: 5478-5483
- 157 **Doss SK**. Surface properties of hydroxyapatite: I. The effect of various inorganic ions on the electrophoretic behavior. *J Dent Res* 1976; **55**: 1067-1075
- 158 **Dobrydnev SV**, Bogach VV, Beskov VS. Influence of surfactants on the rate of decomposition of apatites by mineral acids. *Theoret Found Chem Eng* 2003; **37**: 412-415
- 159 **Nielsen AE**. Transport control in crystal growth from solution. *Croat Chem Acta* 1980; **53**: 255-279
- 160 **Okazaki M**, Sato M, Takahashi J. Space-cutting model of hydroxyapatite. *Biomaterials* 1995; **16**: 45-49
- 161 **Iijima M**, Nelson DG, Pan Y, Kreinbrink AT, Adachi M, Goto T, Moriawaki Y. Fluoride analysis of apatite crystals with a central planar OCP inclusion: concerning the role of F⁻ ions on apatite/OCP/apatite structure formation. *Calcif Tissue Int* 1996; **59**: 377-384
- 162 **Aoba T**. The effect of fluoride on apatite structure and growth. *Crit Rev Oral Biol Med* 1997; **8**: 136-153
- 163 **de Leeuw NH**. Resisting the onset of hydroxyapatite dissolution through the incorporation of fluoride. *J Phys Chem B* 2004; **108**: 1809-1811
- 164 **Liu Y**, Sethuraman G, Wu W, Nancollas GH, Grynaps M. The Crystallization of Fluorapatite in the Presence of Hydroxyapatite Seeds and of Hydroxyapatite in the Presence of Fluorapatite Seeds *J Colloid Interface Sci* 1997; **186**: 102-109
- 165 **Dickens B**, Schroeder LW. Investigation of epitaxy relationships between Ca₅(PO₄)₃OH and other calcium orthophosphates. *J Res Natl Bur Stand* 1980; **85**: 347-362
- 166 **Kaischew R**. Zur Theorie des Kristallwachstums. *Zeitschrift für Physik* 1936; **102**: 684-690
- 167 **Nangia S**, Garrison BJ. Ab initio study of dissolution and precipitation reactions from the edge, kink, and terrace sites of quartz as a function of pH. *Molecular Phys* 2009; **107**: 831-843
- 168 **Kossel W**. Zur Energetik von Oberflächenvorgängen. *Annalen der Physik* 1934; **21**: 457-480

S- Editor Wang JL L- Editor A E- Editor Li JY



ACKNOWLEDGMENTS

Acknowledgments to reviewers of *World Journal of Methodology*

Many reviewers have contributed their expertise and time to the peer review, a critical process to ensure the quality of *World Journal of Methodology*. The editors and authors of the articles submitted to the journal are grateful to the following reviewers for evaluating the articles (including those published in this issue and those rejected for this issue) during the last editing time period.

Richard W Bohannon, EdD, DPT, Professor, Kinesiology, University of Connecticut, 358 Mansfield Road, Storrs, CT 06269, United States

Sang-Soo Lee, MD, PhD, Professor, Head of Orthopedic Surgery, Chief Planning Officer, Institute for Skeletal Aging and Orthopedic Surgery, Chunchon Sacred Heart Hospital-Hallym University, 153 Gyodong, Chunchonsi, Kangwondo 200-704, South Korea

Wen-Hsiung Chan, PhD, Professor, Department of Bioscience Technology, Chung Yuan Christian University, No. 200, Chung Pei Road, Chung Li 32023, Taiwan, China

András Komócsi, MD, PhD, Heart Centre, University of Pécs, 13. Ifjúság, Pécs H-7621, Hungary

Rodolfo G Wuilloud, PhD, Analytical Chemistry Research and Development Group, LISAMEN – CCT – CONICET – Mendoza, Av. Ruiz Leal S/N Parque General San Martín, M 5502 IRA Mendoza, Argentina

Mariana de Andrea Hacker, PhD, Laboratory of Leprosy, Oswaldo Cruz Foundation, Avenida Brasil 4365 –Manguinhos, Rio de Janeiro 21040360, Brazil

Richard WJ Neufeld, PhD, Professor, Department of Psychology, University of Western Ontario, Westminster Hall, London, Ontario N6B 2K3, Canada

William CS Cho, PhD, FHKIMLS, Chartered Scientist (UK), FHKSMDS, FIBMS (UK), Consultant of Registered Chinese Medicine Practitioner Association, Department of Clinical Oncology, Queen Elizabeth Hospital, Room 1305, 13/F, Block R, 30 Gascoigne Road, Kowloon, Hong Kong, China

Hong-Xiang Sun, PhD, Associate Professor, College of Animal Sciences, Zhejiang University, Yuhangtang Road 866, Hangzhou 310053, Zhejiang Province, China

Marijeta Kralj, PhD, Senior Scientist, Head of Laboratory of Experimental Therapy, Division of Molecular Medicine, Rudjer Boskovic Institute, Zagreb 10000, Croatia

Peter J Quesenberry, MD, Division of Hematology, Oncology, Rhode Island Hospital, 593 Eddy Street, Providence, RI 02903, United States

Thomas TH Wan, PhD, MHS, Professor and Associate Dean for Research, College of Health and Public Affairs, PO Box 163680, Orlando, FL 32826-3680, United States

Events Calendar 2012

January 20-21, 2012

AGA Clinical Congress of Gastroenterology and Hepatology: Practice, Evidence and Quality in 2012
 Miami, FL, United States

January 26, 2012

Symposium of the Swiss Society of Pharmacology and Toxicology, Advances in Pharmacology - Cardiovascular Pharmacology
 Bern, Switzerland

January 28 - February 1, 2012

LabAutomation2012
 Palm Springs Convention Center,
 Palm Springs, CA, United States

February 1-4, 2012

3rd International Workshop on Medical Image Analysis and Description for Diagnosis System
 Hotel Tivoli Victoria, Algarve, Portugal

February 24, 2012

State Stem Cell Agency Governance Subcommittee
 San Francisco, CA, United States

March 11-14, 2012

Thoracic Imaging 2012
 Hyatt Regency, Huntington Beach Resort and Spa, Huntington Beach, CA, United States

March 25-30, 2012

44th International Diagnostic Course

Davos (IDKD)

Davos, Switzerland

April 26-29, 2012

75th Anniversary of the Canadian Association of Radiologists Annual Scientific Meeting
 Le Centre Sheraton, Montreal, Quebec, Canada

April 29 - May 4, 2012

EUCHEM Conference on Stereochemistry
 Brunnen, Switzerland

May 4-6, 2012

World Congress on Biotechnology
 Hyderabad, India

June 7-9, 2012

ASCI 2012 - 6th Congress of Asian Society of Cardiovascular Imaging
 Bangkok, Thailand

June 9-13, 2012

2012 Annual Meeting of the Society of Nuclear Medicine
 Miami Beach, FL, United States

August 15-19, 2012

ICE 2012 - International Congress of Endoscopy
 Daegu, South Korea

October 28-30, 2012

EANM 2012 - Annual Congress of the European Association of Nuclear Medicine
 Milan, Italy

GENERAL INFORMATION

World Journal of Methodology (World J Methodol, WJM, online ISSN 2222-0682, DOI: 10.5662) is a bimonthly peer-reviewed, online, open-access (OA), journal supported by an editorial board consisting of 238 experts in methodology from 41 countries.

The biggest advantage of the OA model is that it provides free, full-text articles in PDF and other formats for experts and the public without registration, which eliminates the obstacle that traditional journals possess and usually delays the speed of the propagation and communication of scientific research results. The open access model has been proven to be a true approach that may achieve the ultimate goal of the journals, i.e. the maximization of the value to the readers, authors and society.

Maximization of personal benefits

The role of academic journals is to exhibit the scientific levels of a country, a university, a center, a department, and even a scientist, and build an important bridge for communication between scientists and the public. As we all know, the significance of the publication of scientific articles lies not only in disseminating and communicating innovative scientific achievements and academic views, as well as promoting the application of scientific achievements, but also in formally recognizing the "priority" and "copyright" of innovative achievements published, as well as evaluating research performance and academic levels. So, to realize these desired attributes of WJM and create a well-recognized journal, the following four types of personal benefits should be maximized. The maximization of personal benefits refers to the pursuit of the maximum personal benefits in a well-considered optimal manner without violation of the laws, ethical rules and the benefits of others. (1) Maximization of the benefits of editorial board members: The primary task of editorial board members is to give a peer review of an unpublished scientific article via online office system to evaluate its innovativeness, scientific and practical values and determine whether it should be published or not. During peer review, editorial board members can also obtain cutting-edge information in that field at first hand. As leaders in their field, they have priority to be invited to write articles and publish commentary articles. We will put peer reviewers' names and affiliations along with the article they reviewed in the journal to acknowledge their contribution; (2) Maximization of the benefits of authors: Since WJM is an open-access journal, readers around the world can immediately download and read, free of charge, high-quality, peer-reviewed articles from WJM official website, thereby realizing the goals and significance of the communication between authors and peers as well as public reading; (3) Maximization of the benefits of readers: Readers can read or use, free of charge, high-quality peer-reviewed articles without any limits, and cite the arguments, viewpoints, concepts, theories, methods, results, conclusion or facts and data of pertinent literature so as to validate the innovativeness, scientific and practical values of their own research achievements, thus ensuring that their articles have novel arguments or viewpoints, solid evidence and correct conclusion; and (4) Maximization of the benefits of employees: It is an iron law that a first-class journal is unable to exist without first-class editors, and only first-class editors can create a first-class academic journal. We insist on strengthening our team cultivation and construction so that every employee, in an open, fair and transparent environment, could contribute their wisdom to edit and publish high-quality ar-

ticles, thereby realizing the maximization of the personal benefits of editorial board members, authors and readers, and yielding the greatest social and economic benefits.

Aims and scope

WJM aims to rapidly report the most recent results in medical diagnostics, therapeutic techniques and equipment, clinical medical research, clinical and experimental techniques and methodology. It provides a platform to facilitate the integration of clinical medicine and experimental techniques and methodology to help clinicians improve diagnostic accuracy and therapeutic efficacy. The journal publishes original articles and reviews on the following topics: (1) Clinical medical techniques, including but not limited to those for pharmaceutical medicine, laboratory medicine, radioactive medicine, medical imaging, nuclear medicine, physical therapy, pathology, surgery, disinfection, nutritional therapy, transfusion and medical equipment; (2) Clinical medical research on etiology, epidemiology, pathogenesis, morphology and function, signs and symptoms, clinical trials, and evidence-based medicine; and (3) Laboratory methodology, including but not limited to techniques in DNA/RNA sequencing, preparation and transformation of competent cells, PCR, protein biochemistry, cell biology, genetics and epigenetics, immunology, microbiology, animal models of human pathologies, bioinformatics, and laboratory equipment manipulation and control.

Columns

The columns in the issues of WJM will include: (1) Editorial: To introduce and comment on major advances and developments in the field; (2) Frontier: To review representative achievements, comment on the state of current research, and propose directions for future research; (3) Topic Highlight: This column consists of three formats, including (A) 10 invited review articles on a hot topic, (B) a commentary on common issues of this hot topic, and (C) a commentary on the 10 individual articles; (4) Observation: To update the development of old and new questions, highlight unsolved problems, and provide strategies on how to solve the questions; (5) Guidelines for Basic Research: To provide Guidelines for basic research; (6) Guidelines for Clinical Practice: To provide guidelines for clinical diagnosis and treatment; (7) Review: To review systemically progress and unresolved problems in the field, comment on the state of current research, and make suggestions for future work; (8) Original Articles: To report innovative and original findings in basic and clinical medical research methodology; (9) Brief Articles: To briefly report the novel and innovative findings in basic and clinical medical research methodology; (10) Case Report: To report a rare or typical case; (11) Letters to the Editor: To discuss and make reply to the contributions published in WJM, or to introduce and comment on a controversial issue of general interest; (12) Book Reviews: To introduce and comment on quality monographs of basic and clinical medical research methodology; (13) Guidelines: To introduce Consensuses and Guidelines reached by international and national academic authorities worldwide on the research basic and clinical medical research methodology; and (14) Voices: to publicize methodology-related communications that have been rejected or impossible for publication elsewhere due to evident prejudice and/or unreasonable reasons. Similarly, your experiences of the proven mistreatment during the past grant applications can be narrated or documented in this corner. The corresponding responses and echoes from readers are also welcome here.

Instructions to authors

Name of journal

World Journal of Methodology

ISSN

ISSN 2222-0682 (online)

Editor-in-Chief

Yicheng Ni, MD, PhD, Professor, Department of Radiology, University Hospitals, KU, Leuven, Herestraat 49, B-3000, Leuven, Belgium

Editorial Office

World Journal of Methodology

Editorial Department: Room 903, Building D,

Ocean International Center,

No. 62 Dongsihuan Zhonglu,

Chaoyang District, Beijing 100025, China

E-mail: wjm@wjgnet.com

<http://www.wjgnet.com>

Telephone: +86-10-85381891

Fax: +86-10-85381893

Indexed and Abstracted in

Digital Object Identifier.

Published by

Baishideng Publishing Group Co., Limited

SPECIAL STATEMENT

All articles published in this journal represent the viewpoints of the authors except where indicated otherwise.

Biostatistical editing

Statistical review is performed after peer review. We invite an expert in Biomedical Statistics from to evaluate the statistical method used in the paper, including *t*-test (group or paired comparisons), chi-squared test, Redit, probit, logit, regression (linear, curvilinear, or stepwise), correlation, analysis of variance, analysis of covariance, *etc.* The reviewing points include: (1) Statistical methods should be described when they are used to verify the results; (2) Whether the statistical techniques are suitable or correct; (3) Only homogeneous data can be averaged. Standard deviations are preferred to standard errors. Give the number of observations and subjects (*n*). Losses in observations, such as drop-outs from the study should be reported; (4) Values such as ED50, LD50, IC50 should have their 95% confidence limits calculated and compared by weighted probit analysis (Bliss and Finney); and (5) The word 'significantly' should be replaced by its synonyms (if it indicates extent) or the *P* value (if it indicates statistical significance).

Conflict-of-interest statement

In the interests of transparency and to help reviewers assess any potential bias, *WJM* requires authors of all papers to declare any competing commercial, personal, political, intellectual, or religious interests in relation to the submitted work. Referees are also asked to indicate any potential conflict they might have reviewing a particular paper. Before submitting, authors are suggested to read "Uniform Requirements for Manuscripts Submitted to Biomedical Journals: Ethical Considerations in the Conduct and Reporting of Research: Conflicts of Interest" from International Committee of Medical Journal Editors (ICMJE), which is available at: http://www.icmje.org/ethical_4conflicts.html.

Sample wording: [Name of individual] has received fees for serving as a speaker, a consultant and an advisory board member for [names of organizations], and has received research funding from [names of organization]. [Name of individual] is an employee of [name of organization]. [Name of individual] owns stocks and shares in [name of organization]. [Name of individual] owns patent [patent identification and brief description].

Statement of informed consent

Manuscripts should contain a statement to the effect that all human studies have been reviewed by the appropriate ethics committee or it should be stated clearly in the text that all persons gave their informed consent prior to their inclusion in the study. Details that might disclose the identity of the subjects under study should be omitted. Authors should also draw attention to the Code of Ethics of the World Medical Association (Declaration of Helsinki, 1964, as revised in 2004).

Statement of human and animal rights

When reporting the results from experiments, authors should follow the highest standards and the trial should conform to Good Clinical Practice (for example, US Food and Drug Administration Good Clinical Practice in FDA-Regulated Clinical Trials; UK Medicines Research Council Guidelines for Good Clinical Practice in Clinical Trials) and/or the World Medical Association Declaration of Helsinki. Generally, we suggest authors follow the lead investigator's national standard. If doubt exists whether the research was conducted in accordance with the above standards, the authors must explain the rationale for their approach and demonstrate that the institutional review body explicitly approved the doubtful aspects of the study.

Before submitting, authors should make their study approved by the relevant research ethics committee or institutional review board. If human participants were involved, manuscripts must be accompanied by a statement that the experiments were undertaken with the understanding and appropriate informed consent of each. Any personal item or information will not be published without explicit consents from the involved patients. If experimental animals were used, the materials and methods (experimental procedures) section must clearly indicate that appropriate measures were taken to minimize pain or discomfort, and details of animal care should be provided.

SUBMISSION OF MANUSCRIPTS

Manuscripts should be typed in 1.5 line spacing and 12 pt. Book Antiqua with ample margins. Number all pages consecutively, and start each of the following sections on a new page: Title Page, Abstract, Introduction, Materials and Methods, Results, Discussion, Acknowledgements, References, Tables, Figures, and Figure Legends. Neither the editors nor the publisher are responsible for the opinions expressed by contributors. Manuscripts formally accepted for publication become the permanent property of Baishideng Publishing Group Co., Limited, and may not be reproduced by any means, in whole or in part, without the written permission of both the authors and the publisher. We reserve the right to copy-edit and put onto our website accepted manuscripts. Authors should follow the relevant guidelines for the care and use of laboratory animals of their institution or national animal welfare committee. For the sake of transparency in regard to the performance and reporting of clinical trials, we endorse the policy of the ICMJE to refuse to publish papers on clinical trial results if the trial was not recorded in a publicly-accessible registry at its outset. The only register now available, to our knowledge, is <http://www.clinicaltrials.gov> sponsored by the United States National Library of Medicine and we encourage all potential contributors to register with it. However, in the case that other registers become available you will be duly notified. A letter of recommendation from each author's organization should be provided with the contributed article to ensure the privacy and secrecy of research is protected.

Authors should retain one copy of the text, tables, photographs and illustrations because rejected manuscripts will not be returned to the author(s) and the editors will not be responsible for loss or damage to photographs and illustrations sustained during mailing.

Online submissions

Manuscripts should be submitted through the Online Submission System at: <http://www.wjgnet.com/2222-0682office>. Authors are highly recommended to consult the ONLINE INSTRUCTIONS TO AUTHORS (<http://www.wjgnet.com/2222-0682/>)

g_info_20100722180909.htm) before attempting to submit online. For assistance, authors encountering problems with the Online Submission System may send an email describing the problem to wjm@wjgnet.com, or by telephone: +86-10-85381892. If you submit your manuscript online, do not make a postal contribution. Repeated online submission for the same manuscript is strictly prohibited.

MANUSCRIPT PREPARATION

All contributions should be written in English. All articles must be submitted using word-processing software. All submissions must be typed in 1.5 line spacing and 12 pt. Book Antiqua with ample margins. Style should conform to our house format. Required information for each of the manuscript sections is as follows:

Title page

Title: Title should be less than 12 words.

Running title: A short running title of less than 6 words should be provided.

Authorship: Authorship credit should be in accordance with the standard proposed by ICMJE, based on (1) substantial contributions to conception and design, acquisition of data, or analysis and interpretation of data; (2) drafting the article or revising it critically for important intellectual content; and (3) final approval of the version to be published. Authors should meet conditions 1, 2, and 3.

Institution: Author names should be given first, then the complete name of institution, city, province and postcode. For example, Xu-Chen Zhang, Li-Xin Mei, Department of Pathology, Chengde Medical College, Chengde 067000, Hebei Province, China. One author may be represented from two institutions, for example, George Sgourakis, Department of General, Visceral, and Transplantation Surgery, Essen 45122, Germany; George Sgourakis, 2nd Surgical Department, Korgialenio-Benakio Red Cross Hospital, Athens 15451, Greece

Author contributions: The format of this section should be: Author contributions: Wang CL and Liang L contributed equally to this work; Wang CL, Liang L, Fu JF, Zou CC, Hong F and Wu XM designed the research; Wang CL, Zou CC, Hong F and Wu XM performed the research; Xue JZ and Lu JR contributed new reagents/analytic tools; Wang CL, Liang L and Fu JF analyzed the data; and Wang CL, Liang L and Fu JF wrote the paper.

Supportive foundations: The complete name and number of supportive foundations should be provided, e.g. Supported by National Natural Science Foundation of China, No. 30224801

Correspondence to: Only one corresponding address should be provided. Author names should be given first, then author title, affiliation, the complete name of institution, city, postcode, province, country, and email. All the letters in the email should be in lower case. A space interval should be inserted between country name and email address. For example, Montgomery Bissell, MD, Professor of Medicine, Chief, Liver Center, Gastroenterology Division, University of California, Box 0538, San Francisco, CA 94143, United States. montgomery.bissell@ucsf.edu

Telephone and fax: Telephone and fax should consist of +, country number, district number and telephone or fax number, e.g. Telephone: +86-10-85381892 Fax: +86-10-85381893

Peer reviewers: All articles received are subject to peer review. Normally, three experts are invited for each article. Decision for acceptance is made only when at least two experts recommend an article for publication. Reviewers for accepted manuscripts are acknowledged in each manuscript, and reviewers of articles which

were not accepted will be acknowledged at the end of each issue. To ensure the quality of the articles published in *WJM*, reviewers of accepted manuscripts will be announced by publishing the name, title/position and institution of the reviewer in the footnote accompanying the printed article. For example, reviewers: Professor Jing-Yuan Fang, Shanghai Institute of Digestive Disease, Shanghai, Affiliated Renji Hospital, Medical Faculty, Shanghai Jiaotong University, Shanghai, China; Professor Xin-Wei Han, Department of Radiology, The First Affiliated Hospital, Zhengzhou University, Zhengzhou, Henan Province, China; and Professor Anren Kuang, Department of Nuclear Medicine, Huaxi Hospital, Sichuan University, Chengdu, Sichuan Province, China.

Abstract

There are unstructured abstracts (no less than 256 words) and structured abstracts (no less than 480). The specific requirements for structured abstracts are as follows:

An informative, structured abstracts of no less than 480 words should accompany each manuscript. Abstracts for original contributions should be structured into the following sections. AIM (no more than 20 words): Only the purpose should be included. Please write the aim as the form of "To investigate/study/...; MATERIALS AND METHODS (no less than 140 words); RESULTS (no less than 294 words): You should present *P* values where appropriate and must provide relevant data to illustrate how they were obtained, e.g. 6.92 ± 3.86 vs 3.61 ± 1.67 , $P < 0.001$; CONCLUSION (no more than 26 words).

Key words

Please list 5-10 key words, selected mainly from *Index Medicus*, which reflect the content of the study.

Text

For articles of these sections, original articles and brief articles, the main text should be structured into the following sections: INTRODUCTION, MATERIALS AND METHODS, RESULTS and DISCUSSION, and should include appropriate Figures and Tables. Data should be presented in the main text or in Figures and Tables, but not in both. The main text format of these sections, editorial, topic highlight, case report, letters to the editors, can be found at: http://www.wjgnet.com/2222-0682/g_info_20100725072755.htm.

Illustrations

Figures should be numbered as 1, 2, 3, etc., and mentioned clearly in the main text. Provide a brief title for each figure on a separate page. Detailed legends should not be provided under the figures. This part should be added into the text where the figures are applicable. Figures should be either Photoshop or Illustrator files (in tiff, eps, jpeg formats) at high-resolution. Examples can be found at: <http://www.wjgnet.com/1007-9327/13/4520.pdf>; <http://www.wjgnet.com/1007-9327/13/4554.pdf>; <http://www.wjgnet.com/1007-9327/13/4891.pdf>; <http://www.wjgnet.com/1007-9327/13/4986.pdf>; <http://www.wjgnet.com/1007-9327/13/4498.pdf>. Keeping all elements compiled is necessary in line-art image. Scale bars should be used rather than magnification factors, with the length of the bar defined in the legend rather than on the bar itself. File names should identify the figure and panel. Avoid layering type directly over shaded or textured areas. Please use uniform legends for the same subjects. For example: Figure 1 Pathological changes in atrophic gastritis after treatment. A: ...; B: ...; C: ...; D: ...; E: ...; F: ...; G: ...etc. It is our principle to publish high resolution-figures for the printed and E-versions.

Tables

Three-line tables should be numbered 1, 2, 3, etc., and mentioned clearly in the main text. Provide a brief title for each table. Detailed legends should not be included under tables, but rather added into the text where applicable. The information should complement, but not duplicate the text. Use one horizontal line under the title, a second under column heads, and a third below the Table, above any

Instructions to authors

footnotes. Vertical and italic lines should be omitted.

Notes in tables and illustrations

Data that are not statistically significant should not be noted. ^a*P* < 0.05, ^b*P* < 0.01 should be noted (*P* > 0.05 should not be noted). If there are other series of *P* values, ^c*P* < 0.05 and ^d*P* < 0.01 are used. A third series of *P* values can be expressed as ^e*P* < 0.05 and ^f*P* < 0.01. Other notes in tables or under illustrations should be expressed as ¹F, ²F, ³F; or sometimes as other symbols with a superscript (Arabic numerals) in the upper left corner. In a multi-curve illustration, each curve should be labeled with ●, ○, ■, □, ▲, △, etc., in a certain sequence.

Acknowledgments

Brief acknowledgments of persons who have made genuine contributions to the manuscript and who endorse the data and conclusions should be included. Authors are responsible for obtaining written permission to use any copyrighted text and/or illustrations.

REFERENCES

Coding system

The author should number the references in Arabic numerals according to the citation order in the text. Put reference numbers in square brackets in superscript at the end of citation content or after the cited author's name. For citation content which is part of the narration, the coding number and square brackets should be typeset normally. For example, "Crohn's disease (CD) is associated with increased intestinal permeability^[1,2]". If references are cited directly in the text, they should be put together within the text, for example, "From references^[19,22-24], we know that..."

When the authors write the references, please ensure that the order in text is the same as in the references section, and also ensure the spelling accuracy of the first author's name. Do not list the same citation twice.

PMID and DOI

Please provide PubMed citation numbers to the reference list, e.g. PMID and DOI, which can be found at <http://www.ncbi.nlm.nih.gov/sites/entrez?db=pubmed> and <http://www.crossref.org/SimpleTextQuery/>, respectively. The numbers will be used in E-version of this journal.

Style for journal references

Authors: the name of the first author should be typed in bold-faced letters. The family name of all authors should be typed with the initial letter capitalized, followed by their abbreviated first and middle initials. (For example, Lian-Sheng Ma is abbreviated as Ma LS, Bo-Rong Pan as Pan BR). The title of the cited article and italicized journal title (journal title should be in its abbreviated form as shown in PubMed), publication date, volume number (in black), start page, and end page [PMID: 11819634 DOI: 10.3748/wjg.13.5396].

Style for book references

Authors: the name of the first author should be typed in bold-faced letters. The surname of all authors should be typed with the initial letter capitalized, followed by their abbreviated middle and first initials. (For example, Lian-Sheng Ma is abbreviated as Ma LS, Bo-Rong Pan as Pan BR) Book title. Publication number. Publication place: Publication press, Year: start page and end page.

Format

Journals

English journal article (list all authors and include the PMID where applicable)

- 1 **Jung EM**, Clevert DA, Schreyer AG, Schmitt S, Rennert J, Kubale R, Feuerbach S, Jung F. Evaluation of quantitative contrast harmonic imaging to assess malignancy of liver tumors: A prospective controlled two-center study. *World J Gastroenterol* 2007; **13**: 6356-6364 [PMID: 18081224 DOI: 10.3748/wjg.13.6356]

Chinese journal article (list all authors and include the PMID where applicable)

- 2 **Lin GZ**, Wang XZ, Wang P, Lin J, Yang FD. Immunologic effect of Jianpi Yishen decoction in treatment of Pixu-diarhoea. *Shijie Huaren Xiaobua Zazhi* 1999; **7**: 285-287

In press

- 3 **Tian D**, Araki H, Stahl E, Bergelson J, Kreitman M. Signature of balancing selection in Arabidopsis. *Proc Natl Acad Sci USA* 2006; In press

Organization as author

- 4 **Diabetes Prevention Program Research Group**. Hypertension, insulin, and proinsulin in participants with impaired glucose tolerance. *Hypertension* 2002; **40**: 679-686 [PMID: 12411462 PMID:2516377 DOI:10.1161/01.HYP.0000035706.28494.09]

Both personal authors and an organization as author

- 5 **Vallancien G**, Emberton M, Harving N, van Moorselaar RJ; Alf-One Study Group. Sexual dysfunction in 1, 274 European men suffering from lower urinary tract symptoms. *J Urol* 2003; **169**: 2257-2261 [PMID: 12771764 DOI:10.1097/01.ju.0000067940.76090.73]

No author given

- 6 21st century heart solution may have a sting in the tail. *BMJ* 2002; **325**: 184 [PMID: 12142303 DOI:10.1136/bmj.325.7357.184]

Volume with supplement

- 7 **Geraud G**, Spierings EL, Keywood C. Tolerability and safety of frovatriptan with short- and long-term use for treatment of migraine and in comparison with sumatriptan. *Headache* 2002; **42** Suppl 2: S93-99 [PMID: 12028325 DOI:10.1046/j.1526-4610.42.s2.7.x]

Issue with no volume

- 8 **Banit DM**, Kaufer H, Hartford JM. Intraoperative frozen section analysis in revision total joint arthroplasty. *Clin Orthop Relat Res* 2002; (**401**): 230-238 [PMID: 12151900 DOI:10.1097/00003086-200208000-00026]

No volume or issue

- 9 Outreach: Bringing HIV-positive individuals into care. *HRS-A Careaction* 2002; 1-6 [PMID: 12154804]

Books

Personal author(s)

- 10 **Sherlock S**, Dooley J. Diseases of the liver and biliary system. 9th ed. Oxford: Blackwell Sci Pub, 1993: 258-296

Chapter in a book (list all authors)

- 11 **Lam SK**. Academic investigator's perspectives of medical treatment for peptic ulcer. In: Swabb EA, Azabo S. Ulcer disease: investigation and basis for therapy. New York: Marcel Dekker, 1991: 431-450

Author(s) and editor(s)

- 12 **Breedlove GK**, Schorheide AM. Adolescent pregnancy. 2nd ed. Wiczorek RR, editor. White Plains (NY): March of Dimes Education Services, 2001: 20-34

Conference proceedings

- 13 **Harnden P**, Joffe JK, Jones WG, editors. Germ cell tumours V. Proceedings of the 5th Germ cell tumours Conference; 2001 Sep 13-15; Leeds, UK. New York: Springer, 2002: 30-56

Conference paper

- 14 **Christensen S**, Oppacher F. An analysis of Koza's computational effort statistic for genetic programming. In: Foster JA, Lutton E, Miller J, Ryan C, Tettamanzi AG, editors. Genetic programming. EuroGP 2002: Proceedings of the 5th European Conference on Genetic Programming; 2002 Apr 3-5; Kinsdale, Ireland. Berlin: Springer, 2002: 182-191

Electronic journal (list all authors)

- 15 Morse SS. Factors in the emergence of infectious diseases. *Emerg Infect Dis* serial online, 1995-01-03, cited 1996-06-05; 1(1): 24 screens. Available from: URL: <http://www.cdc.gov/ncidod/eid/index.htm>

Patent (list all authors)

- 16 **Pagedas AC**, inventor; Ancel Surgical R&D Inc., assignee. Flexible endoscopic grasping and cutting device and positioning tool assembly. United States patent US 20020103498. 2002 Aug 1

Statistical data

Write as mean \pm SD or mean \pm SE.

Statistical expression

Express *t* test as *t* (in italics), *F* test as *F* (in italics), chi square test as χ^2 (in Greek), related coefficient as *r* (in italics), degree of freedom as *v* (in Greek), sample number as *n* (in italics), and probability as *P* (in italics).

Units

Use SI units. For example: body mass, *m* (B) = 78 kg; blood pressure, *p* (B) = 16.2/12.3 kPa; incubation time, *t* (incubation) = 96 h; blood glucose concentration, *c* (glucose) 6.4 ± 2.1 mmol/L; blood CEA mass concentration, *p* (CEA) = 8.6 $24.5 \mu\text{g/L}$; CO_2 volume fraction, 50 mL/L CO_2 , not 5% CO_2 ; likewise for 40 g/L formaldehyde, not 10% formalin; and mass fraction, 8 ng/g, *etc.* Arabic numerals such as 23, 243, 641 should be read 23 243 641.

The format for how to accurately write common units and quantum numbers can be found at: http://www.wjgnet.com/2222-0682/g_info_20100725073806.htm.

Abbreviations

Standard abbreviations should be defined in the abstract and on first mention in the text. In general, terms should not be abbreviated unless they are used repeatedly and the abbreviation is helpful to the reader. Permissible abbreviations are listed in Units, Symbols and Abbreviations: A Guide for Biological and Medical Editors and Authors (Ed. Baron DN, 1988) published by The Royal Society of Medicine, London. Certain commonly used abbreviations, such as DNA, RNA, HIV, LD50, PCR, HBV, ECG, WBC, RBC, CT, ESR, CSF, IgG, ELISA, PBS, ATP, EDTA, mAb, can be used directly without further explanation.

Italics

Quantities: *t* time or temperature, *c* concentration, *A* area, *l* length, *m* mass, *V* volume.

Genotypes: *gyrA*, *arg 1*, *c myc*, *c fos*, *etc.*

Restriction enzymes: *EcoRI*, *HindIII*, *BamHI*, *Kho I*, *Kpn I*, *etc.*

Biology: *H. pylori*, *E. coli*, *etc.*

Examples for paper writing

Editorial: http://www.wjgnet.com/2222-0682/g_info_20100725071851.htm

Frontier: http://www.wjgnet.com/2222-0682/g_info_20100725071932.htm

Topic highlight: http://www.wjgnet.com/2222-0682/g_info_20100725072121.htm

Observation: http://www.wjgnet.com/2222-0682/g_info_20100725072232.htm

Guidelines for basic research: http://www.wjgnet.com/2222-0682/g_info_20100725072344.htm

Guidelines for clinical practice: http://www.wjgnet.com/2222-0682/g_info_20100725072543.htm

Review: http://www.wjgnet.com/2222-0682/g_info_20100725072656.htm

Original articles: http://www.wjgnet.com/2222-0682/g_info_20100725072755.htm

Brief articles: http://www.wjgnet.com/2222-0682/g_info_20100725072920.htm

Case report: http://www.wjgnet.com/2222-0682/g_info_20100725073015.htm

Letters to the editor: http://www.wjgnet.com/2222-0682/g_info_20100725073136.htm

Book reviews: http://www.wjgnet.com/2222-0682/g_info_20100725073214.htm

Guidelines: http://www.wjgnet.com/2222-0682/g_info_20100725073300.htm

SUBMISSION OF THE REVISED MANUSCRIPTS AFTER ACCEPTED

Please revise your article according to the revision policies of *WJM*. The revised version including manuscript and high-resolution image figures (if any) should be re-submitted online (<http://www.wjgnet.com/2222-0682office/>). The author should send the copyright transfer letter, responses to the reviewers, English language Grade B certificate (for non-native speakers of English) and final manuscript checklist to wjm@wjgnet.com.

Language evaluation

The language of a manuscript will be graded before it is sent for revision. (1) Grade A: priority publishing; (2) Grade B: minor language polishing; (3) Grade C: a great deal of language polishing needed; and (4) Grade D: rejected. Revised articles should reach Grade A or B.

Copyright assignment form

Please download a Copyright assignment form from http://www.wjgnet.com/2222-0682/g_info_20100725073726.htm.

Responses to reviewers

Please revise your article according to the comments/suggestions provided by the reviewers. The format for responses to the reviewers' comments can be found at: http://www.wjgnet.com/2222-0682/g_info_20100725073445.htm.

Proof of financial support

For paper supported by a foundation, authors should provide a copy of the document and serial number of the foundation.

Links to documents related to the manuscript

WJM will be initiating a platform to promote dynamic interactions between the editors, peer reviewers, readers and authors. After a manuscript is published online, links to the PDF version of the submitted manuscript, the peer-reviewers' report and the revised manuscript will be put on-line. Readers can make comments on the peer reviewer's report, authors' responses to peer reviewers, and the revised manuscript. We hope that authors will benefit from this feedback and be able to revise the manuscript accordingly in a timely manner.

Science news releases

Authors of accepted manuscripts are suggested to write a science news item to promote their articles. The news will be released rapidly at EurekAlert/AAAS (<http://www.eurekalert.org>). The title for news items should be less than 90 characters; the summary should be less than 75 words; and main body less than 500 words. Science news items should be lawful, ethical, and strictly based on your original content with an attractive title and interesting pictures.

Publication fee

WJM is an international, peer-reviewed, open-access, online journal. Articles published by this journal are distributed under the terms of the Creative Commons Attribution Non-commercial License, which permits use, distribution, and reproduction in any medium, provided the original work is properly cited, the use is non commercial and is otherwise in compliance with the license. Authors of accepted articles must pay a publication fee. The related standards are as follows. Publication fee: 1300 USD per article. Editorial, topic highlights, original articles, brief articles, book reviews and letters to the editor are published free of charge.